

ASME B16.18-2001
[Revision of ANSI B16.18-1984 (R1994)]

CAST COPPER ALLOY SOLDER JOINT PRESSURE FITTINGS

AN AMERICAN NATIONAL STANDARD



The American Society of
Mechanical Engineers



The American Society of
Mechanical Engineers

A N A M E R I C A N N A T I O N A L S T A N D A R D

CAST COPPER ALLOY SOLDER JOINT PRESSURE FITTINGS

ASME B16.18-2001

[Revision of ANSI B16.18-1984 (R1994)]

Date of Issuance: April 19, 2002

The next edition of this Standard is scheduled for publication in 2007. There will be no addenda issued to this edition.

ASME issues written replies to inquiries concerning interpretations of technical aspects of this Standard.

ASME is the registered trademark of The American Society of Mechanical Engineers.

This code or standard was developed under procedures accredited as meeting the criteria for American National Standards. The Standards Committee that approved the code or standard was balanced to assure that individuals from competent and concerned interests have had an opportunity to participate. The proposed code or standard was made available for public review and comment that provides an opportunity for additional public input from industry, academia, regulatory agencies, and the public-at-large.

ASME does not "approve," "rate," or "endorse" any item, construction, proprietary device, or activity.

ASME does not take any position with respect to the validity of any patent rights asserted in connection with any items mentioned in this document, and does not undertake to insure anyone utilizing a standard against liability for infringement of any applicable letters patent, nor assume any such liability. Users of a code or standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, is entirely their own responsibility.

Participation by federal agency representative(s) or person(s) affiliated with industry is not to be interpreted as government or industry endorsement of this code or standard.

ASME accepts responsibility for only those interpretations of this document issued in accordance with the established ASME procedures and policies, which precludes the issuance of interpretations by individuals.

No part of this document may be reproduced in any form,
in an electronic retrieval system or otherwise,
without the prior written permission of the publisher.

The American Society of Mechanical Engineers
Three Park Avenue, New York, NY 10016-5990

Copyright © 2002 by
THE AMERICAN SOCIETY OF MECHANICAL ENGINEERS
All Rights Reserved
Printed in U.S.A.

CONTENTS

Foreword	v
Committee Roster	vi
Correspondence With the B16 Committee	vii
1 Scope	1
1.1 General	1
1.2 Units of Measurement	1
1.3 Convention	1
1.4 References	1
1.5 Quality System	1
2 Pressure–Temperature Ratings	1
2.1 Rating of Fitting and of Joint	1
2.2 Bursting Strength	1
3 Abbreviations	2
4 Size	2
5 Marking	2
6 Material	2
7 Metal Thickness	2
8 Inspection Tolerance	2
8.1 Linear Dimensions	2
8.2 Ovality	2
8.3 Gaging of Solder Joint Ends	2
8.4 Standard Gaging Method of Threaded Ends	2
8.5 Alignment	4
9 Threaded Ends	4
9.1 Thread Type	4
9.2 Countersink or Chamfer	4
9.3 Threading Tolerances	4
9.4 Thread Length	5
10 Configuration of Threaded Ends	5
11 Test	5
Figure	
1 Method of Designating Openings of Fittings	3

Tables

1	Internal Working-Pressure Rating for Cast Copper Alloy Fittings, psi (kPa)	5
2	Inspection Tolerances	5
3	Dimensions of Solder Joint Ends	6
4	Dimensions of Elbows, Tees, and 45 deg Elbows	7
5	Dimensions of Reducing 90 deg Elbows	9
6	Dimensions of Reducing Tees	10
7	Dimensions of Couplings	13
8	Dimensions of Caps and Plugs	15
9	Dimensions of Fitting Reducers	16
10	Dimensions of Solder Joint Elbows and Tees With Pipe Thread Ends (Straight Sizes)	18
11	Dimensions of Solder Joint Elbows and Tees With Pipe Thread Ends (Reducing Sizes)	19
12	Dimensions of Solder Joint Adapters and Fitting Adapters With Pipe Thread Ends (Straight and Reducing Sizes)	21
13	Dimensions of Return Bends (Straight Sizes)	23
14	Dimensions of Supply and Return Tees	23
15	Dimensions of Baseboard Tees (F×F×C)	24
16	Dimensions of Tees	24
17	Dimensions of Baseboard Tees (C×F×C)	25
18	Dimensions of Flush Bushings (FTG×C)	26
19	Dimensions of Flush Bushings (FTG×F)	26

Nonmandatory Annexes

A	Strength of Solder Joints	27
B	Metric (SI) Tables	29
C	Fitting Rating	51
D	References	52
E	Quality System Program	53

FOREWORD

This American National Standard for solder joint fittings was originally developed by a subcommittee of American Standards Association (ASA) Sectional Committee A40 on Minimum Requirements for Plumbing and Standardization of Plumbing Equipment, organized in August 1928, under the procedures of the ASA. Subcommittee No. 11 on Solder-Joint Fittings for Tubing was appointed in October 1936.

At its first meeting, the subcommittee was informed of the investigation of solder joints being carried out by the National Bureau of Standards (now the National Institute of Standards and Technology). It was decided that the committee's scope should cover only solder fittings for use in plumbing. A subgroup was appointed to study the tolerances of commercial fittings, including depth of bore, laying lengths, and diameters of copper tube.

A draft standard was sent to the subcommittee in February 1939; a revision was distributed in August to selected organizations and individuals for review. A new subcommittee draft dated April 1940 was approved by Sectional Committee A40, the sponsor, and following ASA approval, was published in January 1941 as ASA A40.3-1941.

In 1949, the sponsors agreed to transfer responsibility for solder joint fittings to Sectional Committee B16 of ASA, because the fittings were being used in many applications other than plumbing. Subcommittee 9, Standardization of Solder Joint Fittings was established and charged with developing a revised standard. An April 1949 draft was distributed for industry review, resulting in recommended changes. A new draft was approved by Sectional Committee B16, sponsor organizations, and ASA and published as ASA B16.18-1950.

Work began in 1958 on a revision, including improvements in language. It was approved by B16, sponsor organizations, and ASA and published as ASA B16.18-1963. Starting in 1969, a comprehensive review resulted in revisions to clarify the text and to permit additional material. Final approval was granted by the American National Standards Institute (formally ASA) on March 2, 1972, for publication as ANSI B16.18-1972.

The subcommittee, now Subcommittee I, began a new revision on 1974, resulting in the addition of supply and return tees, baseboard tees, and flush bushings, as well as metrication, and change of "bronze" to "copper alloy." The draft finally approved was published as ANSI B16.18-1978.

In 1982, American National Standards Committee B16 became the ASME B16 Standards Committee, operating with the same scope under ASME procedures accredited by ANSI. Subsequently, Subcommittee I merged with Subcommittee J, which had a related scope. A general review was then started, resulting in a number of editorial changes and a few pictorial corrections. Table 2 (now Table 3) was updated to three place decimals from four, bringing the table more in line with practical gaging methods. Table B2 (now Table B3) was correspondingly corrected. Following approval by Subcommittee J, the B16 Standards Committee, and ASME, the American National Standards Institute granted approval on January 13, for publication as ANSI B16.18-1984. The standard was reaffirmed in 1994 with no change.

This 2001 edition of B16.18 contains a defined bursting strength, defined standard gaging method of threaded ends, and other clarifications and updates to text. Following approval by the Standards Committee and ASME, approval as an American National Standard was given on October 17, 2001 with the designation ASME B16.18-2001.

Requests for interpretations and suggestions for revision should be sent to the Secretary, B16 Committee, The American Society of Mechanical Engineers, Three Park Avenue, New York, NY 10016-5990.

ASME B16 COMMITTEE

Standardization of Valves, Flanges, Fittings, and Gaskets

(The following is the roster of the Committee at the time of approval of this Standard.)

OFFICERS

W. N. McLean, *Chair*
H. R. Sonderegger, *Vice Chair*
P. A. Reddington, *Secretary*

COMMITTEE PERSONNEL

R. W. Barnes, Anric Enterprises
R. R. Brodin, Fisher Controls International, Inc.
M. A. Clark, Nibco, Inc.
A. Cohen, Arthur Cohen & Associates
C. E. Floren, Mueller Co.
D. R. Frikken, Solutia, Inc.
G. A. Jolly, Vogt Valve Co.
W. G. Knecht, BW/IP International, Inc.
R. Koester, The William Powell Co.
W. N. McLean, Newco Valves
M. L. Nayyar, Bechtel Power Corp.
P. A. Reddington, The American Society of Mechanical Engineers
R. A. Schmidt, Trinity-Ladish Co.
H. R. Sonderegger, Grinnell Corp.
W. M. Stephan, Flexitallic Inc.
T. F. Stroud, Ductile Iron Pipe Research Association
R. E. White, Richard E. White and Associates
D. A. Williams, Southern Company Services
L. A. Willis, Dow Chemical Co.
W. R. Worley, Union Carbide Corp.

SUBCOMMITTEE J — COPPER AND COPPER ALLOY FLANGES, FLANGED FITTINGS, AND SOLDER JOINT FITTINGS

M. A. Clark, *Chair*, Nibco, Inc.
G. E. Moino, *Secretary*, The American Society of Mechanical Engineers
D. F. Buccicone, Elkhart Products Corp.
A. Cohen, Arthur Cohen & Associates
D. R. Frikken, Solutia, Inc.
A. G. Kireta, Jr., Copper Development Association, Inc.
A. A. Knapp, Canadian Copper/Brass Development Association
L. McDaniel, Mueller Copper Fittings, LP
T. L. Jamison, *Alternate*, Mueller Industries

CORRESPONDENCE WITH THE B16 COMMITTEE

General. ASME standards are developed and maintained with the intent to represent the consensus of concerned interests. As such, users of this Standard may interact with the Committee by requesting interpretations, proposing revisions, and attending Committee meetings. Correspondence should be addressed to:

Secretary, B16 Main Committee
The American Society of Mechanical Engineers
Three Park Avenue
New York, NY 10016-5990

Proposing Revisions. Revisions are made periodically to the Standard to incorporate changes that appear necessary or desirable, as demonstrated by the experience gained from the application of the Standard. Approved revisions will be published periodically.

The Committee welcomes proposals for revisions to this Standard. Such proposals should be as specific as possible, citing the paragraph number(s), the proposed wording, and a detailed description of the reasons for the proposal, including any pertinent documentation.

Interpretations. Upon request, the B16 Committee will render an interpretation of any requirement of the Standard. Interpretations can only be rendered in response to a written request sent to the Secretary of the B16 Main Committee.

The request for interpretation should be clear and unambiguous. It is further recommended that the inquirer submit his/her request in the following format:

Subject:	Cite the applicable paragraph number(s) and the topic of the inquiry.
Edition:	Cite the applicable edition of the Standard for which the interpretation is being requested.
Question:	Phrase the question as a request for an interpretation of a specific requirement suitable for general understanding and use, not as a request for an approval of a proprietary design or situation. The inquirer may also include any plans or drawings, which are necessary to explain the question; however, they should not contain proprietary names or information.

Requests that are not in this format will be rewritten in this format by the Committee prior to being answered, which may inadvertently change the intent of the original request.

ASME procedures provide for reconsideration of any interpretation when or if additional information that might affect an interpretation is available. Further, persons aggrieved by an interpretation may appeal to the cognizant ASME Committee or Subcommittee. ASME does not “approve,” “certify,” “rate,” or “endorse” any item, construction, proprietary device, or activity.

Attending Committee Meetings. The B16 Main Committee regularly holds meetings, which are open to the public. Persons wishing to attend any meeting should contact the Secretary of the B16 Main Committee.

CAST COPPER ALLOY SOLDER JOINT PRESSURE FITTINGS

1 SCOPE

1.1 General

This Standard for cast copper alloy solder joint pressure fittings designed for use with copper water tube, establishes requirements for:

- (a) pressure-temperature ratings;
- (b) abbreviations for end connections;
- (c) sizes and method of designating openings of fittings;
- (d) marking;
- (e) material;
- (f) dimensions and tolerances; and
- (g) tests.

1.2 Units of Measurement

The values stated in either U.S. Customary (inch-lb.) or SI (metric) units of measure shall be regarded separately as standard. Within the main text, U.S. Customary units are given. For convenience, the SI units are shown in parentheses and in Nonmandatory Annex B. The values stated in each system are not exact equivalents; therefore, each system shall be used independently of the other.

NOTE: Combining values from the two systems may result in nonconformance with the Standard.

1.3 Convention

For the purpose of determining conformance with this Standard, the convention for fixing significant digits where units, maximum or minimum values, are specified shall be "rounding off" as defined in ASTM Practice E 29. This requires that an observed or calculated value shall be rounded off to the nearest unit in the last right-hand digit used for expressing the limit.

1.4 References

Standards and specifications adopted by reference in this Standard are shown in Nonmandatory Annex D, which is part of this Standard. It is not considered practical to identify the specific edition of each standard and specification in the individual references. Instead, the specific edition reference is identified in Nonmandatory Annex D.

1.5 Quality System

Requirements relating to the product manufacturer's Quality System Programs are described in Nonmandatory Annex E.

2 PRESSURE-TEMPERATURE RATINGS

2.1 Rating of Fitting and of Joint

The internal working-pressure-temperature rating for a solder joint fitting is dependent not only on fitting and tube strength, but also on the composition of the solder used for the joint and selection of valves and appurtenances.

The internal working-pressure ratings of the system shall be the lowest of the values shown in Table 1 and Nonmandatory Annex A, and those of the tube, valves, or appurtenances.

Pressure-temperature ratings for solder joints to the dimensions of Table 3, made with typical commercial solders, are given in Nonmandatory Annex A.

2.2 Bursting Strength

When tested at $73^{\circ}\text{F} \pm 5^{\circ}\text{F}$ ($23^{\circ}\text{C} \pm 2^{\circ}\text{C}$) fittings manufactured to this standard shall have an ambient-temperature bursting strength of at least four times the 100°F (38°C) internal working-pressure rating as shown in Table 1.

3 ABBREVIATIONS

The following symbols are used to designate the type of fitting end:

- C* = solder-joint fitting end made to receive copper tube diameter (female)
- FTG* = solder-joint fitting end made to copper tube diameter (male)
- F* = internal ANSI standard taper pipe thread (female) NPT
- M* = external ANSI standard taper pipe thread (male) NPT

4 SIZE

The size of the fittings shown in Table 3 and Table A1 corresponds to standard water tube size as shown in ASTM B 88, Specification for Seamless Copper Water Tube. The size of the threaded ends corresponds to nominal pipe size as shown in ASME B1.20.1.

Fittings are designated by the size of the openings in the sequence illustrated in Fig. 1.

5 MARKING

Each fitting shall be permanently marked with the manufacturer's name or trademark and other applicable markings as required by MSS-SP-25. Marking of fittings less than Standard Water Tube Size $\frac{1}{2}$, or on any fitting where it damages soldering surfaces is not required.

6 MATERIAL

Castings shall be copper alloy produced to meet:

- (a) the requirement of ASTM B 62 Alloy C83600;
- (b) the chemical and tensile requirements of ASTM B 584 Alloy C83800 or C84400 and in all other respects comply with the requirements of ASTM B 62.

7 METAL THICKNESS

Dimensional variations occur in the casting process. Pattern equipment shall be designed to produce the metal thickness given for fittings in Table 3 or Table B3. The minimum wall-thickness shall not be less than 90% of the body and joint wall-thickness as shown in Table 3 or Table B3.

8 INSPECTION TOLERANCE

8.1 Linear Dimensions

An inspection tolerance as shown in Table 2 shall be allowed on center-to-shoulder, center-to-center, center-to-threaded end, and shoulder-to-threaded end dimensions on all fittings having female solder (solder cup) ends, and on center-to-solder end and solder-to-threaded end dimensions on all fittings having male solder (fitting) ends.

Coupling inspection limits for shoulder-to-shoulder and shoulder-to-end dimensions shall be double those shown in Table 2, except that the minus tolerance applied to dimensions *M*, *N*, and *W*, and Tables 7 and B7 shall not result in a dimension less than 0.06 in. (1.5 mm) for sizes $\frac{1}{4}$ through 1 in., inclusive, or a dimension less than 0.09 in. (2.3 mm) for the larger sizes.

The largest opening in the fitting governs the tolerance to be applied to all openings.

Tables 3 through 19 offer dimensions for pressure fittings covered by this standard.

8.2 Ovality

Maximum ovality shall not exceed 1% of the maximum diameters shown in Table 3 or Table B3. The average of the maximum and minimum diameters must be within the dimensions shown in the table.


8.3 Gaging of Solder Joint Ends

8.3.1 Standard Gaging Method. The standard method of gaging the diameter tolerances for male and female ends shall be by the use of plain plug and ring gages designed to hold the product within the limits established in Table 3 or B3.

8.3.2 Optional Gaging Method. For gaging the diameter tolerance of male and female ends, the manufacturer may use direct reading instruments instead of ring and plug gages as specified in para. 8.3.1. When gaging the diameters of male and female ends using direct reading instruments, refer to para. 8.2.


8.4 Standard Gaging Method of Threaded Ends

The standard method of gaging the external and internal threaded ends shall be in accordance with the requirements of ASME B1.20.1.

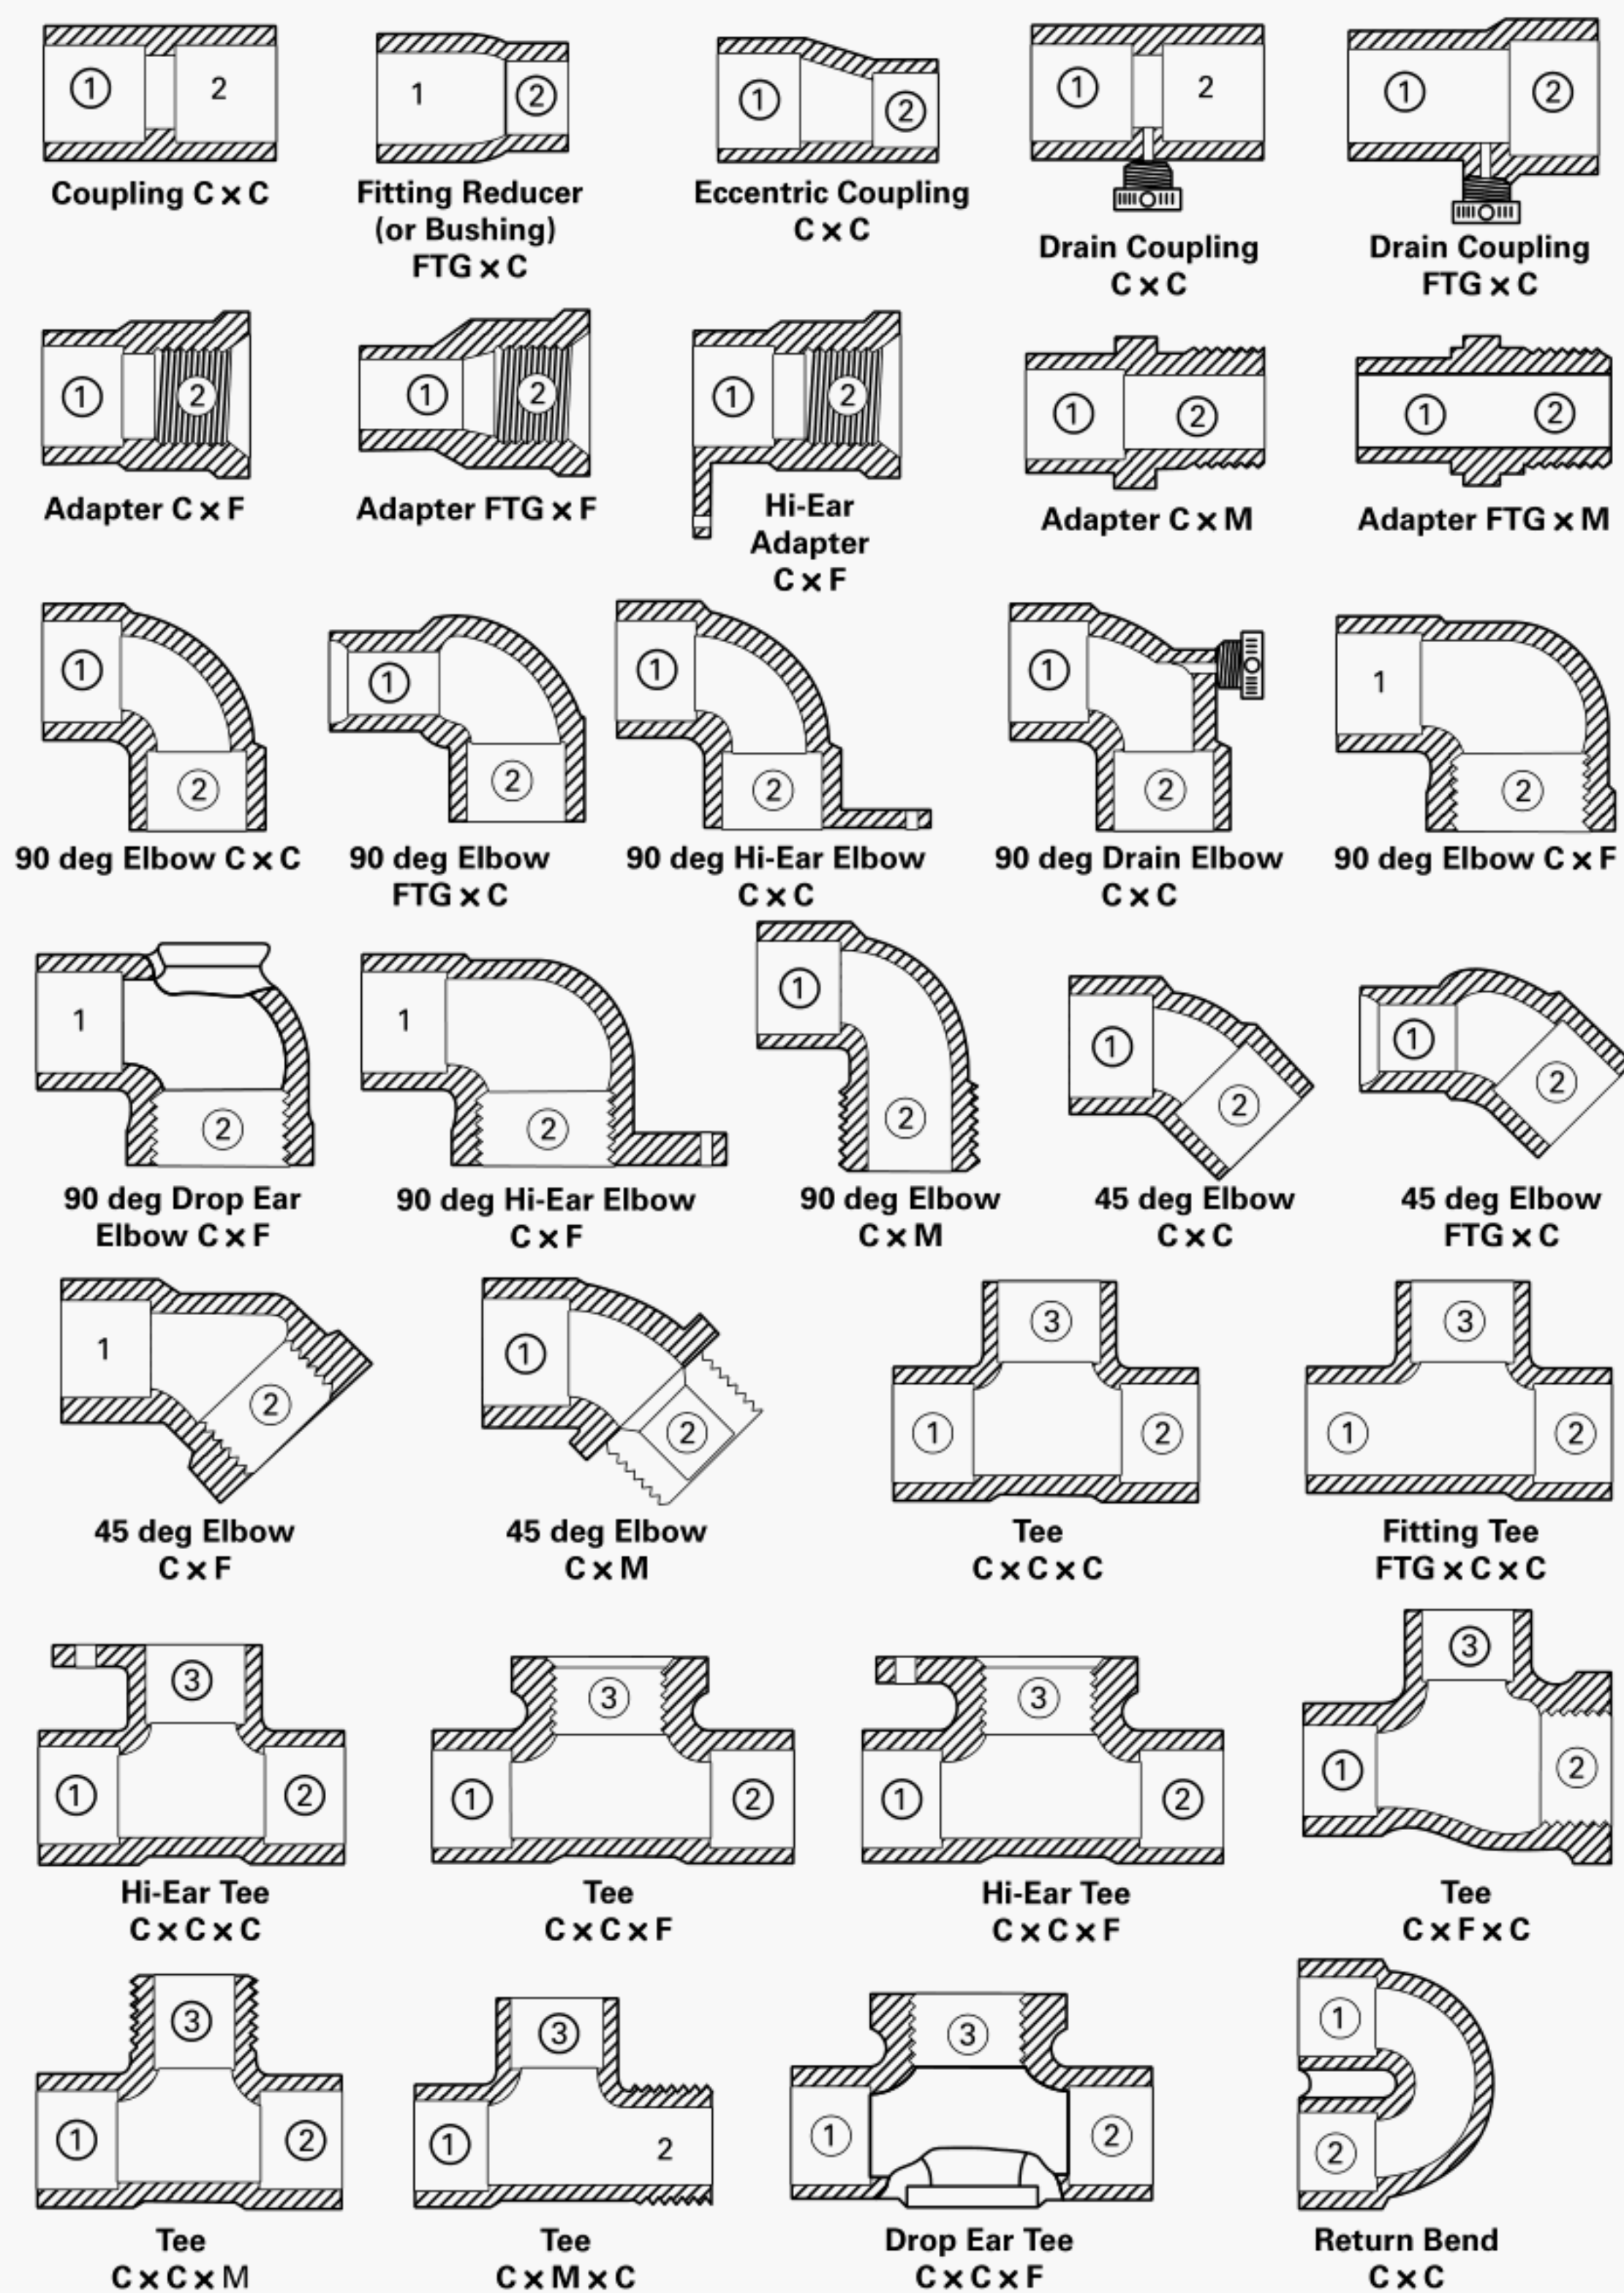

GENERAL NOTE: Fittings are designated by size in the order shown — i.e., 1 x 2 x 3.

FIG.1 METHOD OF DESIGNATING OPENINGS OF FITTINGS

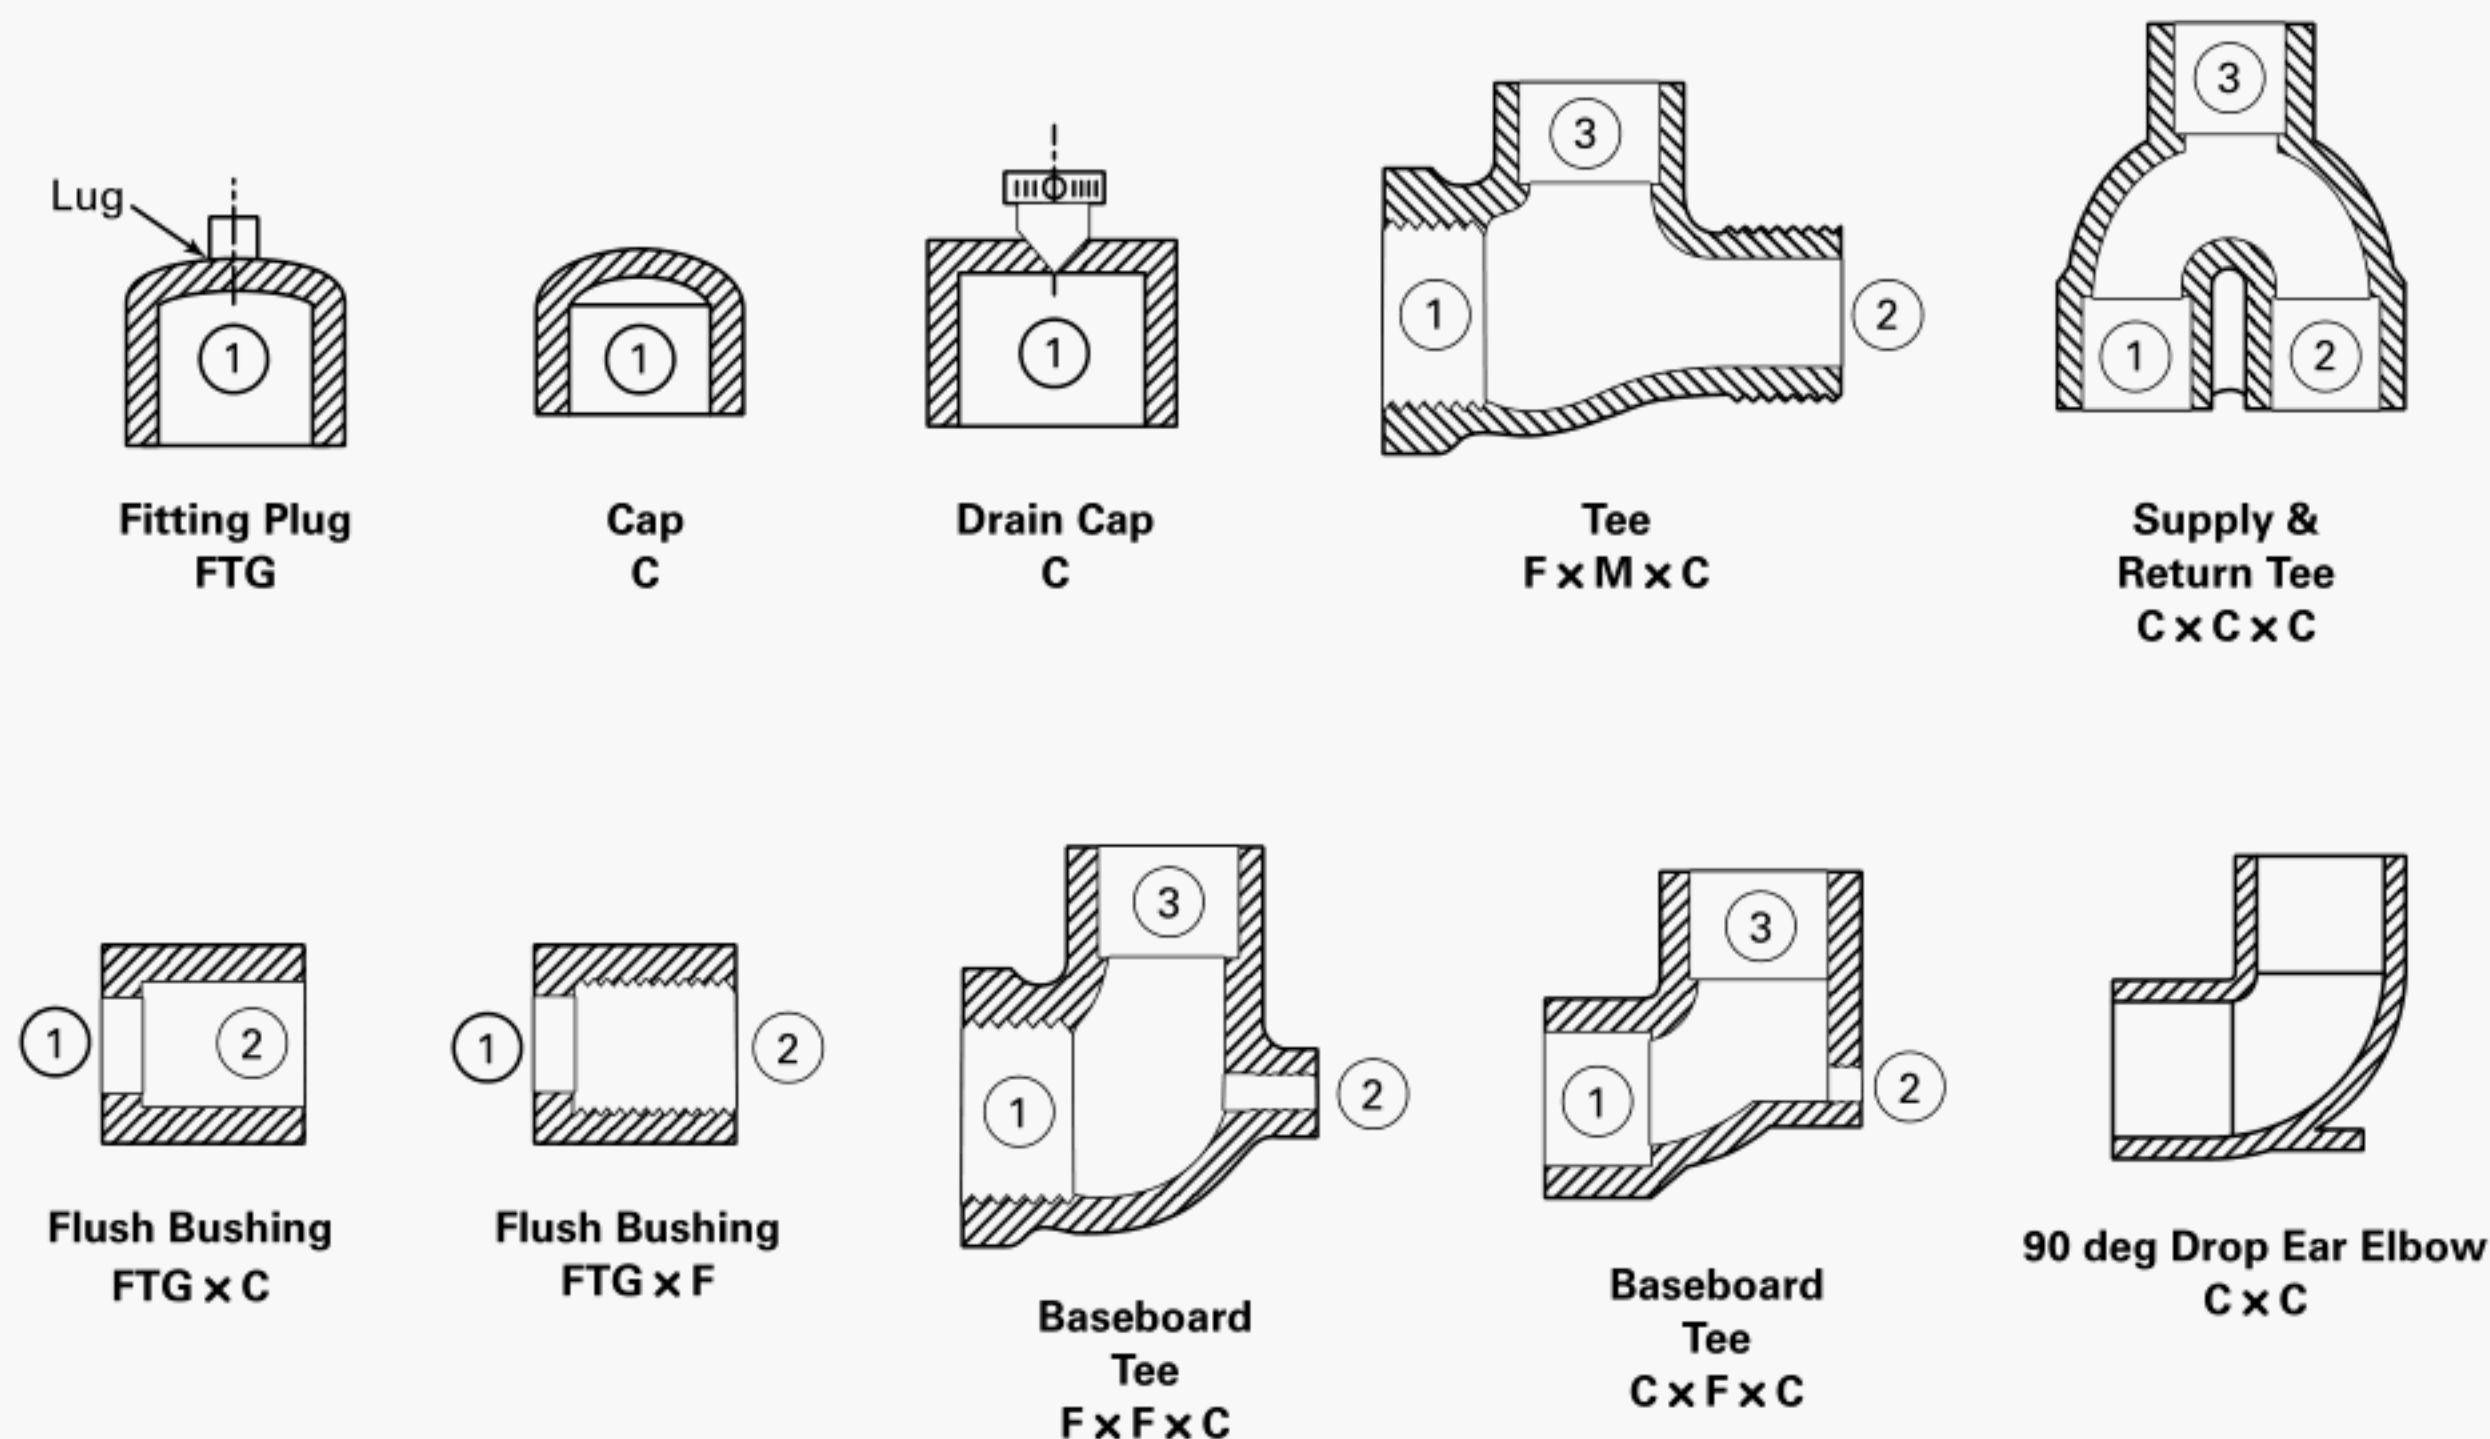

GENERAL NOTE: Fittings are designated by size in the order shown — i.e., 1 x 2 x 3.

FIG.1 METHOD OF DESIGNATING OPENINGS OF FITTINGS (CONT'D)

8.5 Alignment

The maximum-allowable deviation in the angular alignment of any opening shall be 0.06 in./ft (5mm/1 m) (0.5%).

9 THREADED ENDS

9.1 Thread Type

Fitting threads shall be right hand, conforming to ASME B1.20.1, Pipe Threads, General Purpose (Inch). They shall be taper threads (NPT).

9.2 Countersink or Chamfer

All internal threads shall be countersunk a distance not less than one-half the pitch of the thread at an angle approximately 45 deg with the axis of the thread, and all external threads shall be chamfered at an angle of 30 to 45 deg from the axis, for the purpose of

easier entrance in making a joint and protection of the thread. Countersinking and chamfering shall be concentric with the threads.

9.3 Threading Tolerances

Tapered pipe threads (NPT) shall be checked by use of working plug or ring gages in either standard or limit types. Gages shall be threaded on/in hand tight. The reference point for gaging internal product threads depends upon the chamfer diameter. When the internal chamfer diameter exceeds the major diameter of the internal thread, the reference point is the last thread scratch on the chamfer cone. Otherwise, when the internal chamfer diameter does not exceed the major diameter of the internal thread, the reference point is the end of the fitting.

Tolerance for an internal threaded end having an internal shoulder shall be from the gage reference point (notch) to one turn small. Tolerance for an internal

threaded end without shoulder and for an external threaded end shall be from one turn small to one turn large.

9.4 Thread Length

The length of threads specified in all tables shall be measured to include the countersink or chamfer.

10 CONFIGURATION OF THREADED ENDS

At the manufacturer's option, female ends of fittings may be furnished with a polygon or bead with or

without ribs, and male ends of fittings may be furnished with a polygon, ribs, or flats.

11 TEST

These fittings shall be tested at a minimum air pressure of 60 psi (410 kPa) while under water or to a hydrostatic gage pressure of 250 psi (1 720 kPa) for sufficient length of time to assure tightness.

TABLE 1 INTERNAL WORKING-PRESSURE RATING FOR CAST COPPER ALLOY FITTINGS, psi (kPa)


Standard Water Tube Size	–20°F to 100°F (–29°C to 38°C)	150°F (66°C)	200°F (93°C)	250°F (121°C)	300°F (149°C)	350°F (177°C)	400°F (204°C)
1/4	910 (6280)	770 (5340)	725 (5020)	725 (5020)	710 (4920)	605 (4190)	455 (3140)
3/8	775 (5360)	660 (4560)	620 (4290)	620 (4290)	610 (4200)	515 (3570)	385 (2680)
1/2	720 (4970)	610 (4220)	575 (3980)	575 (3980)	565 (3890)	480 (3310)	360 (2480)
5/8	630 (4350)	535 (3700)	505 (3480)	505 (3480)	490 (3410)	420 (2900)	315 (2170)
3/4	580 (4010)	490 (3410)	465 (3210)	465 (3210)	455 (3140)	385 (2670)	290 (2000)
1	490 (3400)	420 (2890)	395 (2720)	395 (2720)	385 (2660)	325 (2270)	245 (1700)
1 1/4	435 (3020)	370 (2570)	350 (2420)	350 (2420)	340 (2370)	290 (2010)	315 (1510)
1 1/2	405 (2810)	345 (2390)	325 (2250)	325 (2250)	315 (2200)	270 (1870)	200 (1400)
2	360 (2500)	305 (2130)	290 (2000)	290 (2000)	280 (1960)	240 (1670)	180 (1250)
2 1/2	335 (2310)	285 (1960)	265 (1850)	265 (1850)	260 (1810)	220 (1540)	165 (1150)
3	315 (2180)	265 (1850)	250 (1740)	250 (1740)	245 (1710)	210 (1450)	155 (1090)
3 1/2	300 (2090)	255 (1770)	240 (1670)	240 (1670)	235 (1630)	200 (1390)	150 (1040)
4	290 (2020)	245 (1710)	230 (1610)	230 (1610)	225 (1580)	195 (1340)	145 (1010)
5	265 (1850)	225 (1570)	215 (1480)	215 (1480)	210 (1450)	175 (1230)	130 (920)
6	250 (1720)	210 (1460)	200 (1380)	200 (1380)	195 (1350)	165 (1150)	125 (860)
8	270 (1860)	225 (1580)	215 (1490)	215 (1490)	210 (1460)	180 (1240)	135 (930)
10	270 (1860)	230 (1580)	215 (1490)	215 (1490)	210 (1460)	180 (1240)	135 (930)
12	250 (1740)	215 (1480)	200 (1390)	200 (1390)	195 (1360)	165 (1160)	125 (870)

GENERAL NOTES:

- For size designation of fittings see Section 4.
- The internal pressure rating applies to the largest opening of the fitting.
- The internal pressure rating is calculated, as shown in Nonmandatory Annex C, then rounded down to the nearest unit of 5 for psi and 10 for kPa.

TABLE 2 INSPECTION TOLERANCES

Standard Water Tube and Pipe Thread Size	Plus or Minus	
	in.	mm
1/4, 3/8	0.05	1.3
1/2, 3/4	0.06	1.5
1 to 2 incl.	0.08	2.0
2 1/2 to 3 1/2 incl.	0.11	2.8
4, 5	0.12	3.2
6, 8	0.16	4.0
10, 12	0.20	5.2

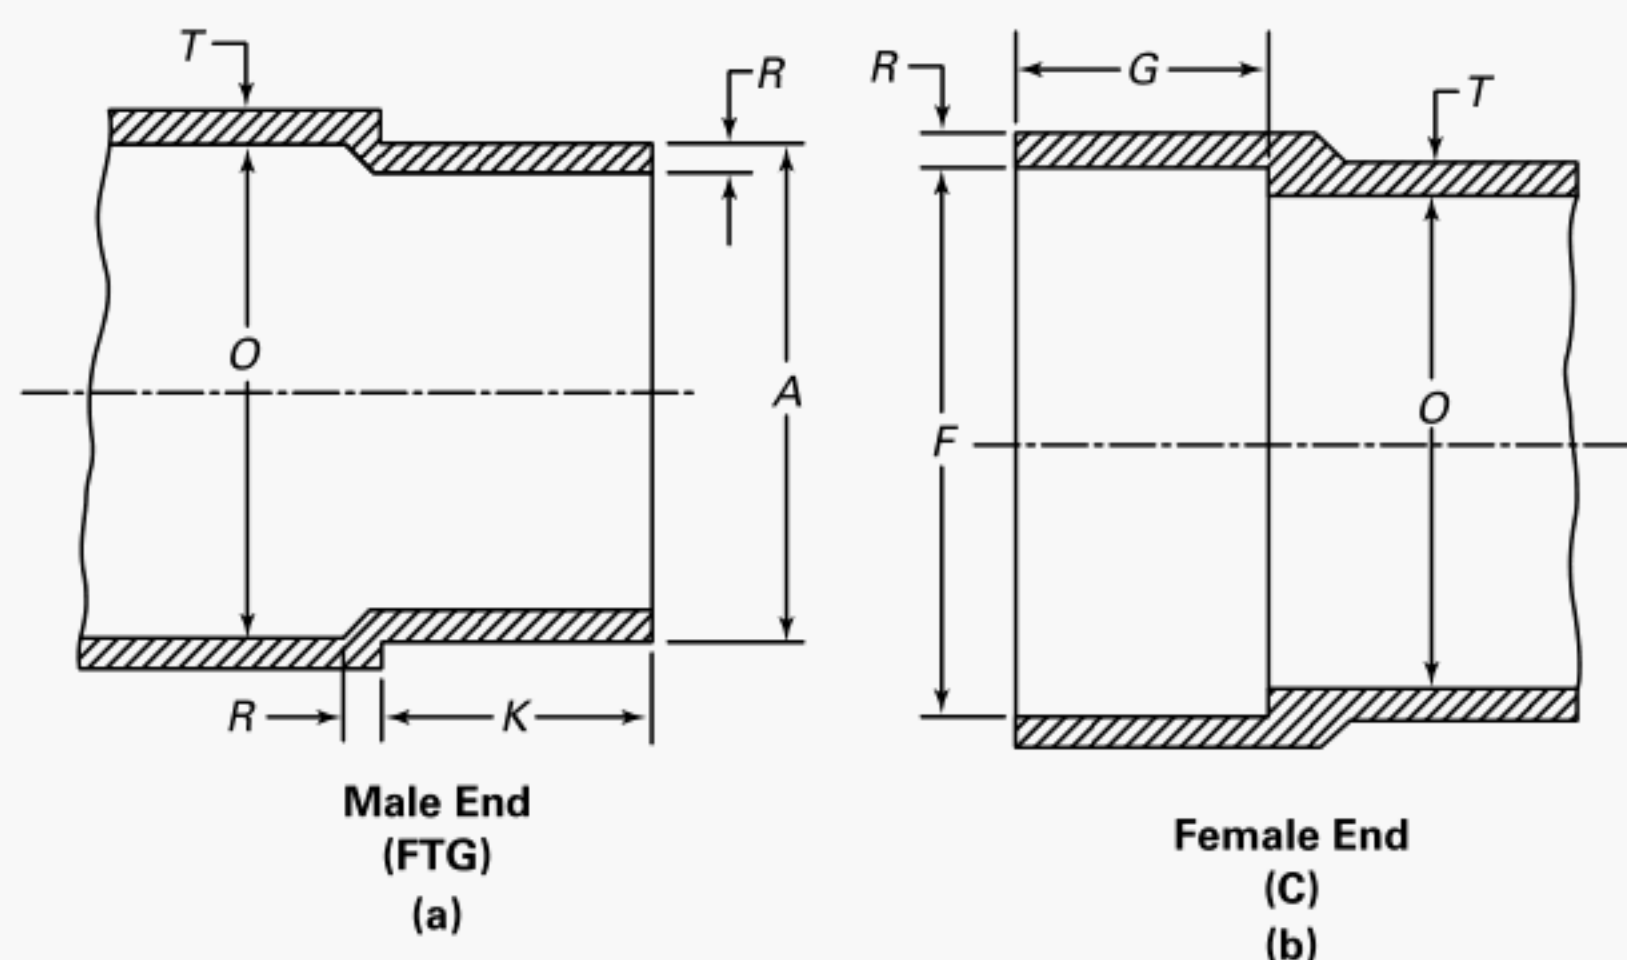**TABLE 3 DIMENSIONS OF SOLDER JOINT ENDS**

Standard Water Tube Size [Note (1)]	Male End			Female End			Metal Thickness [Note (3)]		Inside Diameter of Fitting, <i>O</i> Min.
	Outside Diameter [Note (2)], <i>A</i>		Length, <i>K</i> Min.	Inside Diameter, <i>F</i>		Depth, <i>G</i> Min.	Body, <i>T</i>	Joint, <i>R</i>	
	Min.	Max.		Min.	Max.				
1/4	0.373	0.376	0.38	0.377	0.381	0.31	0.08	0.05	0.31
3/8	0.497	0.501	0.44	0.502	0.506	0.38	0.09	0.05	0.43
1/2	0.622	0.626	0.56	0.627	0.631	0.50	0.09	0.05	0.54
3/4	0.872	0.876	0.81	0.877	0.881	0.75	0.10	0.06	0.78
1	1.122	1.127	0.97	1.128	1.132	0.91	0.11	0.07	1.02
1 1/4	1.372	1.377	1.03	1.378	1.382	0.97	0.12	0.07	1.26
1 1/2	1.621	1.627	1.16	1.628	1.633	1.09	0.13	0.08	1.50
2	2.121	2.127	1.41	2.128	2.133	1.34	0.15	0.09	1.98
2 1/2	2.621	2.627	1.53	2.628	2.633	1.47	0.17	0.10	2.46
3	3.121	3.127	1.72	3.128	3.133	1.66	0.19	0.11	2.94
3 1/2	3.621	3.627	1.97	3.628	3.633	1.91	0.20	0.12	3.42
4	4.121	4.127	2.22	4.128	4.133	2.16	0.22	0.13	3.90
5	5.121	5.127	2.72	5.128	5.133	2.66	0.28	0.17	4.87
6	6.121	6.127	3.22	6.128	6.133	3.09	0.34	0.20	5.84
8	8.119	8.127	4.09	8.128	8.133	3.97	0.38	0.31	7.72
10	10.119	10.127	4.12	10.128	10.133	4.00	0.48	0.48	9.62
12	12.119	12.127	4.62	12.128	12.133	4.50	0.56	0.56	11.56

GENERAL NOTES:

(a) Dimensions are in inches.


(b) The sketches and designs of fittings are illustrative only. Dimensions herein shall govern in all cases.

NOTES:

(1) For size designation of fitting, see Section 4.

(2) For ovality and gaging tolerances, see Section 8.

(3) For metal thickness, see Section 7.

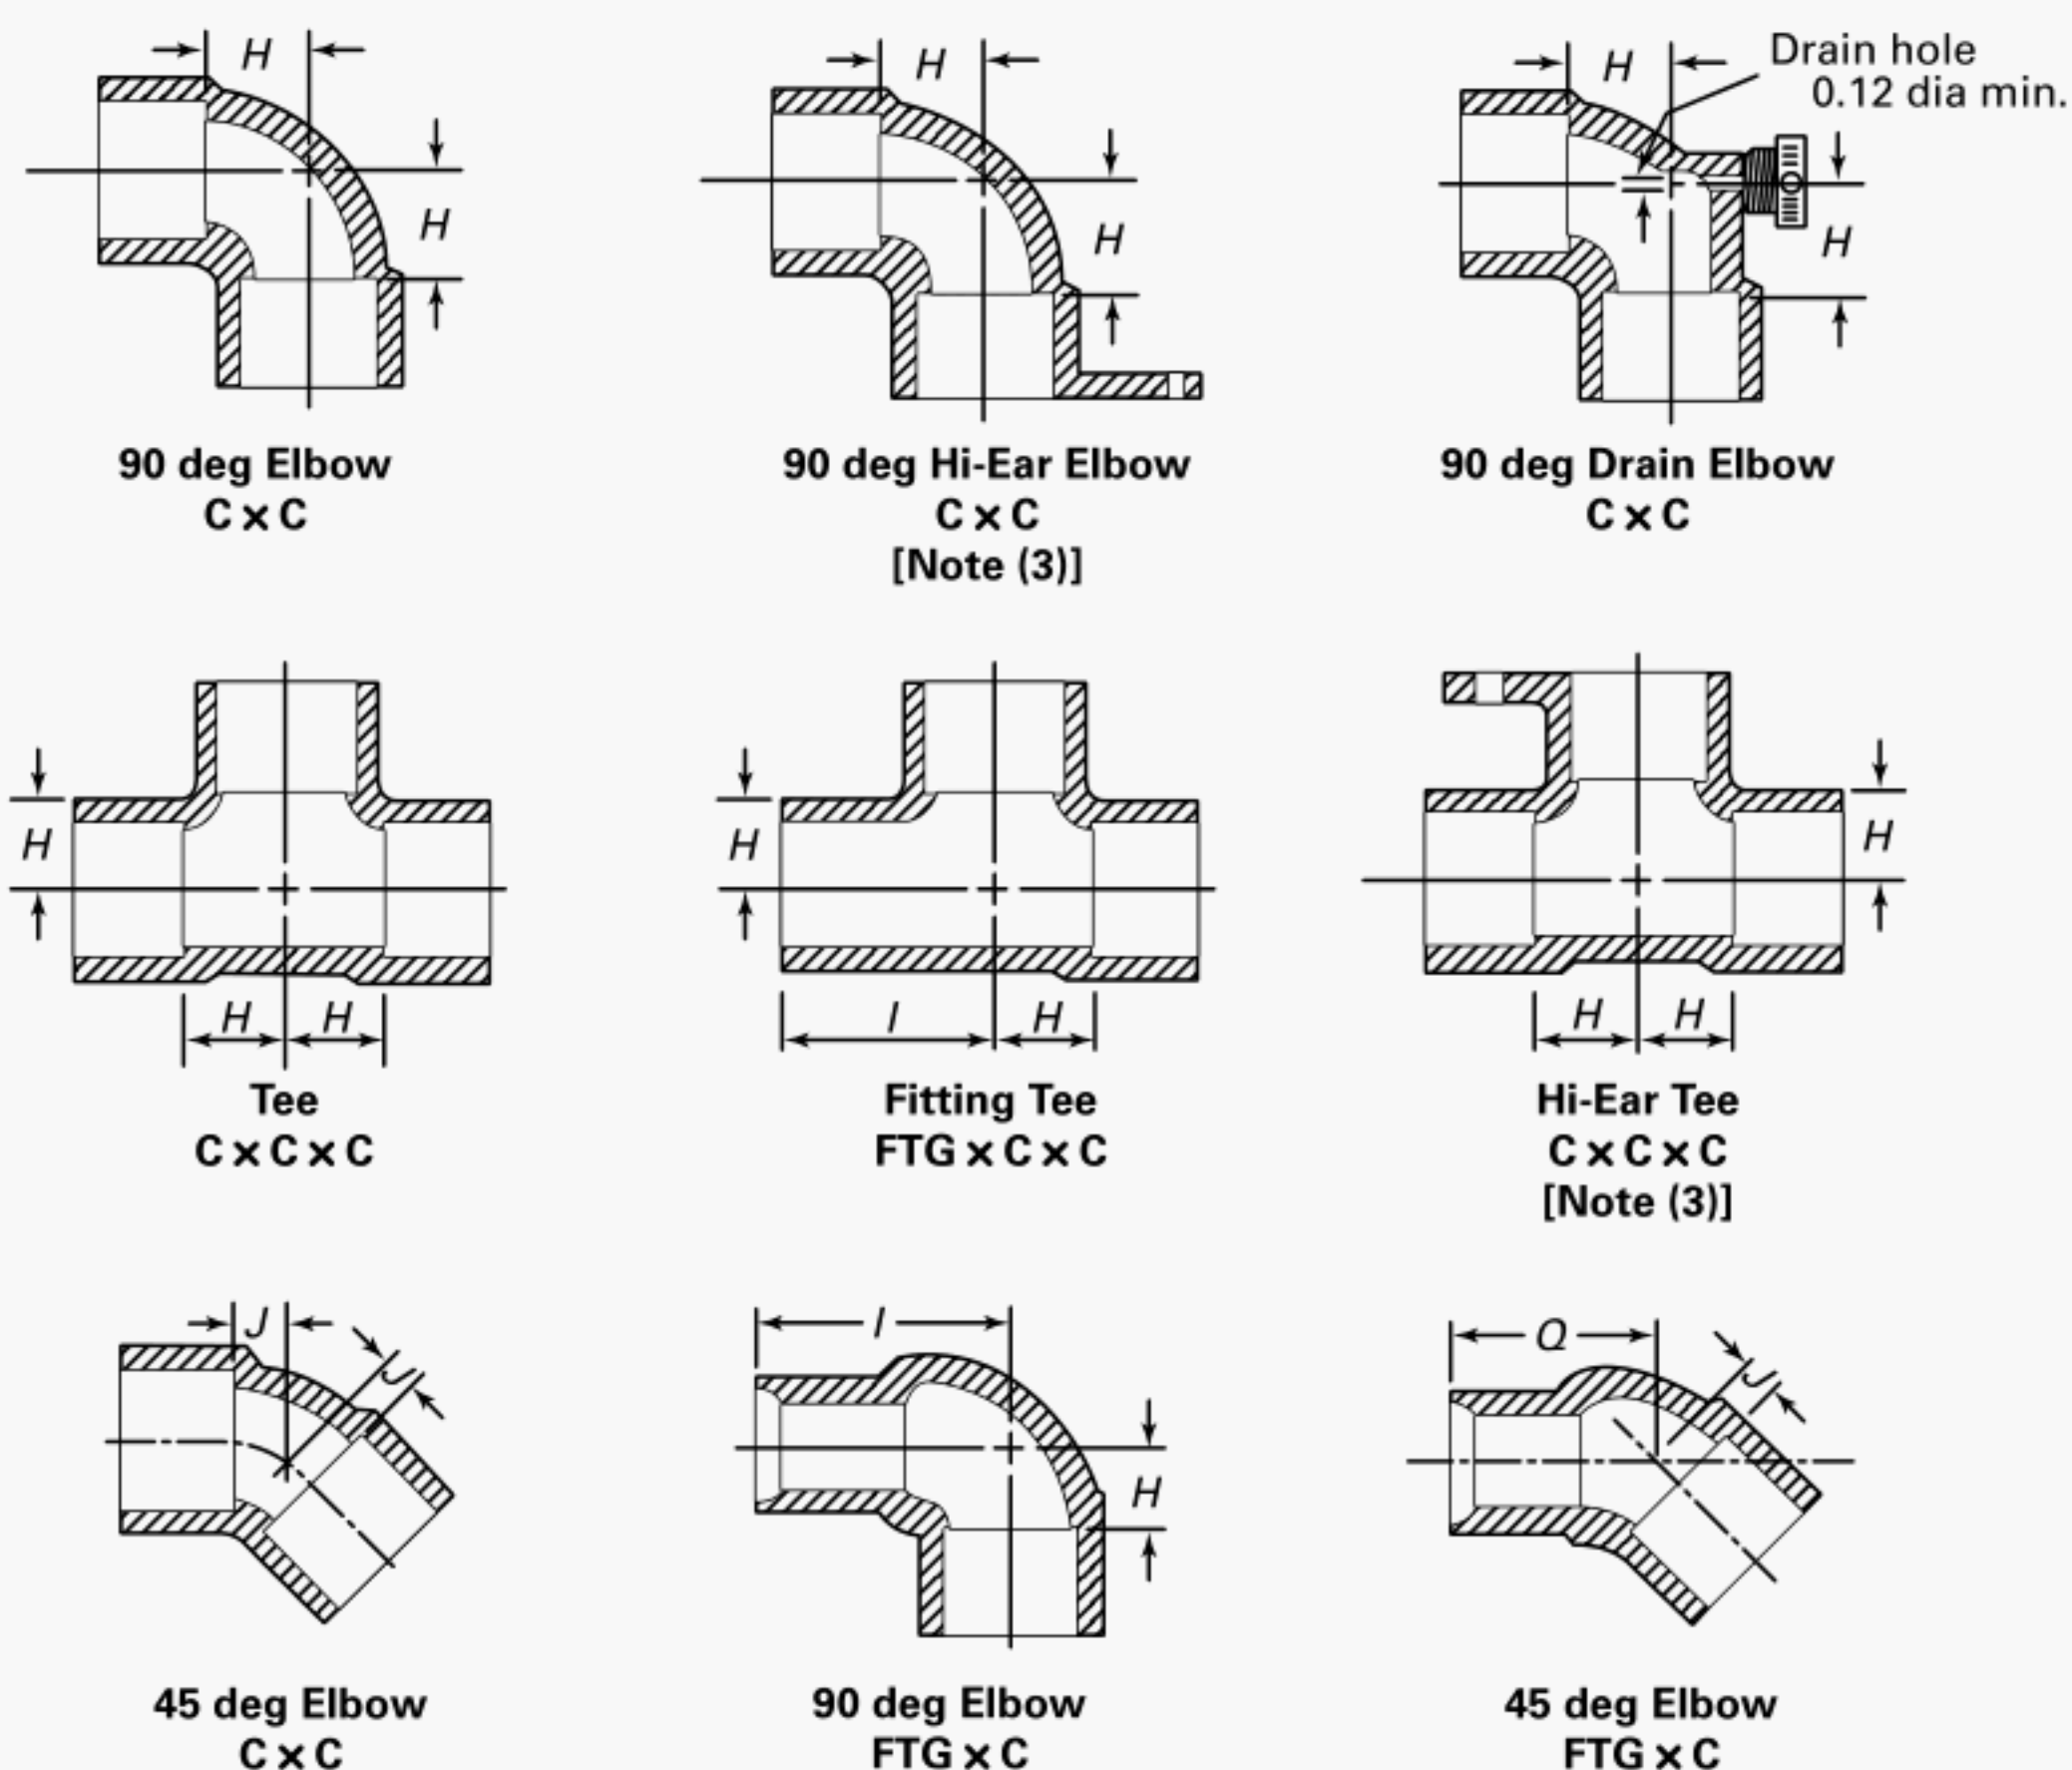**TABLE 4 DIMENSIONS OF ELBOW, TEES, AND 45 deg ELBOWS**

Standard Water Tube Size [Note (1)]	Laying Length Tee and 90 deg Elbow [Note (2)], <i>H</i>	Center-to-End 90 deg Elbow and Tee, [Note (2)], <i>I</i>	Laying Length 45 deg Elbow [Note (2)], <i>J</i>	Center-to-End 45 deg Elbow [Note (2)], <i>Q</i>
1/4	0.25	0.75
3/8	0.31	0.88	0.19	0.75
1/2	0.44	1.12	0.19	0.88
3/4	0.56	1.50	0.25	1.19
1	0.75	1.84	0.31	1.31
1 1/4	0.88	2.03	0.44	1.56
1 1/2	1.00	2.28	0.50	1.75
2	1.25	2.78	0.56	2.12
2 1/2	1.50	3.16	0.62	...
3	1.75	3.59	0.75	...
3 1/2	2.00	...	0.88	...
4	2.25	4.59	0.94	...
5	3.12	...	1.44	...
6	3.62	...	1.62	...
8	4.88	...	2.12	...

(continued)

TABLE 4 (CONT'D)

GENERAL NOTES:

(a) Dimensions are in inches.


(b) For dimensions not given in this table, see Table 3.

NOTES:

(1) For size designation of fitting, see Section 4.

(2) For inspection tolerances, see Section 8 and Table 2.

(3) Hi-ear fittings are designed for use with $\frac{9}{16}$ in. maximum width strap.

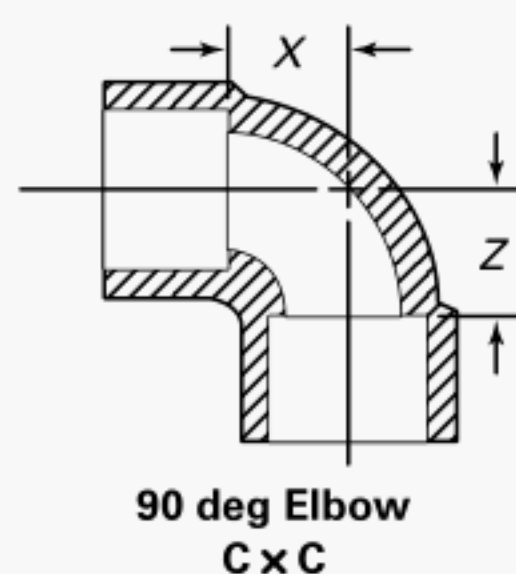**TABLE 5 DIMENSIONS OF REDUCING 90 deg ELBOWS**


Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]	
	X	Z
$\frac{3}{8} \times \frac{1}{4}$	0.25	0.31
$\frac{1}{2} \times \frac{3}{8}$	0.38	0.44
$\frac{3}{4} \times \frac{1}{2}$	0.44	0.56
$1 \times \frac{3}{4}$	0.62	0.75
$1 \times \frac{1}{2}$	0.50	0.75
$1\frac{1}{4} \times 1$	0.75	0.88
$1\frac{1}{4} \times \frac{3}{4}$	0.62	0.88
$1\frac{1}{4} \times \frac{1}{2}$	0.50	0.88
$1\frac{1}{2} \times 1\frac{1}{4}$	0.88	1.00
$1\frac{1}{2} \times 1$	0.75	1.00
$1\frac{1}{2} \times \frac{3}{4}$	0.62	1.00
$2 \times 1\frac{1}{2}$	1.00	1.25
$2 \times 1\frac{1}{4}$	0.88	1.25
2×1	0.75	1.25
$2 \times \frac{3}{4}$	0.62	1.25
$2\frac{1}{2} \times 2$	1.25	1.50
$2\frac{1}{2} \times 1\frac{1}{2}$	1.00	1.50
$2\frac{1}{2} \times 1\frac{1}{4}$	0.88	1.50
$2\frac{1}{2} \times 1$	0.75	1.50
$3 \times 2\frac{1}{2}$	1.50	1.75
3×2	1.25	1.75
$3 \times 1\frac{1}{2}$	1.00	1.75
$3 \times 1\frac{1}{4}$	0.88	1.75
4×3	1.75	2.25
$4 \times 2\frac{1}{2}$	1.50	2.25
4×2	1.25	2.25
6×4	2.62	3.62
6×3	2.00	3.62
8×6	3.88	4.88

GENERAL NOTES:

- (a) Dimensions are in inches.
 (b) For dimensions not given in this Table, see Table 3.

NOTES:

- (1) For size designation of fitting, see Section 4.
 (2) For inspection tolerances, see Section 8 and Table 2.

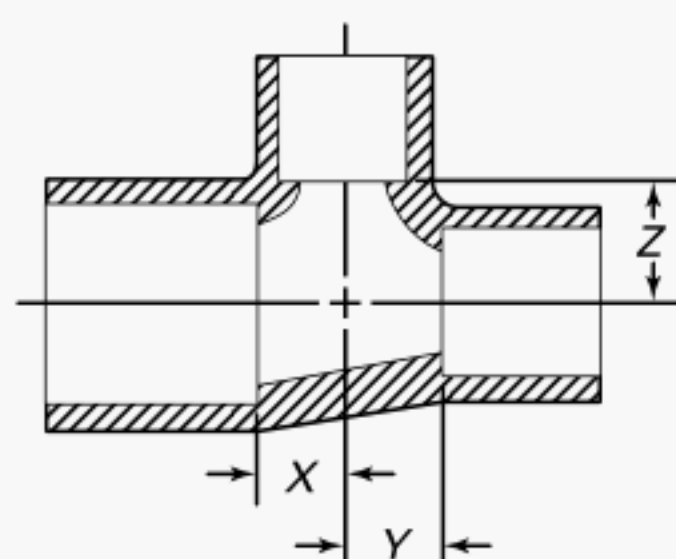

Tee
C x C x C

TABLE 6 DIMENSIONS OF REDUCING TEES

Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]			Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]		
	X	Y	Z		X	Y	Z
$\frac{3}{8} \times \frac{3}{8} \times \frac{1}{2}$	0.44	0.44	0.38	$1\frac{1}{4} \times \frac{3}{4} \times \frac{3}{4}$	0.62	0.62	0.88
$\frac{3}{8} \times \frac{3}{8} \times \frac{1}{4}$	0.25	0.25	0.31	$1\frac{1}{4} \times \frac{1}{2} \times 1\frac{1}{4}$	0.88	0.88	0.88
$\frac{1}{2} \times \frac{1}{2} \times \frac{3}{4}$	0.56	0.56	0.44	$1\frac{1}{4} \times \frac{1}{2} \times 1$	0.75	0.75	0.88
$\frac{1}{2} \times \frac{1}{2} \times \frac{3}{8}$	0.38	0.38	0.44	$1\frac{1}{2} \times 1\frac{1}{2} \times 2\frac{1}{2}$	1.50	1.50	1.00
$\frac{1}{2} \times \frac{1}{2} \times \frac{1}{4}$	0.31	0.31	0.44	$1\frac{1}{2} \times 1\frac{1}{2} \times 2$	1.25	1.25	1.00
$\frac{1}{2} \times \frac{3}{8} \times \frac{1}{2}$	0.44	0.44	0.44	$1\frac{1}{2} \times 1\frac{1}{2} \times 1\frac{1}{4}$	0.88	0.88	1.00
$\frac{1}{2} \times \frac{3}{8} \times \frac{3}{8}$	0.38	0.38	0.44	$1\frac{1}{2} \times 1\frac{1}{2} \times 1$	0.75	0.75	1.00
$\frac{3}{4} \times \frac{3}{4} \times 1$	0.75	0.75	0.62	$1\frac{1}{2} \times 1\frac{1}{2} \times \frac{3}{4}$	0.62	0.62	1.00
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$	0.44	0.44	0.56	$1\frac{1}{2} \times 1\frac{1}{2} \times \frac{1}{2}$	0.50	0.50	1.00
$\frac{3}{4} \times \frac{3}{4} \times \frac{3}{8}$	0.38	0.38	0.56	$1\frac{1}{2} \times 1\frac{1}{4} \times 1\frac{1}{2}$	1.00	1.00	1.00
$\frac{3}{4} \times \frac{1}{2} \times \frac{3}{4}$	0.56	0.56	0.56	$1\frac{1}{2} \times 1\frac{1}{4} \times 1\frac{1}{4}$	0.88	0.88	1.00
$\frac{3}{4} \times \frac{1}{2} \times \frac{1}{2}$	0.44	0.44	0.56	$1\frac{1}{2} \times 1\frac{1}{4} \times 1$	0.75	0.75	1.00
$\frac{3}{4} \times \frac{1}{2} \times \frac{3}{8}$	0.38	0.38	0.56	$1\frac{1}{2} \times 1\frac{1}{4} \times \frac{3}{4}$	0.62	0.62	1.00
$1 \times 1 \times 1\frac{1}{2}$	1.00	1.00	0.75	$1\frac{1}{2} \times 1\frac{1}{4} \times \frac{1}{2}$	0.50	0.50	1.00
$1 \times 1 \times 1\frac{1}{4}$	0.88	0.88	0.75	$1\frac{1}{2} \times 1 \times 1\frac{1}{2}$	1.00	1.00	1.00
$1 \times 1 \times \frac{3}{4}$	0.62	0.62	0.75	$1\frac{1}{2} \times 1 \times 1\frac{1}{4}$	0.88	0.88	1.00
$1 \times 1 \times \frac{1}{2}$	0.50	0.50	0.75	$1\frac{1}{2} \times 1 \times 1$	0.75	0.75	1.00
$1 \times 1 \times \frac{3}{8}$	0.44	0.44	0.75	$1\frac{1}{2} \times \frac{3}{4} \times 1\frac{1}{2}$	1.00	1.00	1.00
$1 \times \frac{3}{4} \times 1$	0.75	0.75	0.75	$1\frac{1}{2} \times \frac{1}{2} \times 1\frac{1}{2}$	1.00	1.00	1.00
$1 \times \frac{3}{4} \times \frac{3}{4}$	0.62	0.62	0.75	$2 \times 2 \times 4$	2.25	2.25	1.25
$1 \times \frac{3}{4} \times \frac{1}{2}$	0.50	0.50	0.75	$2 \times 2 \times 3$	1.75	1.75	1.25
$1 \times \frac{1}{2} \times 1$	0.75	0.75	0.75	$2 \times 2 \times 2\frac{1}{2}$	1.50	1.50	1.25
$1 \times \frac{1}{2} \times \frac{3}{4}$	0.62	0.62	0.75	$2 \times 2 \times 1\frac{1}{2}$	1.00	1.00	1.25
$1 \times \frac{1}{2} \times \frac{1}{2}$	0.50	0.50	0.75	$2 \times 2 \times 1\frac{1}{4}$	0.88	0.88	1.25
$1\frac{1}{4} \times 1\frac{1}{4} \times 2$	1.25	1.25	0.88	$2 \times 2 \times 1$	0.75	0.75	1.25
$1\frac{1}{4} \times 1\frac{1}{4} \times 1\frac{1}{2}$	1.00	1.00	0.88	$2 \times 2 \times \frac{3}{4}$	0.62	0.62	1.25
$1\frac{1}{4} \times 1\frac{1}{4} \times 1$	0.75	0.75	0.88	$2 \times 2 \times \frac{1}{2}$	0.50	0.50	1.25
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{3}{4}$	0.62	0.62	0.88	$2 \times 1\frac{1}{2} \times 2$	1.25	1.25	1.25
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{1}{2}$	0.50	0.50	0.88	$2 \times 1\frac{1}{2} \times 1\frac{1}{2}$	1.00	1.00	1.25
$1\frac{1}{4} \times 1 \times 1\frac{1}{4}$	0.88	0.88	0.88	$2 \times 1\frac{1}{2} \times 1\frac{1}{4}$	0.88	0.88	1.25
$1\frac{1}{4} \times 1 \times 1$	0.75	0.75	0.88	$2 \times 1\frac{1}{2} \times 1$	0.75	0.75	1.25
$1\frac{1}{4} \times 1 \times \frac{3}{4}$	0.62	0.62	0.88	$2 \times 1\frac{1}{2} \times \frac{3}{4}$	0.62	0.62	1.25
$1\frac{1}{4} \times 1 \times \frac{1}{2}$	0.50	0.50	0.88	$2 \times 1\frac{1}{2} \times \frac{1}{2}$	0.50	0.50	1.25
$1\frac{1}{4} \times \frac{3}{4} \times 1\frac{1}{4}$	0.88	0.88	0.88	$2 \times 1\frac{1}{4} \times 2$	1.25	1.25	1.25
$1\frac{1}{4} \times \frac{3}{4} \times 1$	0.75	0.75	0.88	$2 \times 1\frac{1}{4} \times 1\frac{1}{2}$	1.00	1.00	1.25

(continued)

TABLE 6 DIMENSIONS OF REDUCING TEES (CONT'D)

Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]			Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]		
	X	Y	Z		X	Y	Z
$2 \times 1\frac{1}{4} \times 1\frac{1}{4}$	0.88	0.88	1.25	$3 \times 2 \times 1\frac{1}{2}$	1.00	1.00	1.75
$2 \times 1 \times 2$	1.25	1.25	1.25	$3 \times 1\frac{1}{2} \times 3$	1.75	1.75	1.75
$2 \times \frac{3}{4} \times 2$	1.25	1.25	1.25	$3 \times 1\frac{1}{4} \times 3$	1.75	1.75	1.75
$2 \times \frac{1}{2} \times 2$	1.25	1.25	1.25	$3 \times 1 \times 3$	1.75	1.75	1.75
$2\frac{1}{2} \times 2\frac{1}{2} \times 4$	2.25	2.25	1.50	$3\frac{1}{2} \times 3\frac{1}{2} \times 3$	1.75	1.75	2.00
$2\frac{1}{2} \times 2\frac{1}{2} \times 3$	1.75	1.75	1.50	$3\frac{1}{2} \times 3 \times 3\frac{1}{2}$	2.00	2.00	2.00
$2\frac{1}{2} \times 2\frac{1}{2} \times 2$	1.25	1.25	1.50	$4 \times 4 \times 6$	3.62	3.62	2.62
$2\frac{1}{2} \times 2\frac{1}{2} \times 1\frac{1}{2}$	1.00	1.00	1.50	$4 \times 4 \times 3$	1.75	1.75	2.25
$2\frac{1}{2} \times 2\frac{1}{2} \times 1\frac{1}{4}$	0.88	0.88	1.50	$4 \times 4 \times 2\frac{1}{2}$	1.50	1.50	2.25
$2\frac{1}{2} \times 2\frac{1}{2} \times 1$	0.75	0.75	1.50	$4 \times 4 \times 2$	1.25	1.25	2.25
$2\frac{1}{2} \times 2\frac{1}{2} \times \frac{3}{4}$	0.62	0.62	1.50	$4 \times 4 \times 1\frac{1}{2}$	1.00	1.00	2.25
$2\frac{1}{2} \times 2\frac{1}{2} \times \frac{1}{2}$	0.50	0.50	1.50	$4 \times 4 \times 1\frac{1}{4}$	0.88	0.88	2.25
$2\frac{1}{2} \times 2 \times 2\frac{1}{2}$	1.50	1.50	1.50	$4 \times 4 \times 1$	0.75	0.75	2.25
$2\frac{1}{2} \times 2 \times 2$	1.25	1.25	1.50	$4 \times 4 \times \frac{3}{4}$	0.62	0.62	2.25
$2\frac{1}{2} \times 2 \times 1\frac{1}{2}$	1.00	1.00	1.50	$4 \times 3 \times 4$	2.25	2.25	2.25
$2\frac{1}{2} \times 2 \times 1\frac{1}{4}$	0.88	0.88	1.50	$4 \times 3 \times 3$	1.75	1.75	2.25
$2\frac{1}{2} \times 2 \times 1$	0.75	0.75	1.50	$4 \times 3 \times 2\frac{1}{2}$	1.50	1.50	2.25
$2\frac{1}{2} \times 2 \times \frac{3}{4}$	0.62	0.62	1.50	$4 \times 3 \times 2$	1.25	1.25	2.25
$2\frac{1}{2} \times 2 \times \frac{1}{2}$	0.50	0.50	1.50	$4 \times 2\frac{1}{2} \times 4$	2.25	2.25	2.25
$2\frac{1}{2} \times 1\frac{1}{2} \times 2\frac{1}{2}$	1.50	1.50	1.50	$4 \times 2 \times 4$	2.25	2.25	2.25
$2\frac{1}{2} \times 1\frac{1}{2} \times 2$	1.25	1.25	1.50	$4 \times 2 \times 3$	1.75	1.75	2.25
$2\frac{1}{2} \times 1\frac{1}{2} \times 1\frac{1}{2}$	1.00	1.00	1.50	$4 \times 2 \times 2$	1.25	1.25	2.25
$2\frac{1}{2} \times 1\frac{1}{4} \times 2\frac{1}{2}$	1.50	1.50	1.50	$4 \times 1\frac{1}{2} \times 4$	2.25	2.25	2.25
$2\frac{1}{2} \times 1 \times 2\frac{1}{2}$	1.50	1.50	1.50	$4 \times 1\frac{1}{4} \times 4$	2.25	2.25	2.25
$2\frac{1}{2} \times \frac{3}{4} \times 2\frac{1}{2}$	1.50	1.50	1.50	$4 \times 1 \times 4$	2.25	2.25	2.25
$2\frac{1}{2} \times \frac{1}{2} \times 2\frac{1}{2}$	1.50	1.50	1.50	$5 \times 5 \times 4$	2.62	2.62	3.12
$3 \times 3 \times 4$	2.25	2.25	1.75	$5 \times 4 \times 5$	3.12	3.12	3.12
$3 \times 3 \times 2\frac{1}{2}$	1.50	1.50	1.75	$6 \times 6 \times 8$	4.88	4.88	3.88
$3 \times 3 \times 2$	1.25	1.25	1.75	$6 \times 6 \times 4$	2.62	2.62	3.62
$3 \times 3 \times 1\frac{1}{2}$	1.00	1.00	1.75	$6 \times 6 \times 3$	2.00	2.00	3.62
$3 \times 3 \times 1\frac{1}{4}$	0.88	0.88	1.75	$6 \times 6 \times 2\frac{1}{2}$	1.88	1.88	3.62
$3 \times 3 \times 1$	0.75	0.75	1.75	$6 \times 6 \times 2$	1.62	1.62	3.62
$3 \times 3 \times \frac{3}{4}$	0.62	0.62	1.75	$6 \times 6 \times 1\frac{1}{2}$	1.38	1.38	3.62
$3 \times 3 \times \frac{1}{2}$	0.50	0.50	1.75	$6 \times 6 \times 1\frac{1}{4}$	1.25	1.25	3.62
$3 \times 2\frac{1}{2} \times 3$	1.75	1.75	1.75	$6 \times 6 \times 1$	1.12	1.12	3.62
$3 \times 2\frac{1}{2} \times 2\frac{1}{2}$	1.50	1.50	1.75	$6 \times 4 \times 6$	3.62	3.62	3.62
$3 \times 2\frac{1}{2} \times 2$	1.25	1.25	1.75	$6 \times 4 \times 4$	2.62	2.62	3.62
$3 \times 2\frac{1}{2} \times 1\frac{1}{2}$	1.00	1.00	1.75	$6 \times 3 \times 6$	3.62	3.62	3.62
$3 \times 2\frac{1}{2} \times 1\frac{1}{4}$	0.88	0.88	1.75	$6 \times 2\frac{1}{2} \times 6$	3.62	3.62	3.62
$3 \times 2\frac{1}{2} \times 1$	0.75	0.75	1.75	$6 \times 2 \times 6$	3.62	3.62	3.62
$3 \times 2 \times 3$	1.75	1.75	1.75	$8 \times 8 \times 6$	3.88	3.88	4.88
$3 \times 2 \times 2\frac{1}{2}$	1.50	1.50	1.75	$8 \times 8 \times 4$	2.88	2.88	4.88
$3 \times 2 \times 2$	1.25	1.25	1.75

(continued)

TABLE 6 (CONT'D)

GENERAL NOTES:


(a) Dimensions are in inches.

(b) For dimensions not given in this table, see Table 3.

NOTES:

(1) For size designation of fitting, see Section 4.

(2) For inspection tolerances, see Section 8 and Table 2.

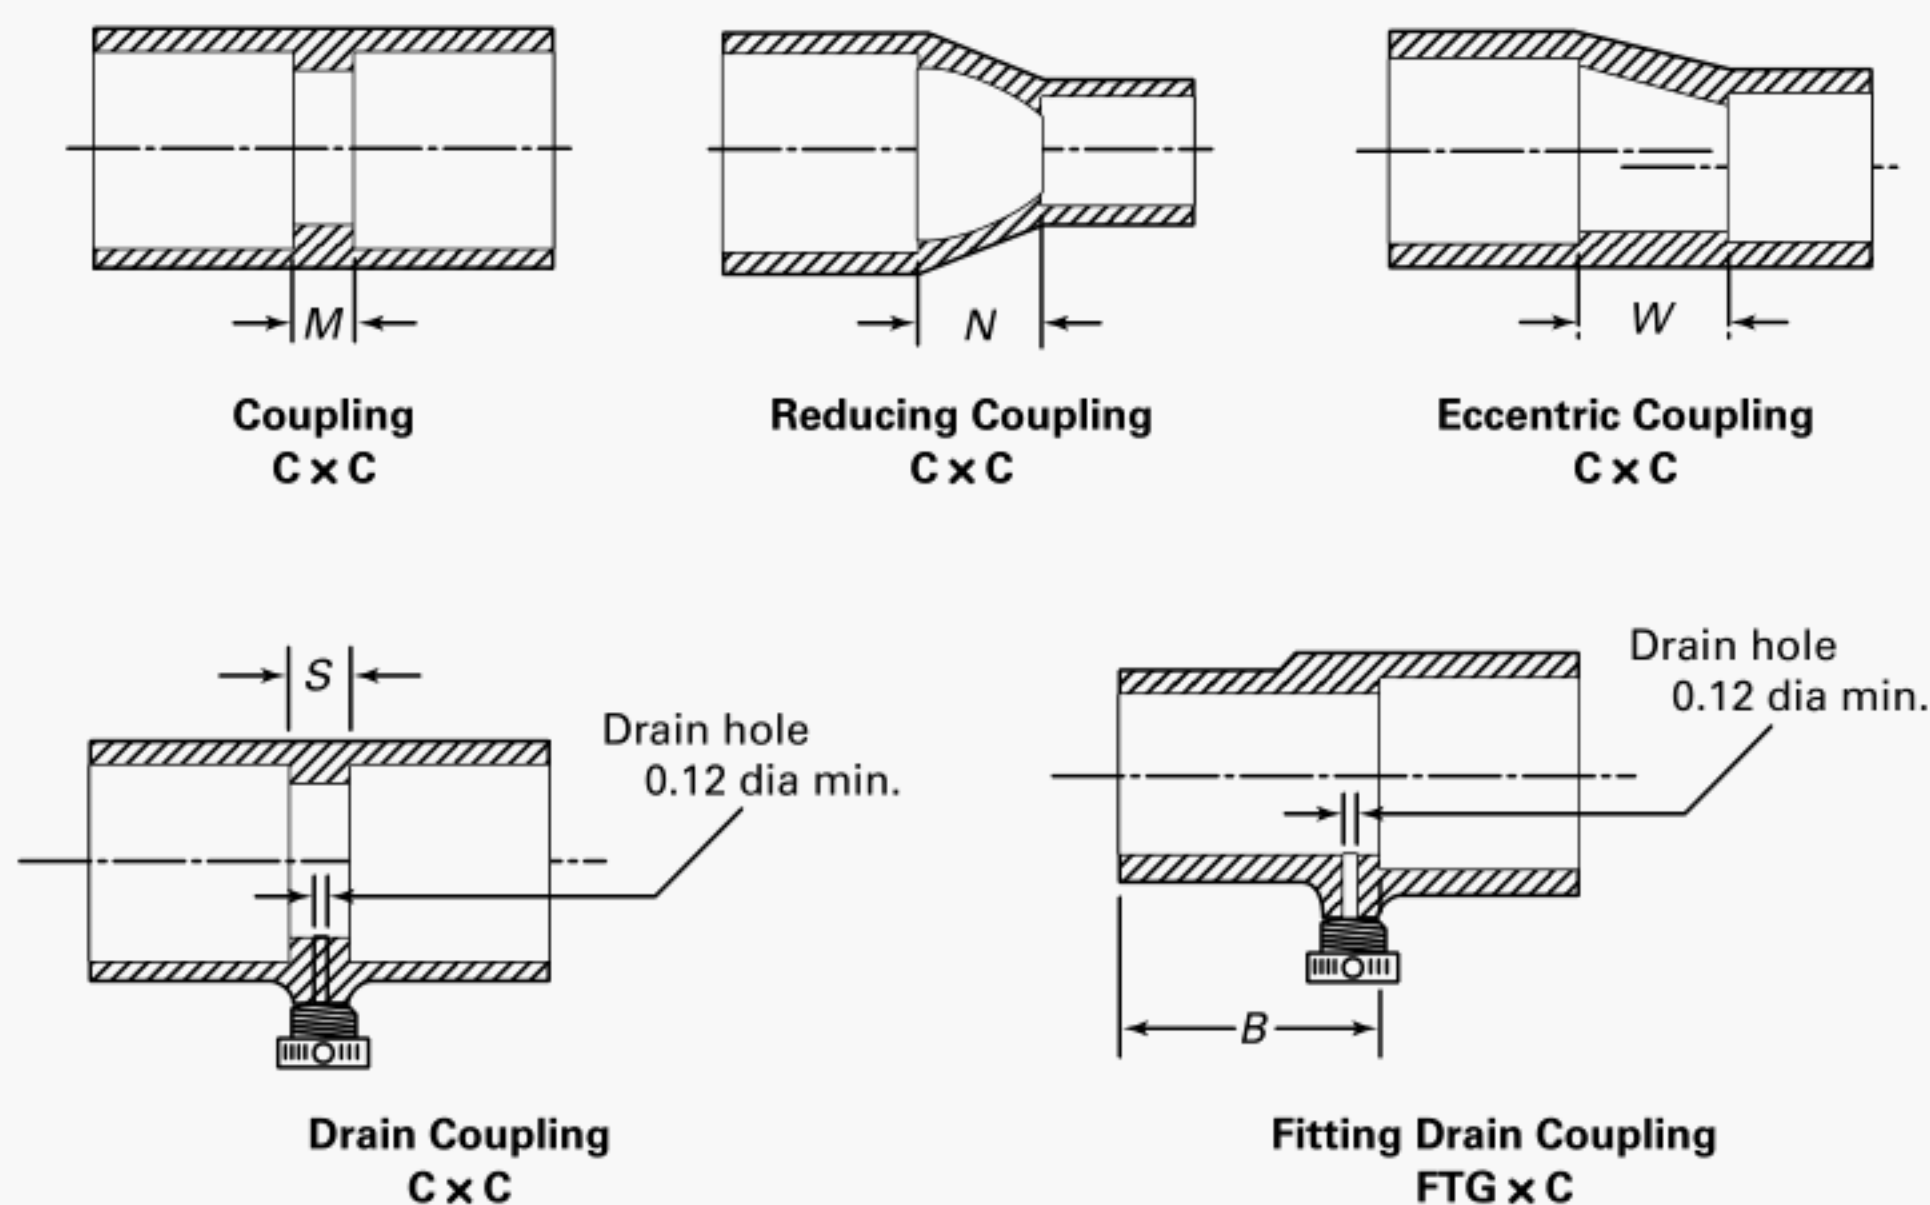**TABLE 7 DIMENSIONS OF COUPLINGS**

Straight		Reducing		Eccentric		Drain	
Standard Water Tube Size [Note (1)]	Laying Length, [Note (2)] <i>M</i>	Standard Water Tube Size [Note (1)]	Laying Length, [Note (2)] <i>N</i>	Standard Water Tube Size [Note (1)]	Laying Length [Note (2)], <i>W</i>	Laying Length [Note(2)], <i>S</i>	Laying Length [Note(2)], <i>B</i>
$\frac{1}{4}$	0.06	$\frac{3}{4} \times \frac{1}{2}$	0.31	$\frac{3}{4} \times \frac{1}{2}$	0.62	0.25	...
$\frac{3}{8}$	0.06	$1 \times \frac{3}{4}$	0.38	$1 \times \frac{3}{4}$	0.69	0.25	...
$\frac{1}{2}$	0.12	$1\frac{1}{4} \times 1$	0.38	$1\frac{1}{4} \times 1$	0.75	0.25	1.00
$\frac{3}{4}$	0.12	$1\frac{1}{4} \times \frac{3}{4}$	0.38	$1\frac{1}{4} \times \frac{3}{4}$	0.75	0.25	1.28
1	0.12	$1\frac{1}{2} \times 1\frac{1}{4}$	0.38	$1\frac{1}{2} \times 1\frac{1}{4}$	0.69	0.25	...
$1\frac{1}{4}$	0.12	$1\frac{1}{2} \times 1$	0.38	$1\frac{1}{2} \times 1$	0.69	0.25	...
$1\frac{1}{2}$	0.12	$1\frac{1}{2} \times \frac{3}{4}$	0.44	$2 \times 1\frac{1}{2}$	1.12	0.25	...
2	0.19	$2 \times 1\frac{1}{2}$	0.50	$2 \times 1\frac{1}{4}$	0.94	0.25	...
$2\frac{1}{2}$	0.19	$2 \times 1\frac{1}{4}$	0.50	$2\frac{1}{2} \times 2$	1.19
3	0.19	2×1	0.50	$3 \times 2\frac{1}{2}$	1.25
$3\frac{1}{2}$	0.25	$2 \times \frac{3}{4}$	0.50	3×2	1.31
4	0.25	$2\frac{1}{2} \times 2$	0.56	4×3	2.00
5	0.25	$2\frac{1}{2} \times 1\frac{1}{2}$	0.56
6	0.25	$2\frac{1}{2} \times 1\frac{1}{4}$	0.62
8	0.62	$2\frac{1}{2} \times 1$	0.62
...	...	$3 \times 2\frac{1}{2}$	0.62
...	...	3×2	0.62
...	...	4×3	0.69
...	...	$4 \times 2\frac{1}{2}$	1.12
...	...	4×2	1.19
...	...	6×4	1.31
...	...	8×6	1.38

continued

TABLE 7 (CONT'D)

GENERAL NOTES:


(a) Dimensions are in inches.

(b) For dimensions not given in this table, see Table 3.

NOTES:

(1) For size designation of fitting, see Section 4.

(2) For inspection tolerances, see Section 8 and Table 2.

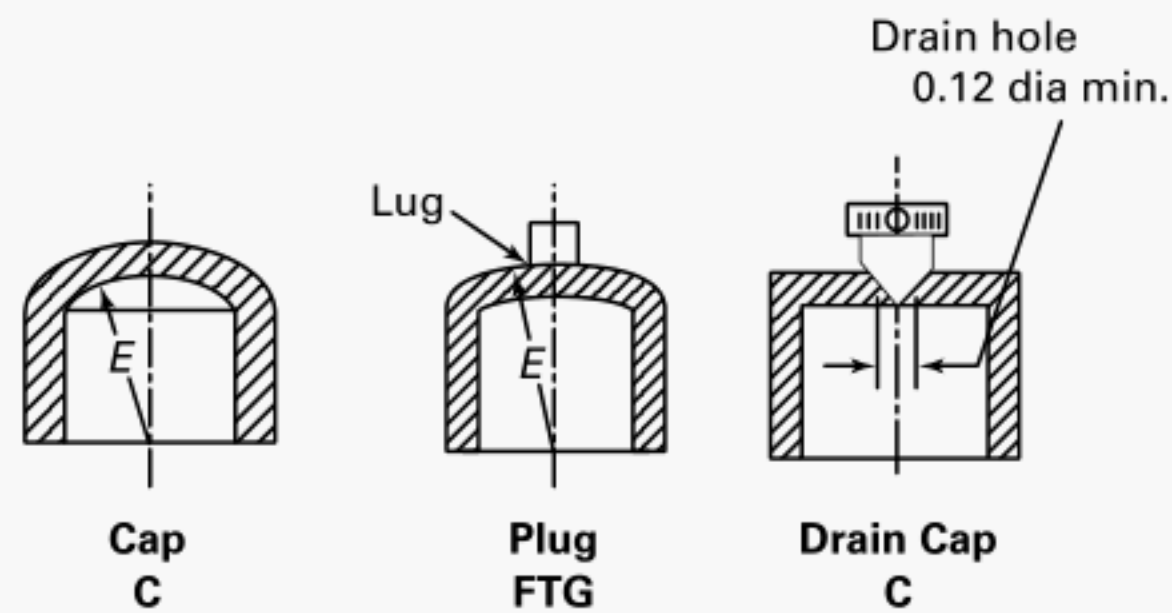**TABLE 8 DIMENSIONS OF CAPS AND PLUGS**


Standard Water Tube Size [Note (1)]	Caps and Plugs Radius [Note (2)], <i>E</i>
$\frac{1}{4}$	0.38
$\frac{3}{8}$	0.50
$\frac{1}{2}$	0.62
$\frac{3}{4}$	0.88
1	1.12
$1\frac{1}{4}$	1.38
$1\frac{1}{2}$	1.62
2	2.12
$2\frac{1}{2}$	2.62
3	3.12
$3\frac{1}{2}$	3.62
4	4.12
5	5.12
6	6.12

GENERAL NOTES:

- (a) Dimensions are in inches.
 (b) For other dimensions not given in this table, see Table 3.
 (c) Casting of lug or square on plugs shall be optional.

NOTES:

- (1) For size designation of fitting, see Section 4.
 (2) Caps shall have either flat or rounded top.

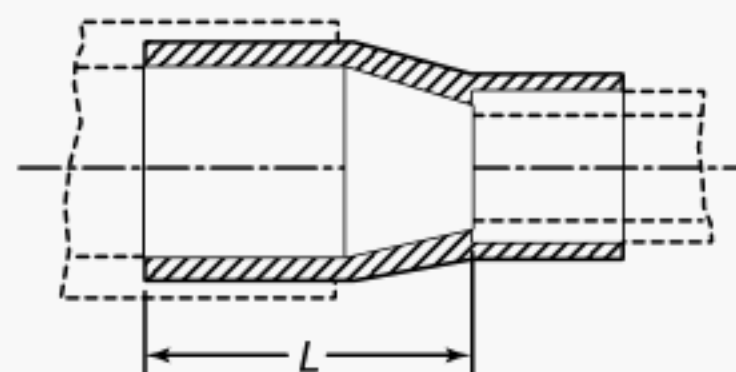

Fitting reducer
(or Bushing)
FTG × C

TABLE 9 DIMENSIONS OF FITTING REDUCERS

Standard Water Tube Size [Note (1)]	Length, <i>L</i>
$\frac{3}{8} \times \frac{1}{4}$	0.69
$\frac{1}{2} \times \frac{3}{8}$	0.94
$\frac{1}{2} \times \frac{1}{4}$	0.94
$\frac{3}{4} \times \frac{1}{2}$	1.19
$\frac{3}{4} \times \frac{3}{8}$	1.25
$1 \times \frac{3}{4}$	1.50
$1 \times \frac{1}{2}$	1.50
$1\frac{1}{4} \times 1$	1.62
$1\frac{1}{4} \times \frac{3}{4}$	1.62
$1\frac{1}{4} \times 1\frac{1}{2}$	1.62
$1\frac{1}{2} \times 1\frac{1}{4}$	1.81
$1\frac{1}{2} \times 1$	1.81
$1\frac{1}{2} \times \frac{3}{4}$	1.81
$2 \times 1\frac{1}{2}$	2.12
$2 \times 1\frac{1}{4}$	2.12
2×1	2.12
$2\frac{1}{2} \times 2$	2.38
$2\frac{1}{2} \times 1\frac{1}{2}$	2.38
$2\frac{1}{2} \times 1\frac{1}{4}$	2.38
$3 \times 2\frac{1}{2}$	2.62
3×2	2.62
$3 \times 1\frac{1}{2}$	2.62
4×3	3.44
$4 \times 2\frac{1}{2}$	3.44
4×2	3.44

GENERAL NOTES:

(a) Dimensions are in inches.

(b) For other dimensions not given in this table, see Table 3.

NOTE:

(1) For size designation of fitting, see Section 4.

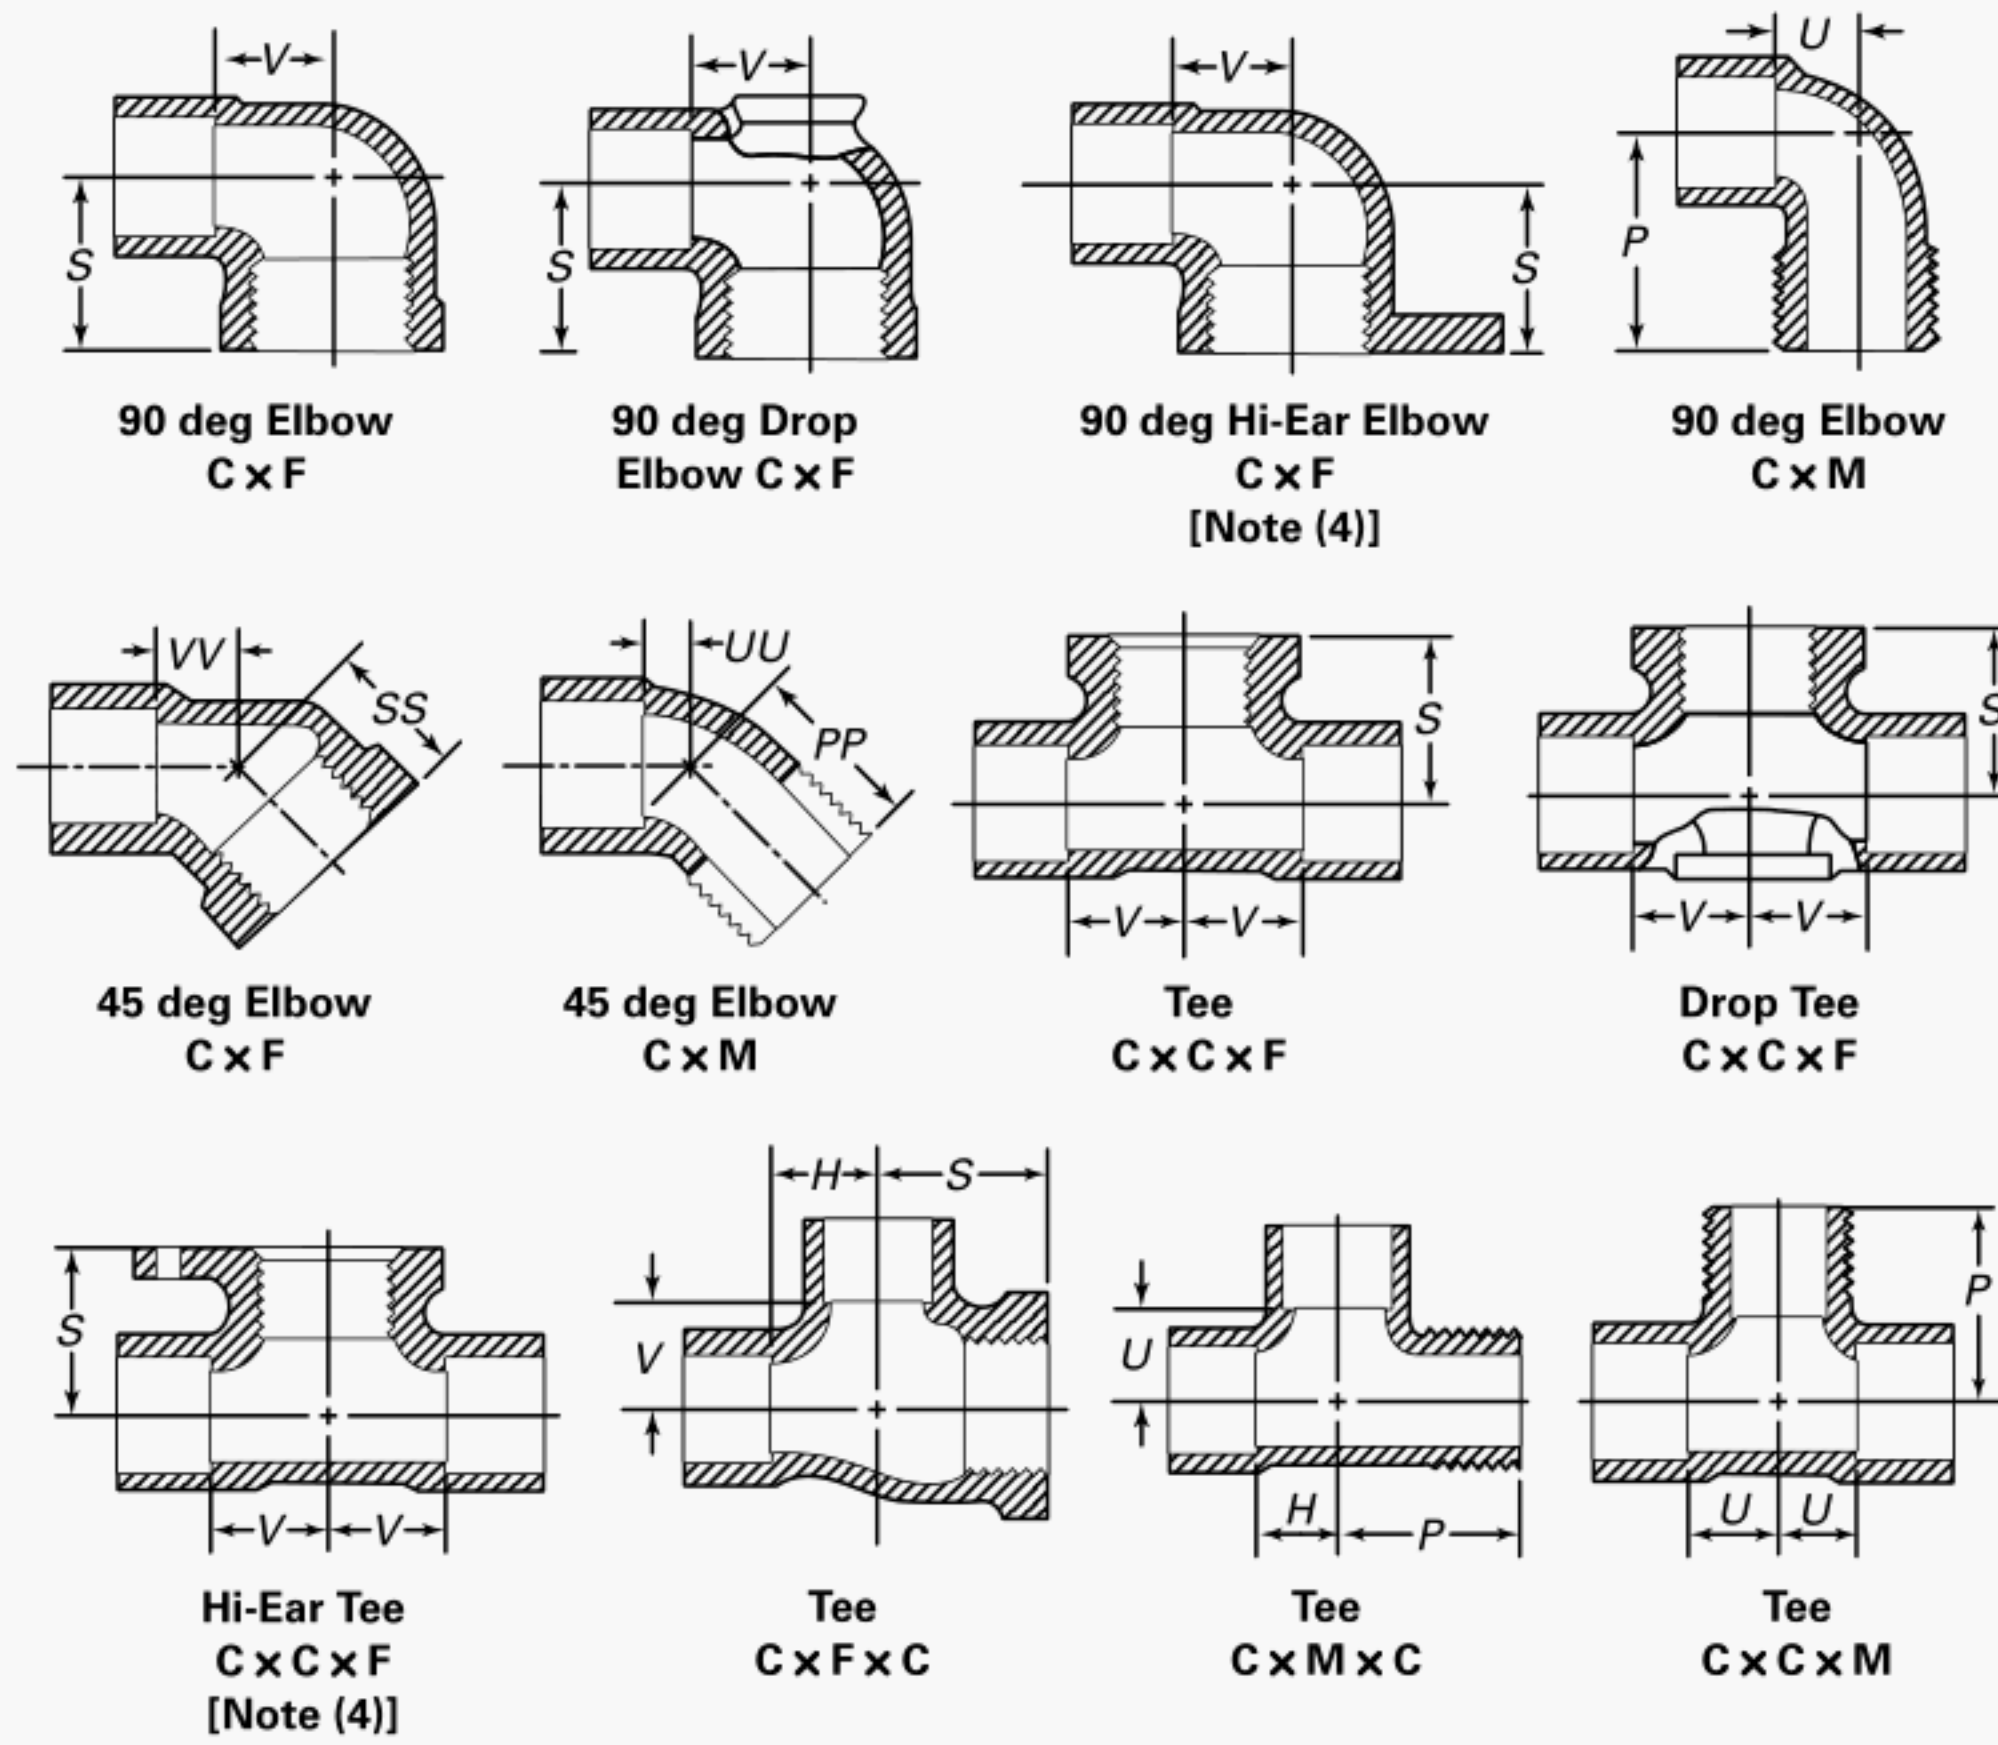


TABLE 10 AND 11 ILLUSTRATION

**TABLE 10 DIMENSIONS OF SOLDER JOINT ELBOWS AND TEES WITH PIPE THREAD ENDS
(STRAIGHT SIZES)**

Standard Water Tube and Pipe Thread Size [Note (1)]	Internal Threads [Note (2)]					External Threads [Note (2)]				
	Center-to-End [Note (3)]		Laying Length [Note (3)]			Center-to-End [Note (3)]		Laying Length [Note (3)]		
	Ell and Tee, <i>S</i>	45 deg Ell, <i>SS</i>	Ell and Tee, <i>V</i>	Tee, <i>H</i>	45 deg Ell, <i>VV</i>	Ell and Tee, <i>P</i>	45 deg Ell, <i>PP</i>	Ell and Tee, <i>U</i>	Tee, <i>H</i>	45 deg Ell, <i>UU</i>
$\frac{1}{4}$	0.56	...	0.38	0.94	...	0.25
$\frac{3}{8}$	0.69	0.69	0.44	0.31	0.19	1.06	0.81	0.31	0.31	0.19
$\frac{1}{2}$	0.88	0.94	0.56	0.44	0.19	1.31	1.00	0.44	0.44	0.19
$\frac{3}{4}$	1.00	1.00	0.69	0.56	0.25	1.50	1.19	0.56	0.56	0.25
1	1.25	1.19	0.88	0.75	0.31	1.64	1.31	0.75	0.75	0.31
$1\frac{1}{4}$	1.50	...	1.00	0.88	...	2.00	...	0.88
$1\frac{1}{2}$	1.62	...	1.12	1.00	...	2.19	...	1.00
2	1.94	...	1.38	1.25	...	2.62	...	1.25
$2\frac{1}{2}$	2.50	...	1.62
3	2.81	...	1.94
4	3.44	...	2.44
6	4.88	...	3.88

GENERAL NOTES:

(a) For reference, see Table 10 Illustration beginning on page 17.

(b) Dimensions are in inches.

(c) For dimensions of threaded ends, see ASME B16.15. For configuration of threaded end, see Section 10. For dimensions of solder joint ends, see Table 3.

(d) For dimensions of reducing tees and ells, see Table 11.

NOTES:

(1) For size designation of fitting, see Section 4.

(2) For threads of threaded ends, see Section 9.

(3) For inspection tolerances, see Section 8 and Table 2.

(4) Hi-ear fittings are designed for use with $\frac{9}{16}$ in. maximum width strap.

**TABLE 11 DIMENSIONS OF SOLDER JOINT ELBOWS AND TEES WITH PIPE THREAD ENDS
(REDUCING SIZES)**

Standard Water Tube and Pipe Thread Size [Note (1)]	Internal Threads [Note (2)]							External Threads [Note (2)]	
	Center-to-End			Laying Length [Note (3)]				Center-to- -End	Laying Length [Note (3)]
	<i>S</i>			<i>V</i>			<i>H</i>	<i>P</i>	<i>U</i>
	90 deg El C-F	Tee C-C-F	Tee C-F-C	90 deg El C-F	Tee C-C-F	Tee C-F-C	Tee C-F-C	90 deg El C-M	90 deg El C-M
$\frac{3}{8} \times \frac{3}{8} \times \frac{1}{2}$...	0.81	0.56
$\frac{3}{8} \times \frac{1}{2}$	0.81	0.56	1.25	0.44
$\frac{1}{2} \times \frac{1}{2} \times \frac{3}{4}$...	0.94	0.69
$\frac{1}{2} \times \frac{3}{4}$	0.94	0.69	1.38	0.56
$\frac{1}{2} \times \frac{1}{2} \times \frac{3}{8}$...	0.81	0.50
$\frac{1}{2} \times \frac{3}{8}$	0.81	0.50	1.12	0.31
$\frac{3}{4} \times \frac{3}{4} \times 1$...	1.12	0.88
$\frac{3}{4} \times 1$	1.12	0.88	1.69	0.75
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$...	0.94	0.94	...	0.56	0.69	0.44
$\frac{3}{4} \times \frac{1}{2}$	0.94	0.56	1.44	0.44
$\frac{3}{4} \times \frac{3}{4} \times \frac{3}{8}$...	0.88	0.50
$\frac{3}{4} \times \frac{3}{8}$	0.88	0.50
$\frac{3}{4} \times \frac{1}{2} \times \frac{3}{4}$	0.94	0.56	0.56
$\frac{3}{4} \times \frac{1}{2} \times \frac{1}{2}$...	0.94	0.88	...	0.56	0.56	0.44
$1 \times 1\frac{1}{4}$	1.38	1.00
$1 \times 1 \times \frac{3}{4}$...	1.19	0.69
$1 \times \frac{3}{4}$	1.19	0.69	1.62	0.56
$1 \times 1 \times \frac{1}{2}$...	1.12	0.56
$1 \times 1 \times \frac{3}{8}$...	1.06	0.50
$1 \times \frac{3}{4} \times 1$...	1.25	1.19	...	0.88	0.75	0.75
$1 \times \frac{3}{4} \times \frac{3}{4}$...	1.19	0.69
$1 \times \frac{3}{4} \times \frac{1}{2}$...	1.12	0.56
$1 \times \frac{1}{2} \times 1$	1.12	0.75	0.75
$1 \times \frac{1}{2}$	1.12	0.56
$1\frac{1}{4} \times 1\frac{1}{4} \times 1$...	1.44	0.88
$1\frac{1}{4} \times 1$	1.44	0.88
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{3}{4}$...	1.31	0.69
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{1}{2}$...	1.25	0.56
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{3}{8}$...	1.19	0.50
$1\frac{1}{4} \times \frac{3}{4} \times 1$	1.19	0.88	0.75
$1\frac{1}{2} \times 1\frac{1}{2} \times 1$...	1.50	1.38	...	0.88	1.12	0.75
$1\frac{1}{2} \times 1\frac{1}{2} \times \frac{3}{4}$...	1.44	0.69
$1\frac{1}{2} \times 1\frac{1}{2} \times \frac{1}{2}$...	1.38	0.56
$1\frac{1}{2} \times \frac{3}{4} \times 1$	1.19	1.00	0.75
$2 \times 2 \times 1\frac{1}{2}$...	1.88	1.12
$2 \times 2 \times 1$...	1.75	0.88
$2 \times 2 \times \frac{3}{4}$...	1.69	0.69
$2 \times 2 \times \frac{1}{2}$...	1.62	0.56
$2\frac{1}{2} \times 2\frac{1}{2} \times \frac{3}{4}$...	2.06	0.69

(continued)

TABLE 11 (CONT'D)

GENERAL NOTES:

- (a) For reference, see Table 11 Illustration beginning on page 17.
- (b) Dimensions are in inches.
- (c) For dimensions of threaded ends, see ASME B16.15. For configuration of threaded ends, see Section 10. For dimensions of solder joint ends, see Table 3.

NOTES:

- (1) For size designation of fitting, see Section 4.
- (2) For threads of threaded ends, see Section 8.
- (3) For inspection tolerance, see Section 8 and Table 2.

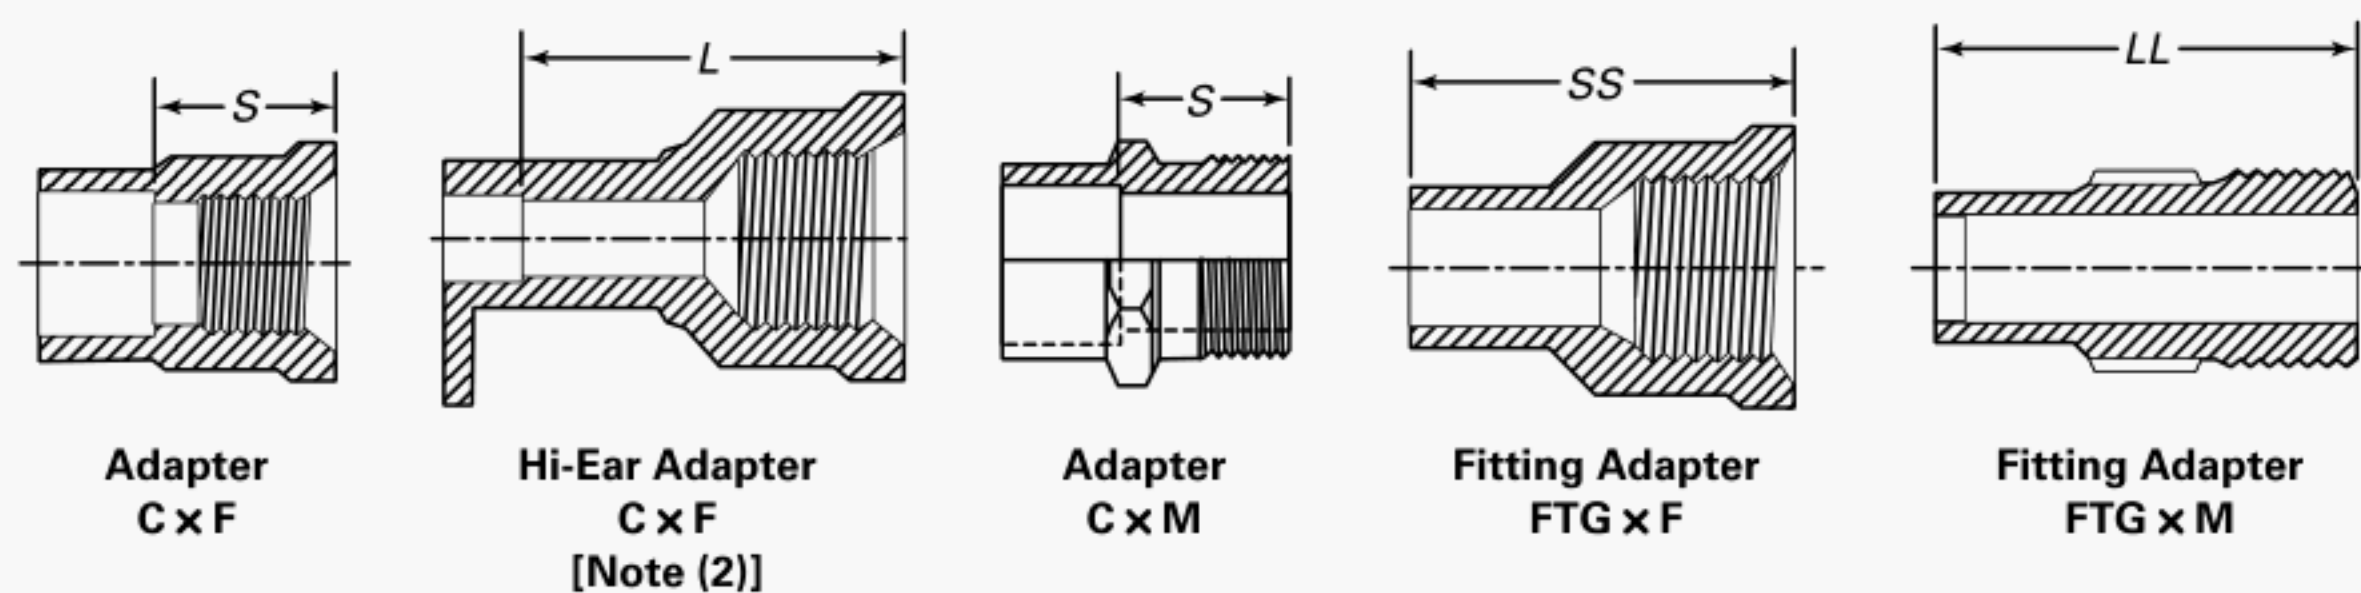


TABLE 12 DIMENSIONS OF SOLDER JOINT ADAPTERS AND FITTING ADAPTERS WITH PIPE THREAD ENDS (STRAIGHT AND REDUCING SIZES)

Standard Water Tube and Pipe Thread Size [Note (1)]		Shoulder- to-End <i>S</i>	End-to-End		End-to-Tube Stop <i>L</i>
Solder Joint	Pipe Thread		<i>SS</i>	<i>LL</i>	
1/4	3/8	0.62
1/4	1/4	0.62	...	1.00	...
3/8	1/2	0.75	...	1.25	...
3/8	3/8	0.62	1.06	1.12	...
1/2	1	1.00
1/2	3/4	0.88	1.44	1.47	...
1/2	1/2	0.75	1.38	1.38	1.25
1/2	3/8	0.62	1.22	1.25	...
3/4	1	1.00	1.81	1.91	...
3/4	3/4	0.88	1.66	1.72	...
3/4	1/2	0.75	1.62	1.62	...
1	1 1/4	1.06	2.09	2.16	...
1	1	1.00	1.97	2.09	...
1	3/4	0.88	1.81	1.91	...
1 1/4	2	1.12	...	2.38	...
1 1/4	1 1/2	1.06	2.22	2.28	...
1 1/4	1 1/4	1.06	2.03	2.22	...
1 1/4	1	1.06	2.03	2.12	...
1 1/2	2	1.12	...	2.50	...
1 1/2	1 1/2	1.06	2.22	2.41	...
1 1/2	1 1/4	1.06	2.22	2.34	...
1 1/2	1	1.00	...	2.25	...
2	2	1.12	2.53	2.75	...
2	1 1/2	1.12	...	2.66	...
2 1/2	2 1/2	1.38	3.09	3.12	...
3	3	1.50	3.22	3.41	...
4	4	1.69	3.81	4.12	...
6	6	2.00	5.34	5.75	...
8	8	2.25

(continued)


TABLE 12 (CONT'D)

GENERAL NOTES:

- (a) Dimensions are in inches.
- (b) For threaded ends, see Section 9.
- (c) For dimensions of threaded ends, see ASME B16.15, Class 125. For sizes not listed in ASME B16.15, Class 125, refer to ASME B16.3, Class 150. For configuration of threaded ends, see Section 10. For dimensions of solder joint ends, see Table 3.

NOTES:

- (1) For size designation of fitting, see Section 4.
- (2) Hi-ear fittings are designed for use with $\frac{9}{16}$ in. maximum width strap.

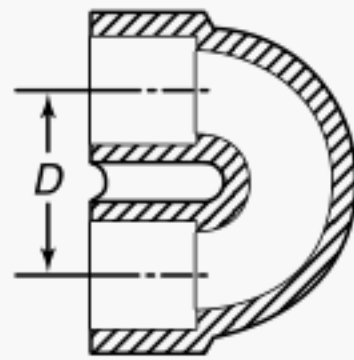

Return Bend
C x C

**TABLE 13 DIMENSIONS OF RETURN BENDS
(STRAIGHT SIZES)**


Standard Water Tube Size [Note (1)]	Center-to-Center, <i>D</i>
$\frac{1}{2}$	1.00
$\frac{3}{4}$	1.31
1	1.88
$1\frac{1}{4}$	2.00
$1\frac{1}{2}$	2.50
2	3.00
3	4.00
4	5.00

GENERAL NOTES:

- (a) Dimensions are in inches.
(b) For dimensions not given in this table, see Table 3.

NOTE:

- (1) For size designation of fitting, see Section 4.

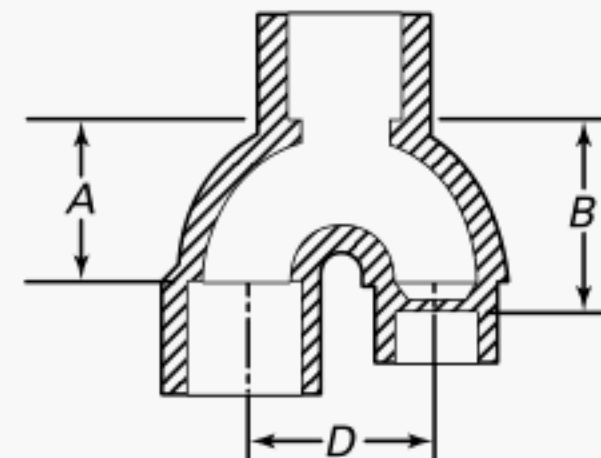

Supply & Return Tee
C x C x C

**TABLE 14 DIMENSIONS OF SUPPLY AND
RETURN TEES**


Standard Water Tube Size [Note 1]	Laying Lengths		Center-to- Center, <i>D</i>
	<i>A</i>	<i>B</i>	
$\frac{1}{2}$	0.81	0.81	1.00
$\frac{3}{4}$	1.09	1.09	1.31
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$	1.09	1.09	1.31
$\frac{3}{4} \times \frac{1}{2} \times \frac{1}{2}$	1.09	1.28	1.31

GENERAL NOTES:

- (a) Dimensions are in inches.
(b) For dimensions not given in this table, see Table 3.
(c) For inspection tolerances, see Section 8 and Table 2.

NOTE:

- (1) For size designation of fittings, see Section 4.

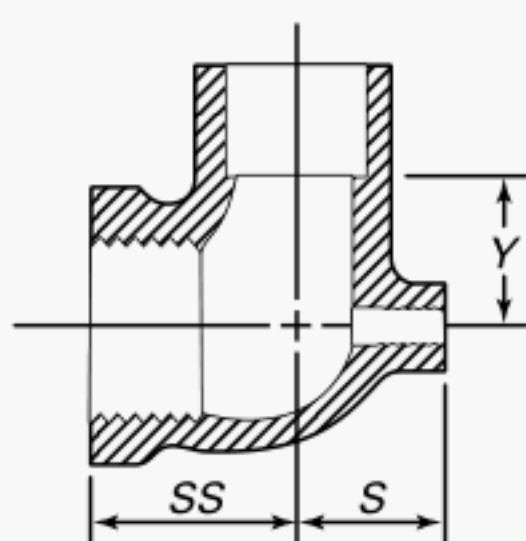

Baseboard Tee
F × F × C

TABLE 15 DIMENSIONS OF BASEBOARD TEES


Standard Water Tube Size [Note (1)]	Laying Lengths		
	SS	S	Y
$\frac{1}{2} \times \frac{1}{8} \times 1$	1.12	0.81	0.56
$\frac{1}{2} \times \frac{1}{8} \times \frac{3}{4}$	0.94	0.69	0.56
$\frac{3}{4} \times \frac{1}{8} \times 1$	1.19	0.81	0.69
$\frac{3}{4} \times \frac{1}{8} \times \frac{3}{4}$	1.00	0.69	0.69
$1\frac{1}{4} \times \frac{1}{8} \times 1\frac{1}{4}$	1.84	0.94	0.88

GENERAL NOTES:

- (a) Dimensions are inches.
 (b) For dimensions not given in this table, see Table 3.
 (c) For inspection tolerances, see Sections 8, 9 and Table 3.

NOTE:

- (1) For size designation of fittings, see Section 4.

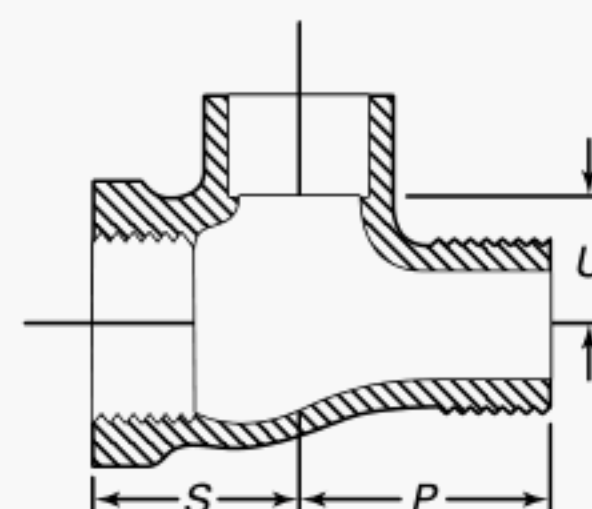

Tee
F × M × C

TABLE 16 DIMENSIONS OF TEES


Standard Water Tube Size [Note (1)]	Laying Lengths		
	U	P	S
$\frac{1}{2} \times \frac{3}{4} \times \frac{1}{2}$	0.69	1.22	0.97
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$	0.69	1.34	1.00
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$	0.69	1.22	0.97

GENERAL NOTE:

- (a) Dimensions are inches.
 (b) For dimensions not given in this table, see Table 3.
 (c) For inspection tolerances, see Sections 8, 9 and Table 3.

NOTE:

- (1) For size designation of fittings, see Section 4.

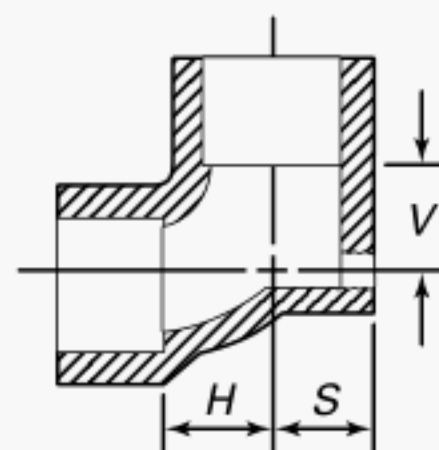

Baseboard Tee
C × F × C

TABLE 17 DIMENSIONS OF BASEBOARD TEES


Standard Water Tube Size [Note (1)]	Laying Lengths		
	<i>H</i>	<i>S</i>	<i>V</i>
$\frac{3}{8} \times \frac{1}{8} \times \frac{3}{8}$	0.59	0.97	0.59
$\frac{1}{2} \times \frac{1}{8} \times 1$	0.75	0.81	0.44
$\frac{1}{2} \times \frac{1}{8} \times \frac{3}{4}$	0.56	0.69	0.44
$\frac{1}{2} \times \frac{1}{8} \times \frac{1}{2}$	0.44	0.56	0.44
$\frac{3}{4} \times \frac{1}{8} \times 1\frac{1}{4}$	0.81	0.94	0.56
$\frac{3}{4} \times \frac{1}{8} \times 1$	0.75	0.81	0.62
$\frac{3}{4} \times \frac{1}{8} \times \frac{3}{4}$	0.56	0.69	0.56
$1 \times \frac{1}{8} \times 1$	0.72	0.75	0.72
$1\frac{1}{4} \times \frac{1}{8} \times 1\frac{1}{4}$	0.88	0.94	0.88

GENERAL NOTES:

- (a) Dimensions are in inches.
- (b) For dimensions not given in this table, see Table 3.
- (c) For inspection tolerances, see Sections 8, 9 and Table 3.

NOTE:

- (1) For size designations of fittings, see Section 4.

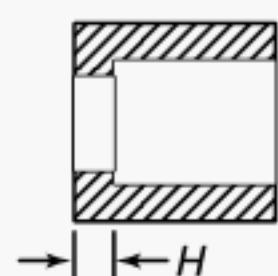

Flush Bushing
FTG x C

TABLE 18 DIMENSIONS OF FLUSH BUSHINGS


Standard Water Tube Size [Note (1)]	Laying Length, <i>H</i>
$\frac{1}{4} \times \frac{1}{8}$	0.06
$\frac{3}{8} \times \frac{1}{4}$	0.06
$\frac{1}{2} \times \frac{3}{8}$	0.09
$\frac{1}{2} \times \frac{1}{4}$	0.25
$\frac{5}{8} \times \frac{1}{2}$	0.06
$\frac{3}{4} \times \frac{5}{8}$	0.19
$\frac{3}{4} \times \frac{1}{2}$	0.09
$\frac{3}{4} \times \frac{3}{8}$	0.44
$1 \times \frac{3}{4}$	0.12
$1 \times \frac{1}{2}$	0.47
$1\frac{1}{4} \times 1$	0.09
$1\frac{1}{2} \times 1\frac{1}{4}$	0.16
$2 \times 1\frac{1}{2}$	0.12

GENERAL NOTES:

- (a) Dimensions are in inches.
 (b) For dimensions not given in this table, see Table 3.
 (c) For inspection tolerances, see Section 8 and Table 3.

NOTE:

- (1) For size designation of fittings, see Section 4.

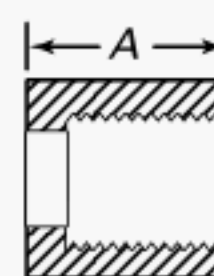

Flush Bushing
FTG x F

TABLE 19 DIMENSIONS OF FLUSH BUSHINGS

Standard Water Tube Size [Note (1)]	Laying Length, <i>A</i>
$\frac{1}{2} \times \frac{1}{8}$	0.56
$\frac{3}{4} \times \frac{3}{8}$	0.81
$1 \times \frac{1}{2}$	0.97
$1\frac{1}{4} \times \frac{3}{4}$	1.03
$1\frac{1}{2} \times 1$	1.16
$2 \times 1\frac{1}{2}$	1.41

GENERAL NOTES:

- (a) Dimensions are in inches.
 (b) For dimensions not given in this table, see Table 3.
 (c) For inspection tolerances, see Sections 8, 9 and Table 3.

NOTE:

- (1) For size designation of fittings, see Section 4.

NONMANDATORY ANNEX A STRENGTH OF SOLDER JOINTS

The maximum recommended pressure–temperature ratings for solder joints made with copper tube and cast copper alloy pressure fittings, using representative

commercial solders, are listed in Table A1. These pressure/temperature ratings are based on solder joints made in accordance with the requirements of ASTM B 828.

TABLE A1 PRESSURE-TEMPERATURE RATINGS

Maximum Working Gage Pressure, for Standard Water Tube Sizes (1)												
Joining Material	Working Temperature		1/8 Through 1		1 1/4 Through 2		2 1/2 Through 4		5 Through 8		10 Through 12	
	°F	°C	psi	kPa	psi	kPa	psi	kPa	psi	kPa	psi	kPa
Alloy Sn50 50-50 tin-lead solder (2, 3)	100	38	200	1375	175	1205	150	1030	135	930	100	685
	150	66	150	1030	125	860	100	685	90	620	70	480
	200	93	100	685	90	620	75	515	70	480	50	340
	250	120	85	585	75	515	50	340	45	310	40	275
Alloy Sb5 95-5 tin-antimony solder (4)	100	38	1090 (9)	7540 (9)	850 (8)	5880 (8)	705 (8)	4880 (8)	660 (8)	4555 (8)	500 (9)	3460 (9)
	150	66	625 (10)	4315 (10)	485 (10)	3365 (10)	405 (10)	2790 (10)	375 (10)	2605 (10)	285 (12)	1975 (11)
	200	93	505 (11)	3500 (11)	395 (10)	2730 (10)	325 (10)	2265 (10)	305 (10)	2115 (10)	230 (11)	1605 (11)
	250	120	270	1885	210	1475	175	1220	165	1135	125	865
Alloy E (5)	100	38	710 (10)	4905 (10)	555 (10)	3825 (10)	460 (10)	3175 (10)	430 (10)	2965 (10)	325 (11)	2255 (11)
	150	66	475 (11)	3275 (11)	370 (10)	2550 (10)	305 (10)	2115 (10)	285 (11)	1975 (11)	215 (11)	1500 (11)
	200	93	375	2595	290	2025	240 (11)	1680 (11)	225 (11)	1570 (11)	170	1190
	250	120	320	2230	250	1735	205	1440	195	1340	145	1020
Alloy HB (6)	100	38	1035 (9)	7135 (9)	805 (8)	5560 (8)	670 (8)	4615 (8)	625 (9)	4305 (9)	475 (9)	3275 (9)
	150	66	710 (10)	4905 (10)	555 (10)	3825 (10)	460 (10)	3175 (10)	430 (10)	2965 (10)	325 (10)	2255 (10)
	200	93	440 (11)	3045 (11)	345 (11)	2375 (11)	285 (11)	1970 (11)	265 (11)	1840 (11)	200	1400
	250	120	430 (11)	2970 (11)	335 (11)	2315 (11)	275 (11)	1920 (11)	260 (11)	1800 (11)	195	1365

Pressure-temperature ratings consistent with the materials and procedures employed.

Joining materials melting at or above 1100°F (593°C) (7)

GENERAL NOTE: For extremely low working temperatures in the 0°F to minus 200°F (minus 18°C to minus 93°C) range, it is recommended that a joint material melting at or above 1100°F (593°C) be employed [see Note (7)].

NOTES:

- (1) Standard water tube sizes per ASTM B 88.
- (2) ASTM B 32 Alloy Grade Sn50.
- (3) The Safe Drinking Water Act Amendment of 1986 prohibits the use in potable water systems of any solder having a lead content in excess of 0.2%.
- (4) ASTM B 32 Alloy Grade Sb5.
- (5) ASTM B 32 Alloy Grade E.
- (6) ASTM B 32 Alloy Grade HB.
- (7) These joining materials are defined as *brazing alloys* by the American Welding Society.
- (8) The solder joint exceeds the strength of Types K, L, and M tube in drawn and annealed tempers.
- (9) The solder joint exceeds the strength of Types L and M tube in drawn temper and Type K tube in annealed temper.
- (10) The solder joint exceeds the strength of Type M tube in drawn temper and Types K and L tube in annealed temper.
- (11) The solder joint exceeds the strength of Type L tube in annealed temper.

NONMANDATORY ANNEX B METRIC (SI) TABLES

(Table designators with the prefix "B" correspond to the table numbers in the body of the standard.)

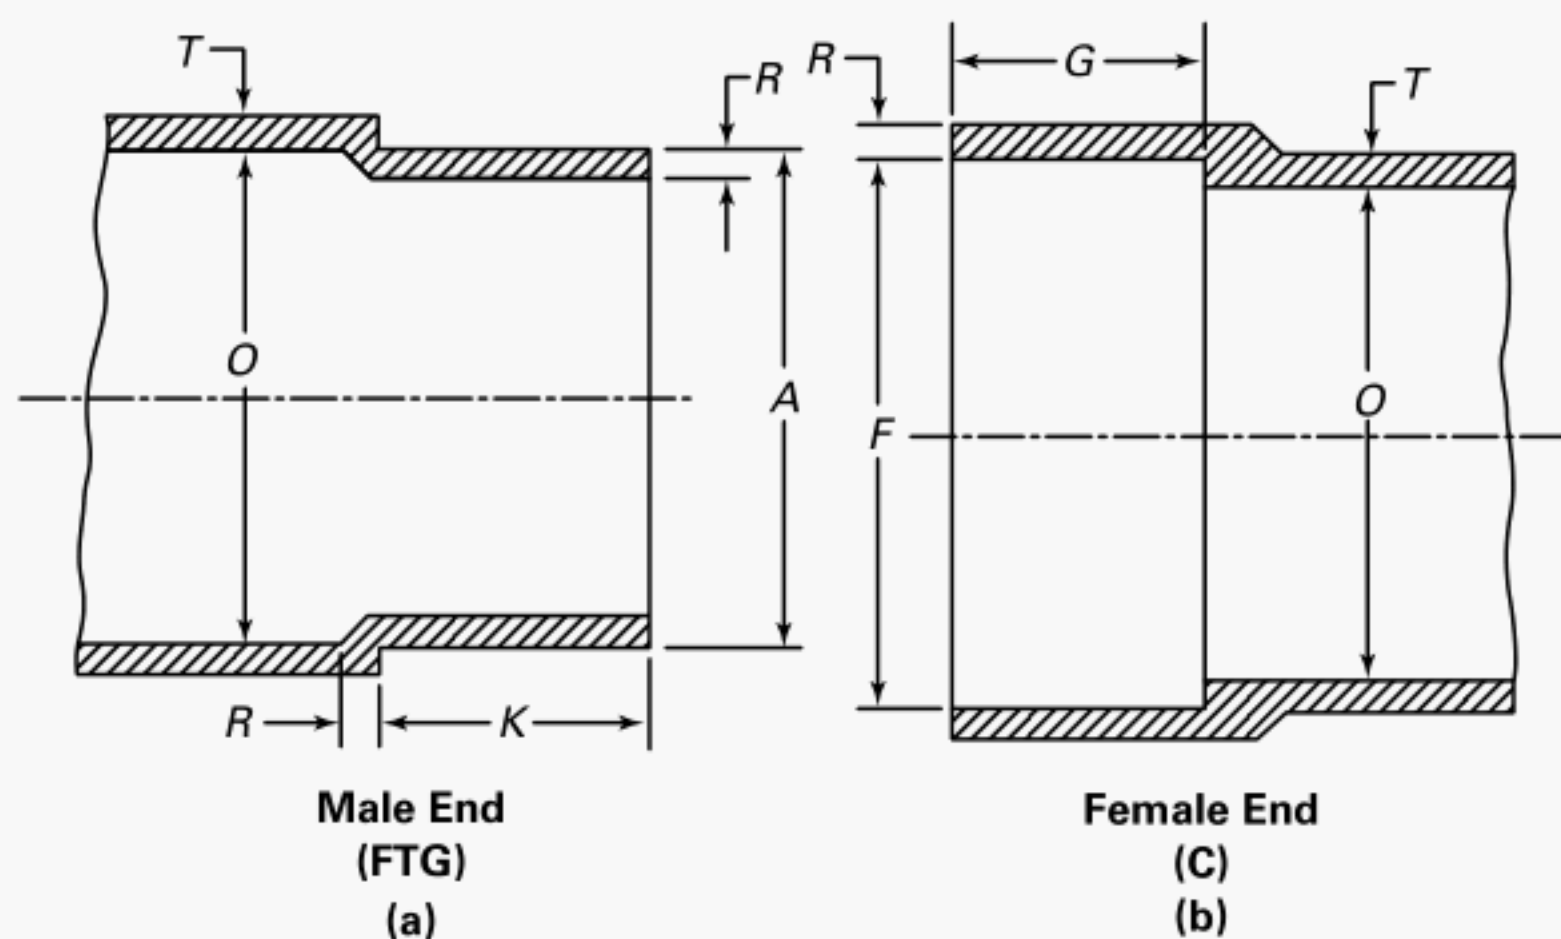


TABLE B3 DIMENSIONS OF SOLDER JOINT ENDS

Standard Water Tube Size [Note (1)]	Male End			Female End			Metal Thickness [Note (3)]		Inside Diameter of Fitting <i>O</i> Min.
	Outside Diameter [Note (2)], <i>A</i>		Length, <i>K</i>	Inside Diameter, <i>F</i>		Depth, <i>G</i>			
	Min.	Max.		Min.	Max.		Body, <i>T</i>	Joint, <i>R</i>	
$\frac{1}{4}$	9.47	9.55	9.5	9.58	9.68	8.0	2.0	1.3	7.9
$\frac{3}{8}$	12.62	12.73	11.0	12.75	12.85	9.5	2.3	1.3	10.9
$\frac{1}{2}$	15.80	15.90	14.5	15.93	16.03	12.5	2.3	1.3	13.7
$\frac{3}{4}$	22.15	22.25	20.5	22.28	22.38	19.0	2.5	1.5	19.8
1	28.50	28.63	24.5	28.65	28.75	23.0	2.8	1.8	25.9
$1\frac{1}{4}$	34.85	34.98	26.0	35.00	35.10	24.5	3.0	1.8	32.0
$1\frac{1}{2}$	41.17	41.33	29.5	41.35	41.48	28.0	3.3	2.0	38.1
2	53.87	54.03	35.5	54.05	54.18	34.0	3.8	2.3	50.3
$2\frac{1}{2}$	66.57	66.73	39.0	66.75	66.88	37.5	4.3	2.5	62.5
3	79.27	79.43	43.5	79.45	79.58	42.0	4.8	2.8	74.7
$3\frac{1}{2}$	91.97	92.13	50.0	92.15	92.28	48.5	5.1	3.0	86.9
4	104.67	104.83	56.5	104.85	104.98	55.0	5.6	3.3	99.1
5	130.07	130.23	69.0	130.25	130.38	67.5	7.1	4.3	123.7
6	155.47	155.63	82.0	155.65	155.78	78.5	8.6	5.1	148.3
8	206.22	206.43	104.0	206.45	206.58	101.0	9.5	7.9	196.1
10	257.02	257.23	104.6	257.25	257.38	101.6	12.2	12.2	244.3
12	307.82	308.03	117.3	308.05	308.18	114.3	14.2	14.2	293.6

(continued)


TABLE B3 (CONT'D)

GENERAL NOTES:

- (a) Dimensions are in millimeters.
- (b) The sketches and designs of fittings are illustrative only. Dimensions herein shall govern in all cases.

NOTES:

- (1) For size designation of fitting, see Section 4.
- (2) For ovality and gaging tolerances, see Section 8.
- (3) For metal thickness, see Section 7.

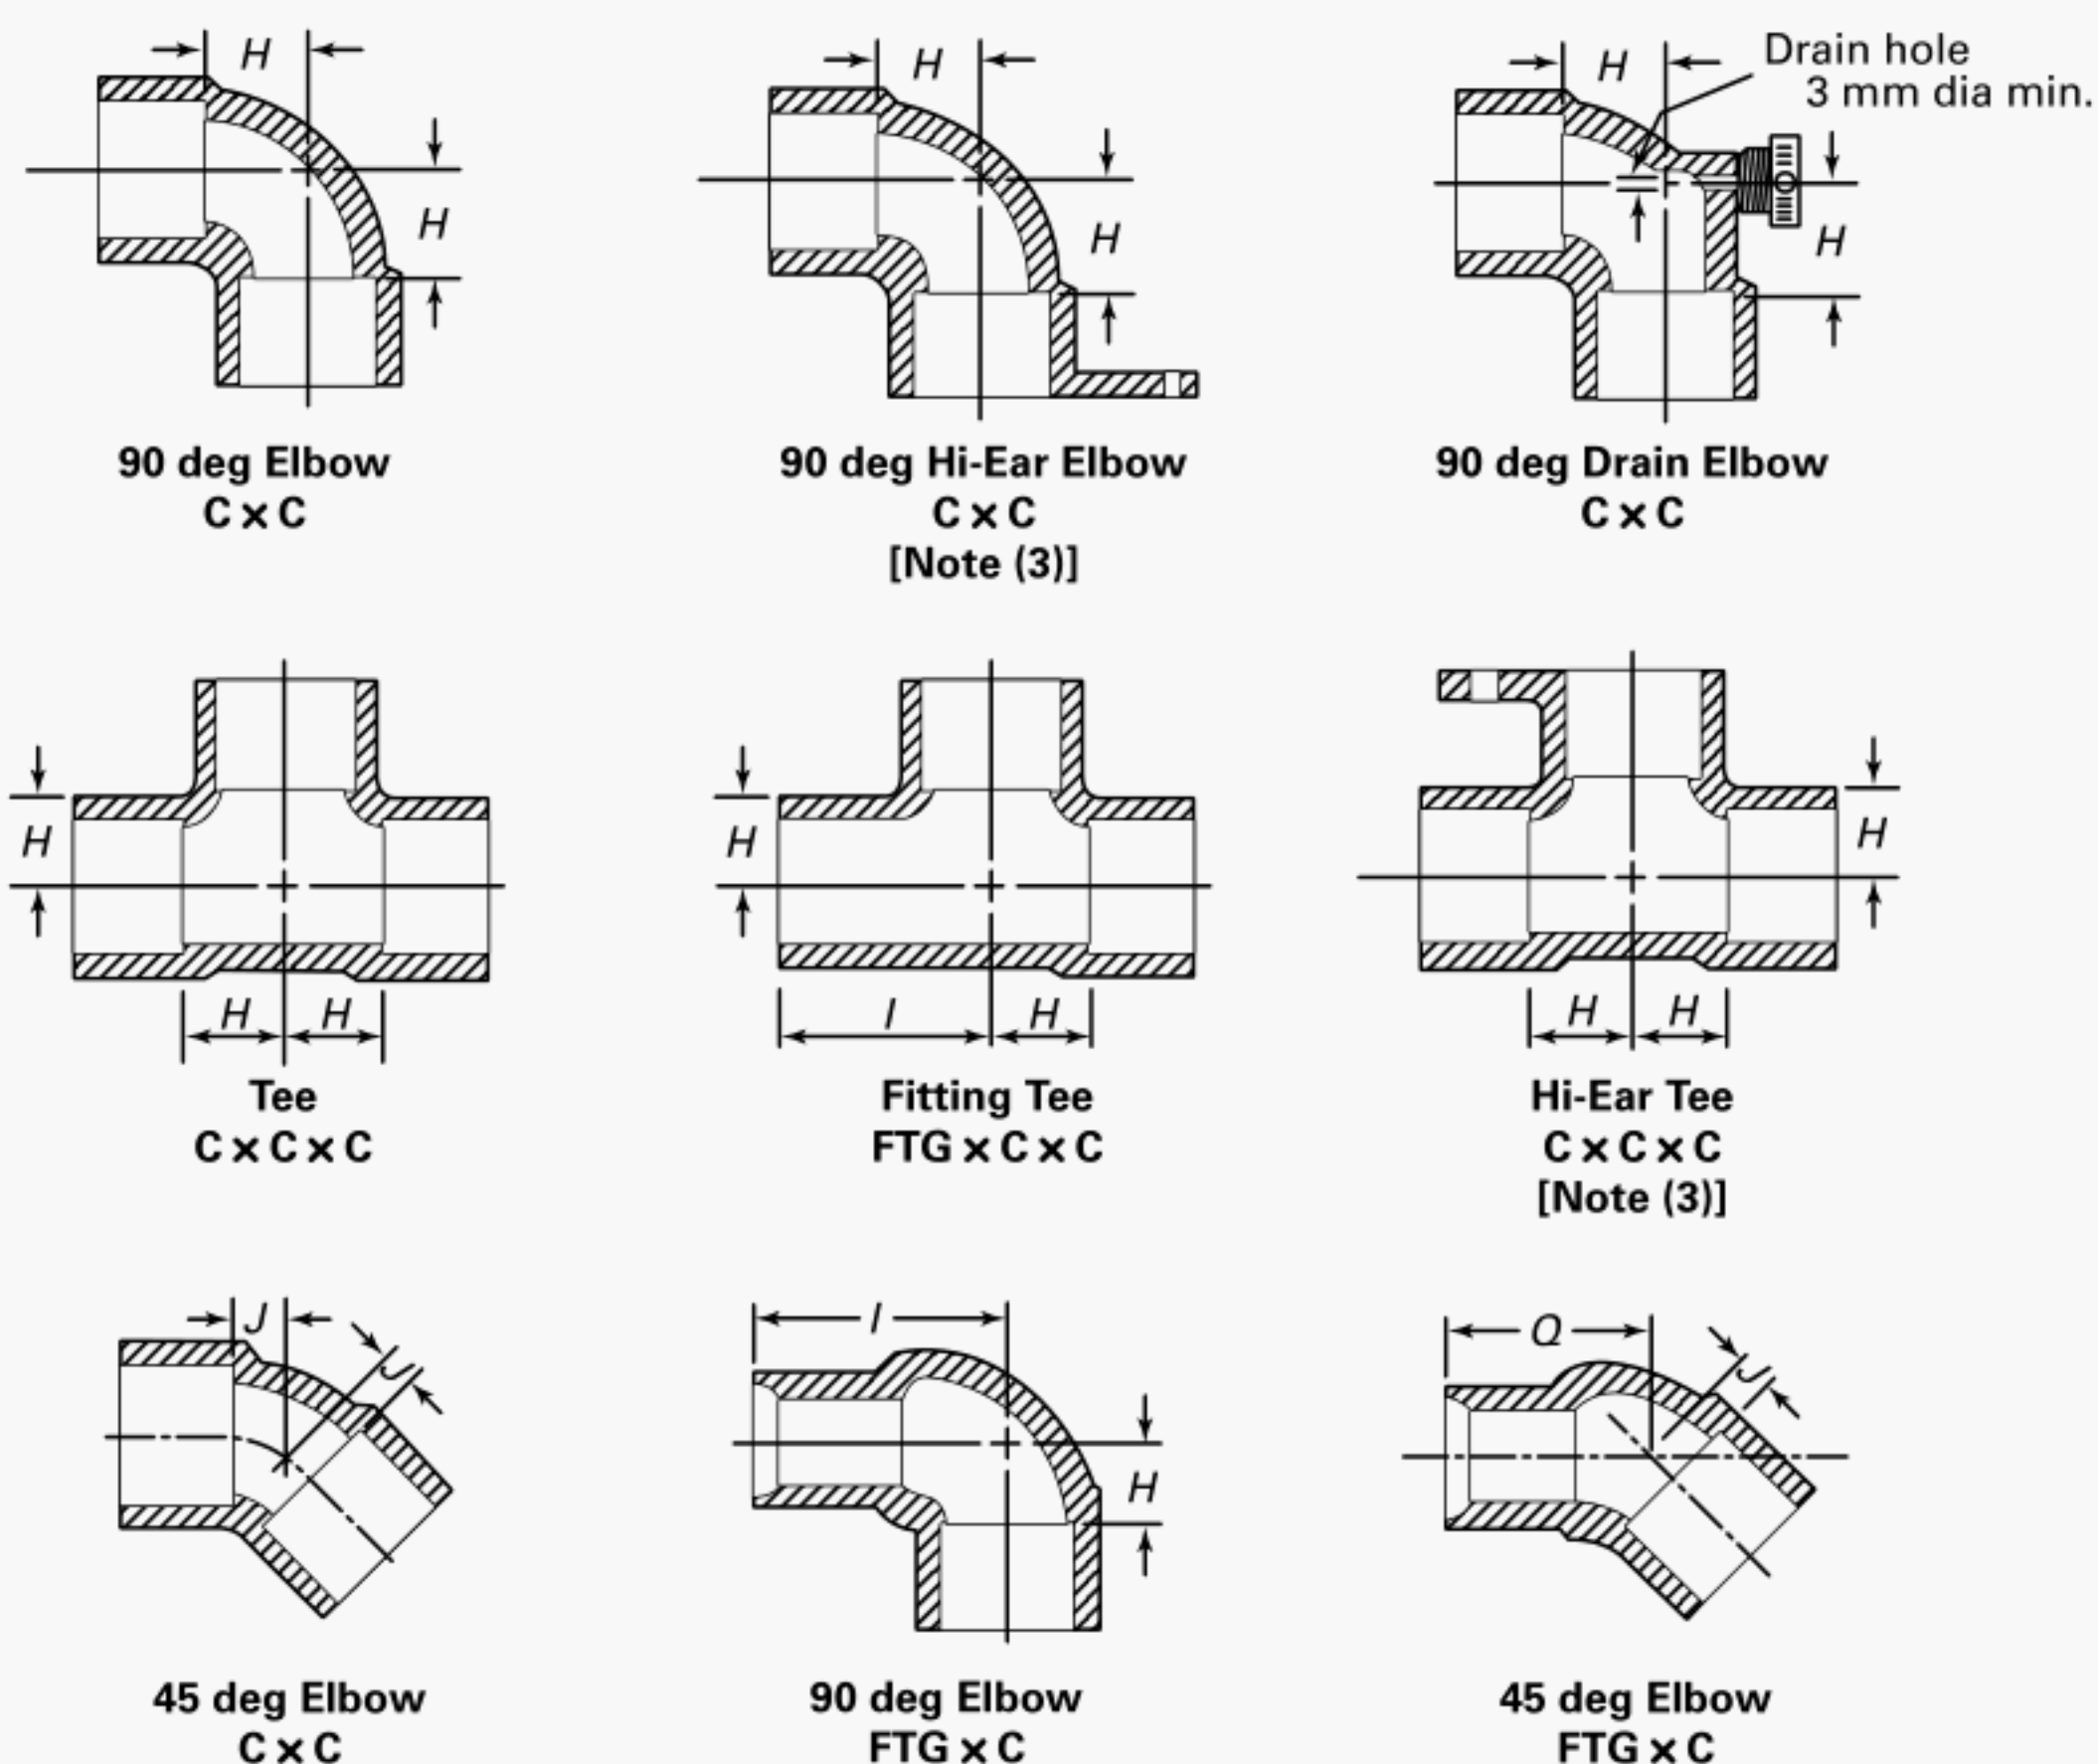**TABLE B4 DIMENSIONS OF ELBOWS, TEES, AND 45 deg ELBOWS**

Standard Water Tube Size [Note (1)]	Laying Length Tee and 90 deg Elbow [Note (2)], <i>H</i>	Center-to-End 90 deg Elbow and Tee, [Note (2)], <i>I</i>	Laying Length 45 deg Elbow [Note (2)], <i>J</i>	Center-to-End 45 deg Elbow [Note (2)], <i>Q</i>
$\frac{1}{4}$	6.5	19.0
$\frac{3}{8}$	8.0	22.0	5.0	19.0
$\frac{1}{2}$	11.0	28.5	5.0	22.0
$\frac{3}{4}$	14.5	38.0	6.5	30.0
1	19.0	47.0	8.0	33.5
$1\frac{1}{4}$	22.0	51.5	11.0	39.5
$1\frac{1}{2}$	25.5	58.0	12.5	44.5
2	32.0	70.5	14.5	54.0
$2\frac{1}{2}$	38.0	80.0	16.0	...
3	44.5	91.5	19.0	...
$3\frac{1}{2}$	51.0	...	22.0	...
4	57.0	116.5	24.0	...
5	79.5	...	36.5	...
6	92.0	...	41.5	...
8	124.0	...	54.0	...

(continued)


TABLE B4 (CONT'D)

GENERAL NOTES:

- (a) Dimensions are in millimeters.
- (b) For dimensions not given in this table, see Table B3.

NOTES:

- (1) For size designation of fitting, see Section 4.
- (2) For inspection tolerances, see Section 8 and Table 2.
- (3) Hi-ear fittings are designed for use with 14mm maximum width strap.

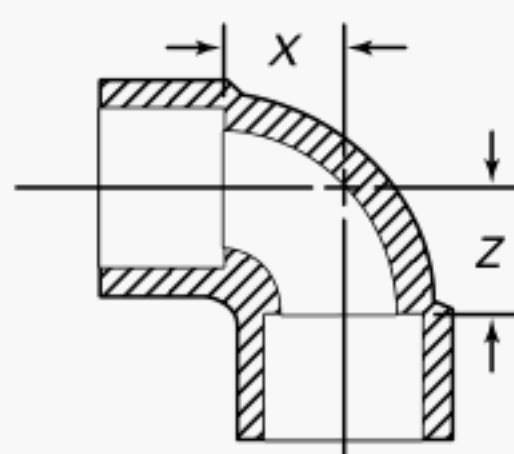

90 deg Elbow
C x C

**TABLE B5 DIMENSIONS OF REDUCING
90 deg ELBOWS**


Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]	
	X	Z
$\frac{3}{8} \times \frac{1}{4}$	6.5	8.0
$\frac{1}{2} \times \frac{3}{8}$	9.5	11.0
$\frac{3}{4} \times \frac{1}{2}$	11.0	14.5
$1 \times \frac{3}{4}$	16.0	19.0
$1 \times \frac{1}{2}$	12.5	19.0
$1\frac{1}{4} \times 1$	19.0	22.0
$1\frac{1}{4} \times \frac{3}{4}$	16.0	22.0
$1\frac{1}{4} \times \frac{1}{2}$	12.5	22.0
$1\frac{1}{2} \times 1\frac{1}{4}$	22.0	25.5
$1\frac{1}{2} \times 1$	19.0	25.5
$1\frac{1}{2} \times \frac{3}{4}$	16.0	25.5
$2 \times 1\frac{1}{2}$	25.5	31.5
$2 \times 1\frac{1}{4}$	22.0	31.5
2×1	19.0	31.5
$2 \times \frac{3}{4}$	16.0	31.5
$2\frac{1}{2} \times 2$	31.5	38.0
$2\frac{1}{2} \times 1\frac{1}{2}$	25.5	38.0
$2\frac{1}{2} \times 1\frac{1}{4}$	22.0	38.0
$2\frac{1}{2} \times 1$	19.0	38.0
$3 \times 2\frac{1}{2}$	38.0	44.5
3×2	31.5	44.5
$3 \times 1\frac{1}{2}$	25.5	44.5
$3 \times 1\frac{1}{4}$	22.0	44.5
4×3	44.5	57.0
$4 \times 2\frac{1}{2}$	38.0	57.0
4×2	31.5	57.0
6×4	66.5	92.0
6×3	51.0	92.0
8×6	98.5	124.0

GENERAL NOTES:

- (a) Dimensions are in millimeters.
(b) For dimensions not given in this table, see Table B3.

NOTES:

- (1) For size designation of fitting, see Section 4.
(2) For inspection tolerances, see Section 8 and Table 2.

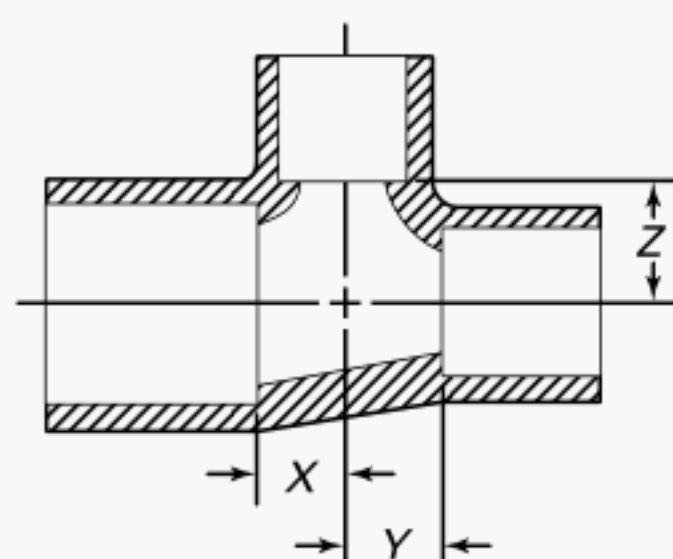

Tee
C x C x C

TABLE B6 DIMENSIONS OF REDUCING TEES

Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]			Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]		
	X	Y	Z		X	Y	Z
$\frac{3}{8} \times \frac{3}{8} \times \frac{1}{2}$	11.0	11.0	9.5	$1\frac{1}{4} \times \frac{3}{4} \times \frac{3}{4}$	16.0	16.0	22.0
$\frac{3}{8} \times \frac{3}{8} \times \frac{1}{4}$	6.5	6.5	8.0	$1\frac{1}{4} \times \frac{1}{2} \times 1\frac{1}{4}$	22.0	22.0	22.0
$\frac{1}{2} \times \frac{1}{2} \times \frac{3}{4}$	14.5	14.5	11.0	$1\frac{1}{4} \times \frac{1}{2} \times 1$	19.0	19.0	22.0
$\frac{1}{2} \times \frac{1}{2} \times \frac{3}{8}$	9.5	9.5	11.0	$1\frac{1}{2} \times 1\frac{1}{2} \times 2\frac{1}{2}$	38.0	38.0	25.5
$\frac{1}{2} \times \frac{1}{2} \times \frac{1}{4}$	8.0	8.0	11.0	$1\frac{1}{2} \times 1\frac{1}{2} \times 2$	32.0	32.0	25.5
$\frac{1}{2} \times \frac{3}{8} \times \frac{1}{2}$	11.0	11.0	11.0	$1\frac{1}{2} \times 1\frac{1}{2} \times 1\frac{1}{4}$	22.0	22.0	25.5
$\frac{1}{2} \times \frac{3}{8} \times \frac{3}{8}$	9.5	9.5	11.0	$1\frac{1}{2} \times 1\frac{1}{2} \times 1$	19.0	19.0	25.5
$\frac{3}{4} \times \frac{3}{4} \times 1$	19.0	19.0	16.0	$1\frac{1}{2} \times 1\frac{1}{2} \times \frac{3}{4}$	16.0	16.0	25.5
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$	11.0	11.0	14.5	$1\frac{1}{2} \times 1\frac{1}{2} \times \frac{1}{2}$	12.5	12.5	25.5
$\frac{3}{4} \times \frac{3}{4} \times \frac{3}{8}$	9.5	9.5	14.5	$1\frac{1}{2} \times 1\frac{1}{4} \times 1\frac{1}{2}$	25.5	25.5	25.5
$\frac{3}{4} \times \frac{1}{2} \times \frac{3}{4}$	14.5	14.5	14.5	$1\frac{1}{2} \times 1\frac{1}{4} \times 1\frac{1}{4}$	22.0	22.0	25.5
$\frac{3}{4} \times \frac{1}{2} \times \frac{1}{2}$	11.0	11.0	14.5	$1\frac{1}{2} \times 1\frac{1}{4} \times 1$	19.0	19.0	25.5
$\frac{3}{4} \times \frac{1}{2} \times \frac{3}{8}$	9.5	9.5	14.5	$1\frac{1}{2} \times 1\frac{1}{4} \times \frac{3}{4}$	16.0	16.0	25.0
$1 \times 1 \times \frac{1}{2}$	25.5	25.5	19.0	$1\frac{1}{2} \times 1\frac{1}{4} \times \frac{1}{2}$	12.5	12.5	25.5
$1 \times 1 \times 1\frac{1}{4}$	22.0	22.0	19.0	$1\frac{1}{2} \times 1 \times 1\frac{1}{2}$	25.5	25.5	25.5
$1 \times 1 \times \frac{3}{4}$	16.0	16.0	19.0	$1\frac{1}{2} \times 1 \times 1\frac{1}{4}$	22.0	22.0	25.5
$1 \times 1 \times \frac{1}{2}$	12.5	12.5	19.0	$1\frac{1}{2} \times 1 \times 1$	19.0	19.0	25.5
$1 \times 1 \times \frac{3}{8}$	11.0	11.0	19.0	$1\frac{1}{2} \times \frac{3}{4} \times 1\frac{1}{2}$	25.5	25.5	25.5
$1 \times \frac{3}{4} \times 1$	19.0	19.0	19.0	$1\frac{1}{2} \times \frac{1}{2} \times 1\frac{1}{2}$	25.5	25.0	25.5
$1 \times \frac{3}{4} \times \frac{3}{4}$	16.0	16.0	19.0	$2 \times 2 \times 4$	57.0	57.0	32.0
$1 \times \frac{3}{4} \times \frac{1}{2}$	12.5	12.5	19.0	$2 \times 2 \times 3$	44.5	44.5	32.0
$1 \times \frac{1}{2} \times 1$	19.0	19.0	19.0	$2 \times 2 \times 2\frac{1}{2}$	38.0	38.0	32.0
$1 \times \frac{1}{2} \times \frac{3}{4}$	16.0	16.0	19.0	$2 \times 2 \times 1\frac{1}{2}$	25.5	25.5	32.0
$1 \times \frac{1}{2} \times \frac{1}{2}$	12.5	12.5	19.0	$2 \times 2 \times 1\frac{1}{4}$	22.0	22.0	32.0
$1\frac{1}{4} \times 1\frac{1}{4} \times 2$	32.0	32.0	22.0	$2 \times 2 \times 1$	19.0	19.0	32.0
$1\frac{1}{4} \times 1\frac{1}{4} \times 1\frac{1}{2}$	25.5	25.5	22.0	$2 \times 2 \times \frac{3}{4}$	16.0	16.0	32.0
$1\frac{1}{4} \times 1\frac{1}{4} \times 1$	19.0	19.0	22.0	$2 \times 2 \times \frac{1}{2}$	12.5	12.5	32.0
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{3}{4}$	16.0	16.0	22.0	$2 \times 1\frac{1}{2} \times 2$	32.0	32.0	32.0
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{1}{2}$	12.5	12.5	22.0	$2 \times 1\frac{1}{2} \times 1\frac{1}{2}$	25.5	25.5	32.0
$1\frac{1}{4} \times 1 \times 1\frac{1}{4}$	22.0	22.0	22.0	$2 \times 1\frac{1}{2} \times 1\frac{1}{4}$	22.0	22.0	32.0
$1\frac{1}{4} \times 1 \times 1$	19.0	19.0	22.0	$2 \times 1\frac{1}{2} \times 1$	19.0	19.0	32.0
$1\frac{1}{4} \times 1 \times \frac{3}{4}$	16.0	16.0	22.0	$2 \times 1\frac{1}{2} \times \frac{3}{4}$	16.0	16.0	32.0
$1\frac{1}{4} \times 1 \times \frac{1}{2}$	12.5	12.5	22.0	$2 \times 1\frac{1}{2} \times \frac{1}{2}$	12.5	12.5	32.0
$1\frac{1}{4} \times \frac{3}{4} \times 1\frac{1}{4}$	22.0	22.0	22.0	$2 \times 1\frac{1}{4} \times 2$	32.0	32.0	32.0
$1\frac{1}{4} \times \frac{3}{4} \times 1$	19.0	19.0	22.0	$2 \times 1\frac{1}{4} \times 1\frac{1}{2}$	25.5	25.5	32.0

(continued)

TABLE B6 DIMENSIONS OF REDUCING TEES (CONT'D)


Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]			Standard Water Tube Size [Note (1)]	Laying Length [Note (2)]		
	X	Y	Z		X	Y	Z
$2 \times 1\frac{1}{4} \times 1\frac{1}{4}$	22.0	22.0	32.0	$3 \times 2 \times 1\frac{1}{2}$	25.5	25.0	44.5
$2 \times 1 \times 2$	32.0	32.0	32.0	$3 \times 1\frac{1}{2} \times 3$	44.5	44.5	44.5
$2 \times \frac{3}{4} \times 2$	32.0	32.0	32.0	$3 \times 1\frac{1}{4} \times 3$	44.5	44.5	44.5
$2 \times \frac{1}{2} \times 2$	32.0	32.0	32.0	$3 \times 1 \times 3$	44.5	44.5	44.5
$2\frac{1}{2} \times 2\frac{1}{2} \times 4$	57.0	57.0	38.0	$3\frac{1}{2} \times 3\frac{1}{2} \times 3$	44.5	44.5	51.0
$2\frac{1}{2} \times 2\frac{1}{2} \times 3$	44.5	44.5	38.0	$3\frac{1}{2} \times 3 \times 3\frac{1}{2}$	51.0	51.0	51.0
$2\frac{1}{2} \times 2\frac{1}{2} \times 2$	32.0	32.0	38.0	$4 \times 4 \times 6$	92.0	92.0	66.0
$2\frac{1}{2} \times 2\frac{1}{2} \times 1\frac{1}{2}$	25.5	25.5	38.0	$4 \times 4 \times 3$	44.5	44.5	57.0
$2\frac{1}{2} \times 2\frac{1}{2} \times 1\frac{1}{4}$	22.0	22.0	38.0	$4 \times 4 \times 2\frac{1}{2}$	38.0	38.0	57.0
$2\frac{1}{2} \times 2\frac{1}{2} \times 1$	19.0	19.0	38.0	$4 \times 4 \times 2$	32.0	32.0	57.0
$2\frac{1}{2} \times 2\frac{1}{2} \times \frac{3}{4}$	16.0	16.0	38.0	$4 \times 4 \times 1\frac{1}{2}$	25.5	25.5	57.0
$2\frac{1}{2} \times 2\frac{1}{2} \times \frac{1}{2}$	12.5	12.5	38.0	$4 \times 4 \times 1\frac{1}{4}$	22.0	22.0	57.0
$2\frac{1}{2} \times 2 \times 2\frac{1}{2}$	38.0	38.0	38.0	$4 \times 4 \times 1$	19.0	19.0	57.0
$2\frac{1}{2} \times 2 \times 2$	32.0	32.0	38.0	$4 \times 4 \times \frac{3}{4}$	16.0	16.0	57.0
$2\frac{1}{2} \times 2 \times 1\frac{1}{2}$	25.5	25.5	38.0	$4 \times 3 \times 4$	57.0	57.0	57.0
$2\frac{1}{2} \times 2 \times 1\frac{1}{4}$	22.0	22.0	38.0	$4 \times 3 \times 3$	44.5	44.5	57.0
$2\frac{1}{2} \times 2 \times 1$	19.0	19.0	38.0	$4 \times 3 \times 2\frac{1}{2}$	38.0	38.0	57.0
$2\frac{1}{2} \times 2 \times \frac{3}{4}$	16.0	16.0	38.0	$4 \times 3 \times 2$	32.0	32.0	57.0
$2\frac{1}{2} \times 2 \times \frac{1}{2}$	12.5	12.5	38.0	$4 \times 2\frac{1}{2} \times 4$	57.0	57.0	57.0
$2\frac{1}{2} \times 1\frac{1}{2} \times 2\frac{1}{2}$	38.0	38.0	38.0	$4 \times 2 \times 4$	57.0	57.0	57.0
$2\frac{1}{2} \times 1\frac{1}{2} \times 2$	32.0	32.0	38.0	$4 \times 2 \times 3$	44.5	44.5	57.0
$2\frac{1}{2} \times 1\frac{1}{2} \times 1\frac{1}{2}$	25.5	25.5	38.0	$4 \times 2 \times 2$	32.0	32.0	57.0
$2\frac{1}{2} \times 1\frac{1}{4} \times 2\frac{1}{2}$	38.0	38.0	38.0	$4 \times 1\frac{1}{2} \times 4$	57.0	57.0	57.0
$2\frac{1}{2} \times 1 \times 2\frac{1}{2}$	38.0	38.0	38.0	$4 \times 1\frac{1}{4} \times 4$	57.0	57.0	57.0
$2\frac{1}{2} \times \frac{3}{4} \times 2\frac{1}{2}$	38.0	38.0	38.0	$4 \times 1 \times 4$	57.0	57.0	57.0
$2\frac{1}{2} \times \frac{1}{2} \times 2\frac{1}{2}$	38.0	38.0	38.0	$5 \times 5 \times 4$	66.0	66.0	79.5
$3 \times 3 \times 4$	57.0	57.0	44.5	$5 \times 4 \times 5$	79.5	79.5	79.5
$3 \times 3 \times 2\frac{1}{2}$	38.0	38.0	44.5	$6 \times 6 \times 8$	124.0	124.0	98.5
$3 \times 3 \times 2$	32.0	32.0	44.5	$6 \times 6 \times 4$	66.5	66.5	92.0
$3 \times 3 \times 1\frac{1}{2}$	25.5	25.5	44.5	$6 \times 6 \times 3$	50.5	50.5	92.0
$3 \times 3 \times 1\frac{1}{4}$	22.0	22.0	44.5	$6 \times 6 \times 2\frac{1}{2}$	47.5	47.5	92.0
$3 \times 3 \times 1$	19.0	19.0	44.5	$6 \times 6 \times 2$	41.5	41.5	92.0
$3 \times 3 \times \frac{3}{4}$	16.0	16.0	44.5	$6 \times 6 \times 1\frac{1}{2}$	35.0	35.0	92.0
$3 \times 3 \times \frac{1}{2}$	12.5	12.5	44.5	$6 \times 6 \times 1\frac{1}{4}$	32.0	32.0	92.0
$3 \times 2\frac{1}{2} \times 3$	44.5	44.5	44.5	$6 \times 6 \times 1$	28.5	28.5	92.0
$3 \times 2\frac{1}{2} \times 2\frac{1}{2}$	38.0	38.0	44.5	$6 \times 4 \times 6$	92.0	92.0	92.0
$3 \times 2\frac{1}{2} \times 2$	32.0	32.0	44.5	$6 \times 4 \times 4$	66.5	66.5	92.0
$3 \times 2\frac{1}{2} \times 1\frac{1}{2}$	25.5	25.5	44.5	$6 \times 3 \times 6$	92.0	92.0	92.0
$3 \times 2\frac{1}{2} \times 1\frac{1}{4}$	22.0	22.0	44.5	$6 \times 2\frac{1}{2} \times 6$	92.0	92.0	92.0
$3 \times 2\frac{1}{2} \times 1$	19.0	19.0	44.5	$6 \times 2 \times 6$	92.0	92.0	92.0
$3 \times 2 \times 3$	44.5	44.5	44.5	$8 \times 8 \times 6$	98.5	98.5	124.0
$3 \times 2 \times 2\frac{1}{2}$	38.0	38.0	44.5	$8 \times 8 \times 4$	73.0	73.0	124.0
$3 \times 2 \times 2$	32.0	32.0	44.5

(continued)

TABLE B6 (CONT'D)

GENERAL NOTES:
(a) Dimensions are in millimeters.
(b) For dimensions not given in this table, see Table B3.

NOTES:
(1) For size designation of fitting, see Section 4.
(2) For inspection tolerances, see Section 8 and Table 2.

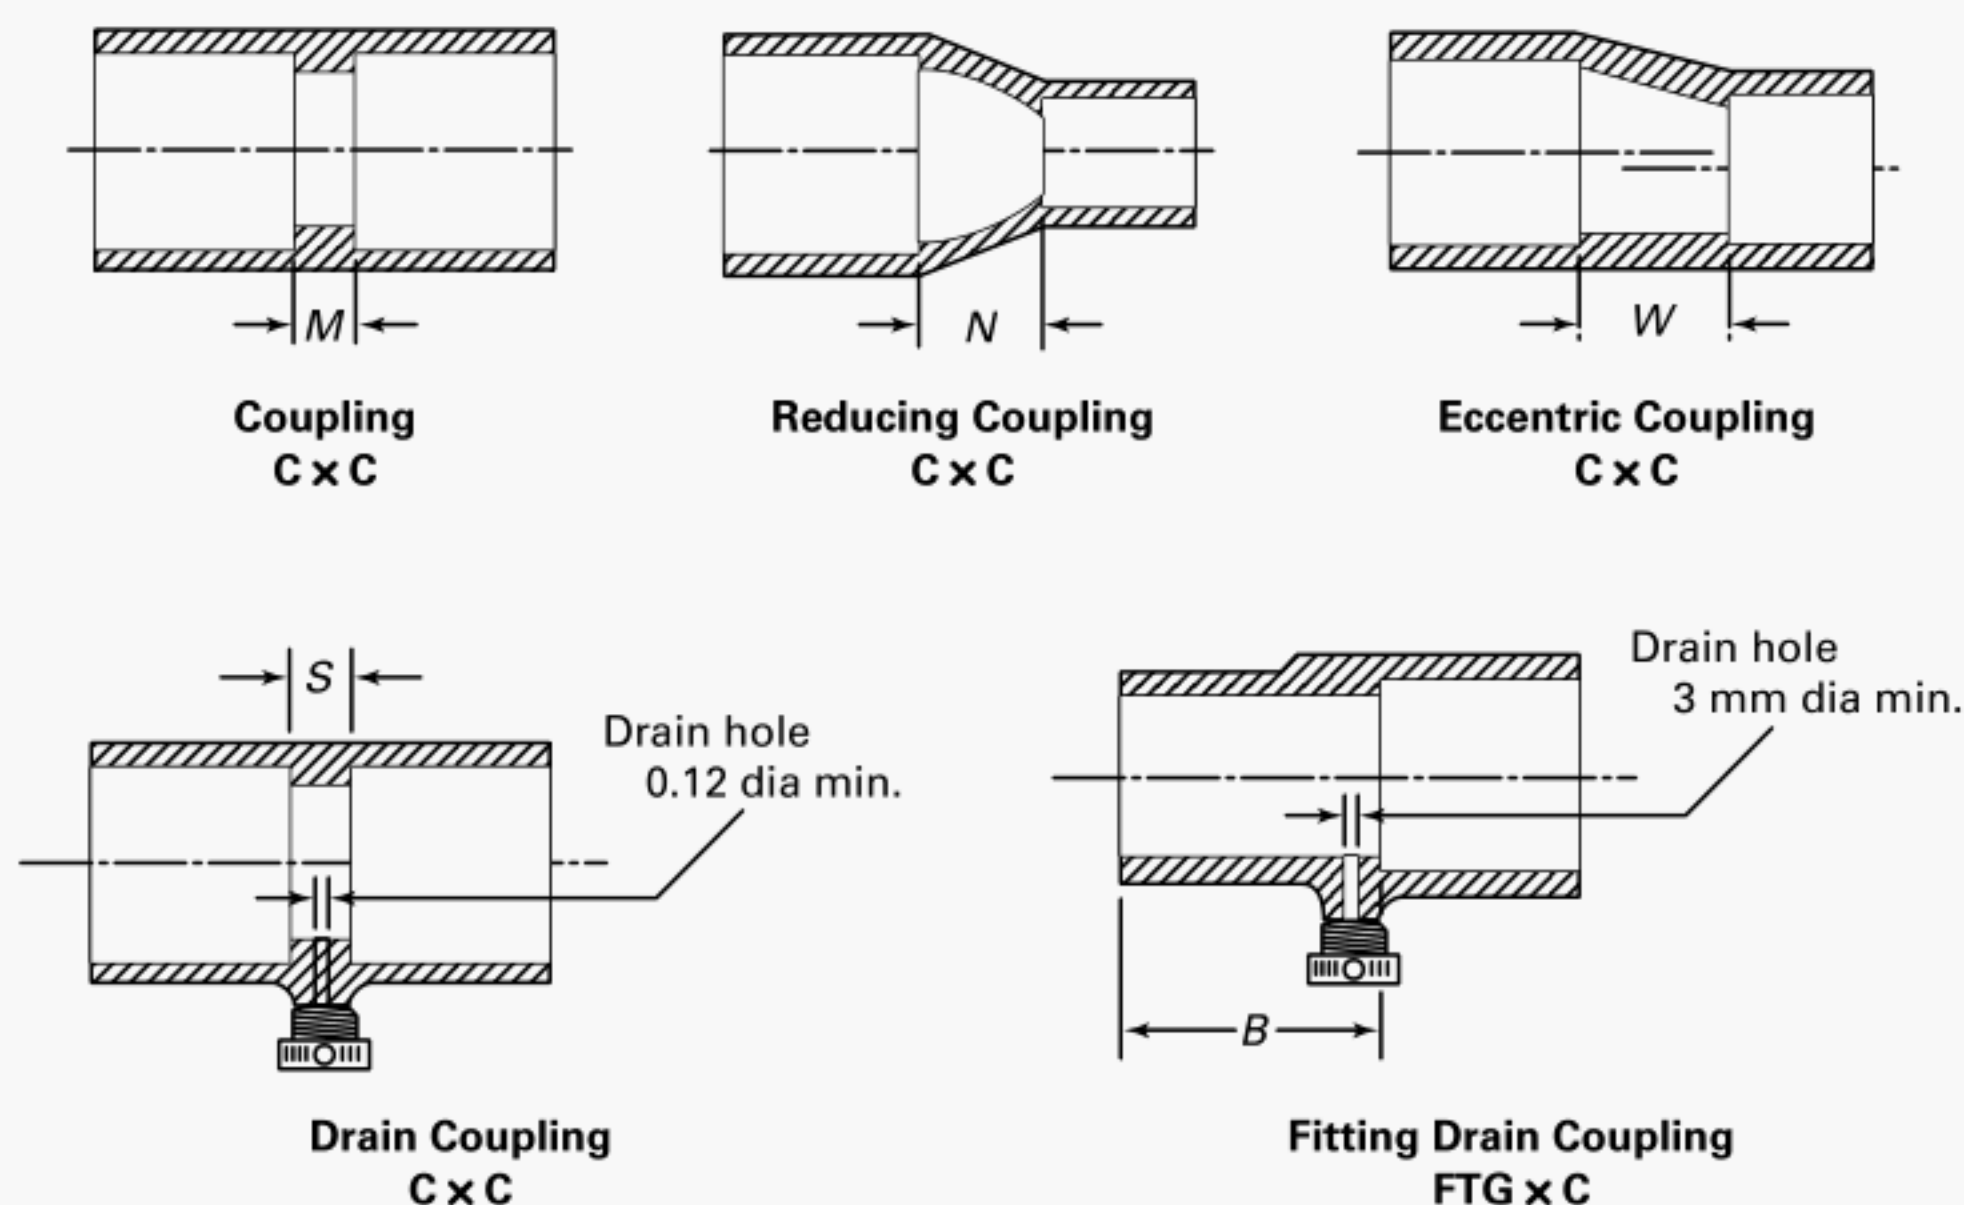**TABLE B7 DIMENSIONS OF COUPLINGS**

Straight		Reducing		Eccentric		Drain	
Standard Water Tube Size [Note (1)]	Laying Length [Note (2)], <i>M</i>	Standard Water Tube Size [Note (1)]	Laying Length Size [Note (2)]	Standard Water Tube Size [Note (1)]	Laying Length [Note (2)], <i>W</i>	Laying Length [Note (2)], <i>S</i>	Laying Length [Note (2)], <i>B</i>
$\frac{1}{4}$	1.5	$\frac{3}{4} \times \frac{1}{2}$	8.0	$\frac{3}{4} \times \frac{1}{2}$	16.0	6.5	...
$\frac{3}{8}$	1.5	$1 \times \frac{3}{4}$	9.5	$1 \times \frac{3}{4}$	17.5	6.5	...
$\frac{1}{2}$	3.0	$1\frac{1}{4} \times 1$	9.5	$1\frac{1}{4} \times 1$	19.0	6.5	25.5
$\frac{3}{4}$	3.0	$1\frac{1}{4} \times \frac{3}{4}$	9.5	$1\frac{1}{4} \times \frac{3}{4}$	19.0	6.5	32.5
1	3.0	$1\frac{1}{2} \times 1\frac{1}{4}$	9.5	$1\frac{1}{2} \times 1\frac{1}{4}$	17.5	6.5	...
$1\frac{1}{4}$	3.0	$1\frac{1}{2} \times 1$	9.5	$1\frac{1}{2} \times 1$	17.5	6.5	...
$1\frac{1}{2}$	3.0	$1\frac{1}{2} \times \frac{3}{4}$	11.0	$2 \times 1\frac{1}{2}$	28.5	6.5	...
2	4.5	$2 \times 1\frac{1}{2}$	12.5	$2 \times 1\frac{1}{4}$	24.0
$2\frac{1}{2}$	4.5	$2 \times 1\frac{1}{4}$	12.5	$2\frac{1}{2} \times 2$	30.0
3	4.5	2×1	12.5	$3 \times 2\frac{1}{2}$	32.0
$3\frac{1}{2}$	6.5	$2 \times \frac{3}{4}$	12.5	3×2	33.5
4	6.5	$2\frac{1}{2} \times 2$	14.5	4×3	51.0
5	6.5	$2\frac{1}{2} \times 1\frac{1}{2}$	14.5
6	6.5	$2\frac{1}{2} \times 1\frac{1}{4}$	16.0
8	16.0	$2\frac{1}{2} \times 1$	16.0
...	...	$3 \times 2\frac{1}{2}$	16.0
...	...	3×2	16.0
...	...	4×3	17.5
...	...	$4 \times 2\frac{1}{2}$	28.5
...	...	4×2	30.0
...	...	6×4	33.5
...	...	8×6	35.0

(continued)

TABLE B7 (CONT'D)

GENERAL NOTES:

- (a) Dimensions are in millimeters.
- (b) For dimensions not given in this table, see Table B3.

NOTES:

- (1) For size designation of fittings, see Section 4.
- (2) For inspection tolerances, see Section 8 Table 2.

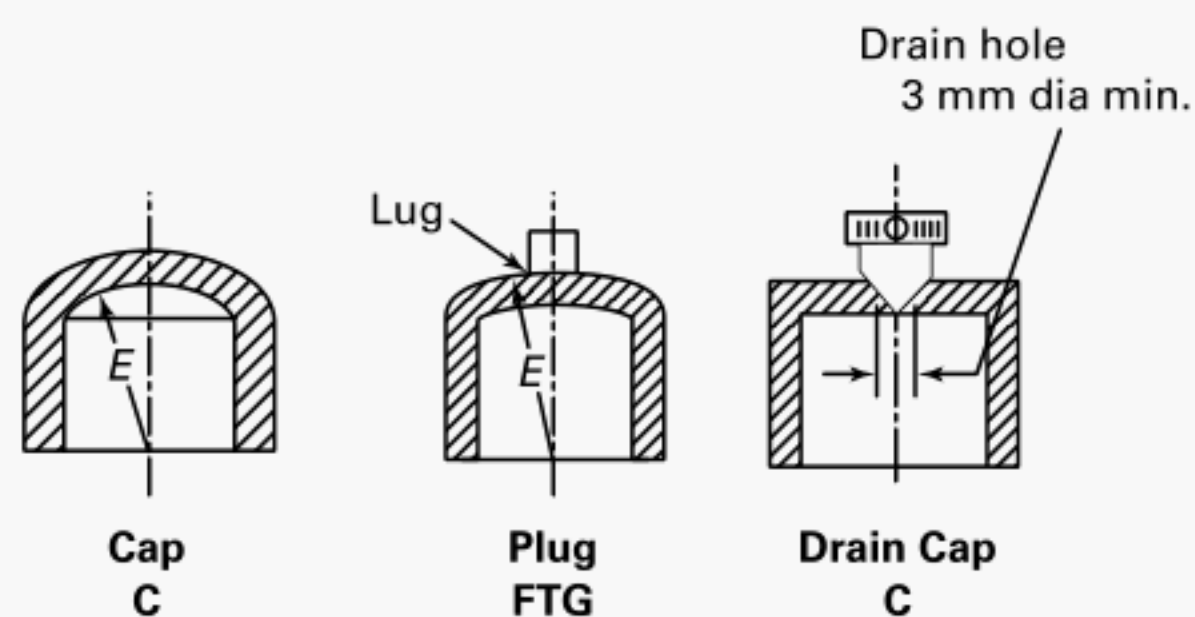


TABLE B8 DIMENSIONS OF CAPS AND PLUGS


Standard Water Tube Size [Note (1)]	Caps and Plugs	
	Radius [Note (2)], <i>B</i>	
$\frac{1}{4}$	9.5	
$\frac{3}{8}$	12.5	
$\frac{1}{2}$	16.0	
$\frac{3}{4}$	22.0	
1	28.5	
$1\frac{1}{4}$	35.0	
$1\frac{1}{2}$	41.5	
2	54.0	
$2\frac{1}{2}$	66.5	
3	79.5	
$3\frac{1}{2}$	92.0	
4	105.0	
5	130.0	
6	155.5	

GENERAL NOTES:

- (a) Dimensions are in millimeters.
- (b) For dimensions not given in this table, see Table B3.
- (c) Casting of lug or square on plugs shall be optional.

NOTES:

- (1) For size designation of fitting see, Section 4.
- (2) Caps may have either flat or rounded top.

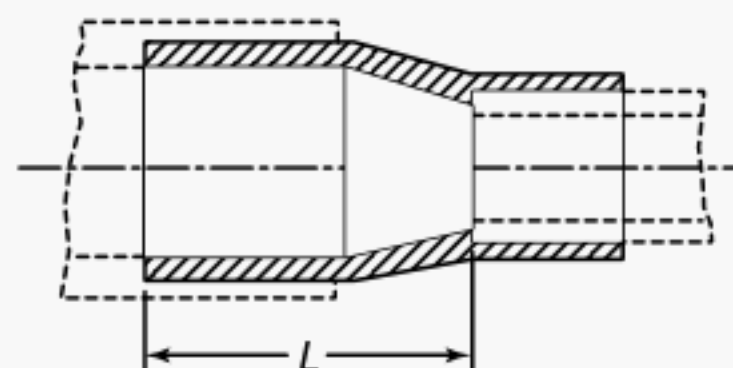

Fitting reducer
(or Bushing)
FTG × C

TABLE B9 DIMENSIONS OF FITTING REDUCERS

Standard Water Tube Size [Note (1)]	Length, <i>L</i>
$\frac{3}{8} \times \frac{1}{4}$	17.5
$\frac{1}{2} \times \frac{3}{8}$	24.0
$\frac{1}{2} \times \frac{1}{4}$	24.0
$\frac{3}{4} \times \frac{1}{2}$	30.0
$\frac{3}{4} \times \frac{3}{8}$	32.0
$1 \times \frac{3}{4}$	38.0
$1 \times \frac{1}{2}$	38.0
$1\frac{1}{4} \times 1$	41.5
$1\frac{1}{4} \times \frac{3}{4}$	41.5
$1\frac{1}{4} \times \frac{1}{2}$	41.5
$1\frac{1}{2} \times 1\frac{1}{4}$	46.0
$1\frac{1}{2} \times 1$	46.0
$1\frac{1}{2} \times \frac{3}{4}$	46.0
$2 \times 1\frac{1}{2}$	54.0
$2 \times 1\frac{1}{4}$	54.0
2×1	54.0
$2\frac{1}{2} \times 2$	60.5
$2\frac{1}{2} \times 1\frac{1}{2}$	60.5
$2\frac{1}{2} \times 1\frac{1}{4}$	60.5
$3 \times 2\frac{1}{2}$	66.5
3×2	66.5
$3 \times 1\frac{1}{2}$	66.5
4×3	87.5
$4 \times 2\frac{1}{2}$	87.5
4×2	87.5

GENERAL NOTES:

(a) Dimensions are in millimeters.

(b) For dimensions not given in this table, see Table B3.

NOTE:

(1) For size designation of fitting, see Section 4.

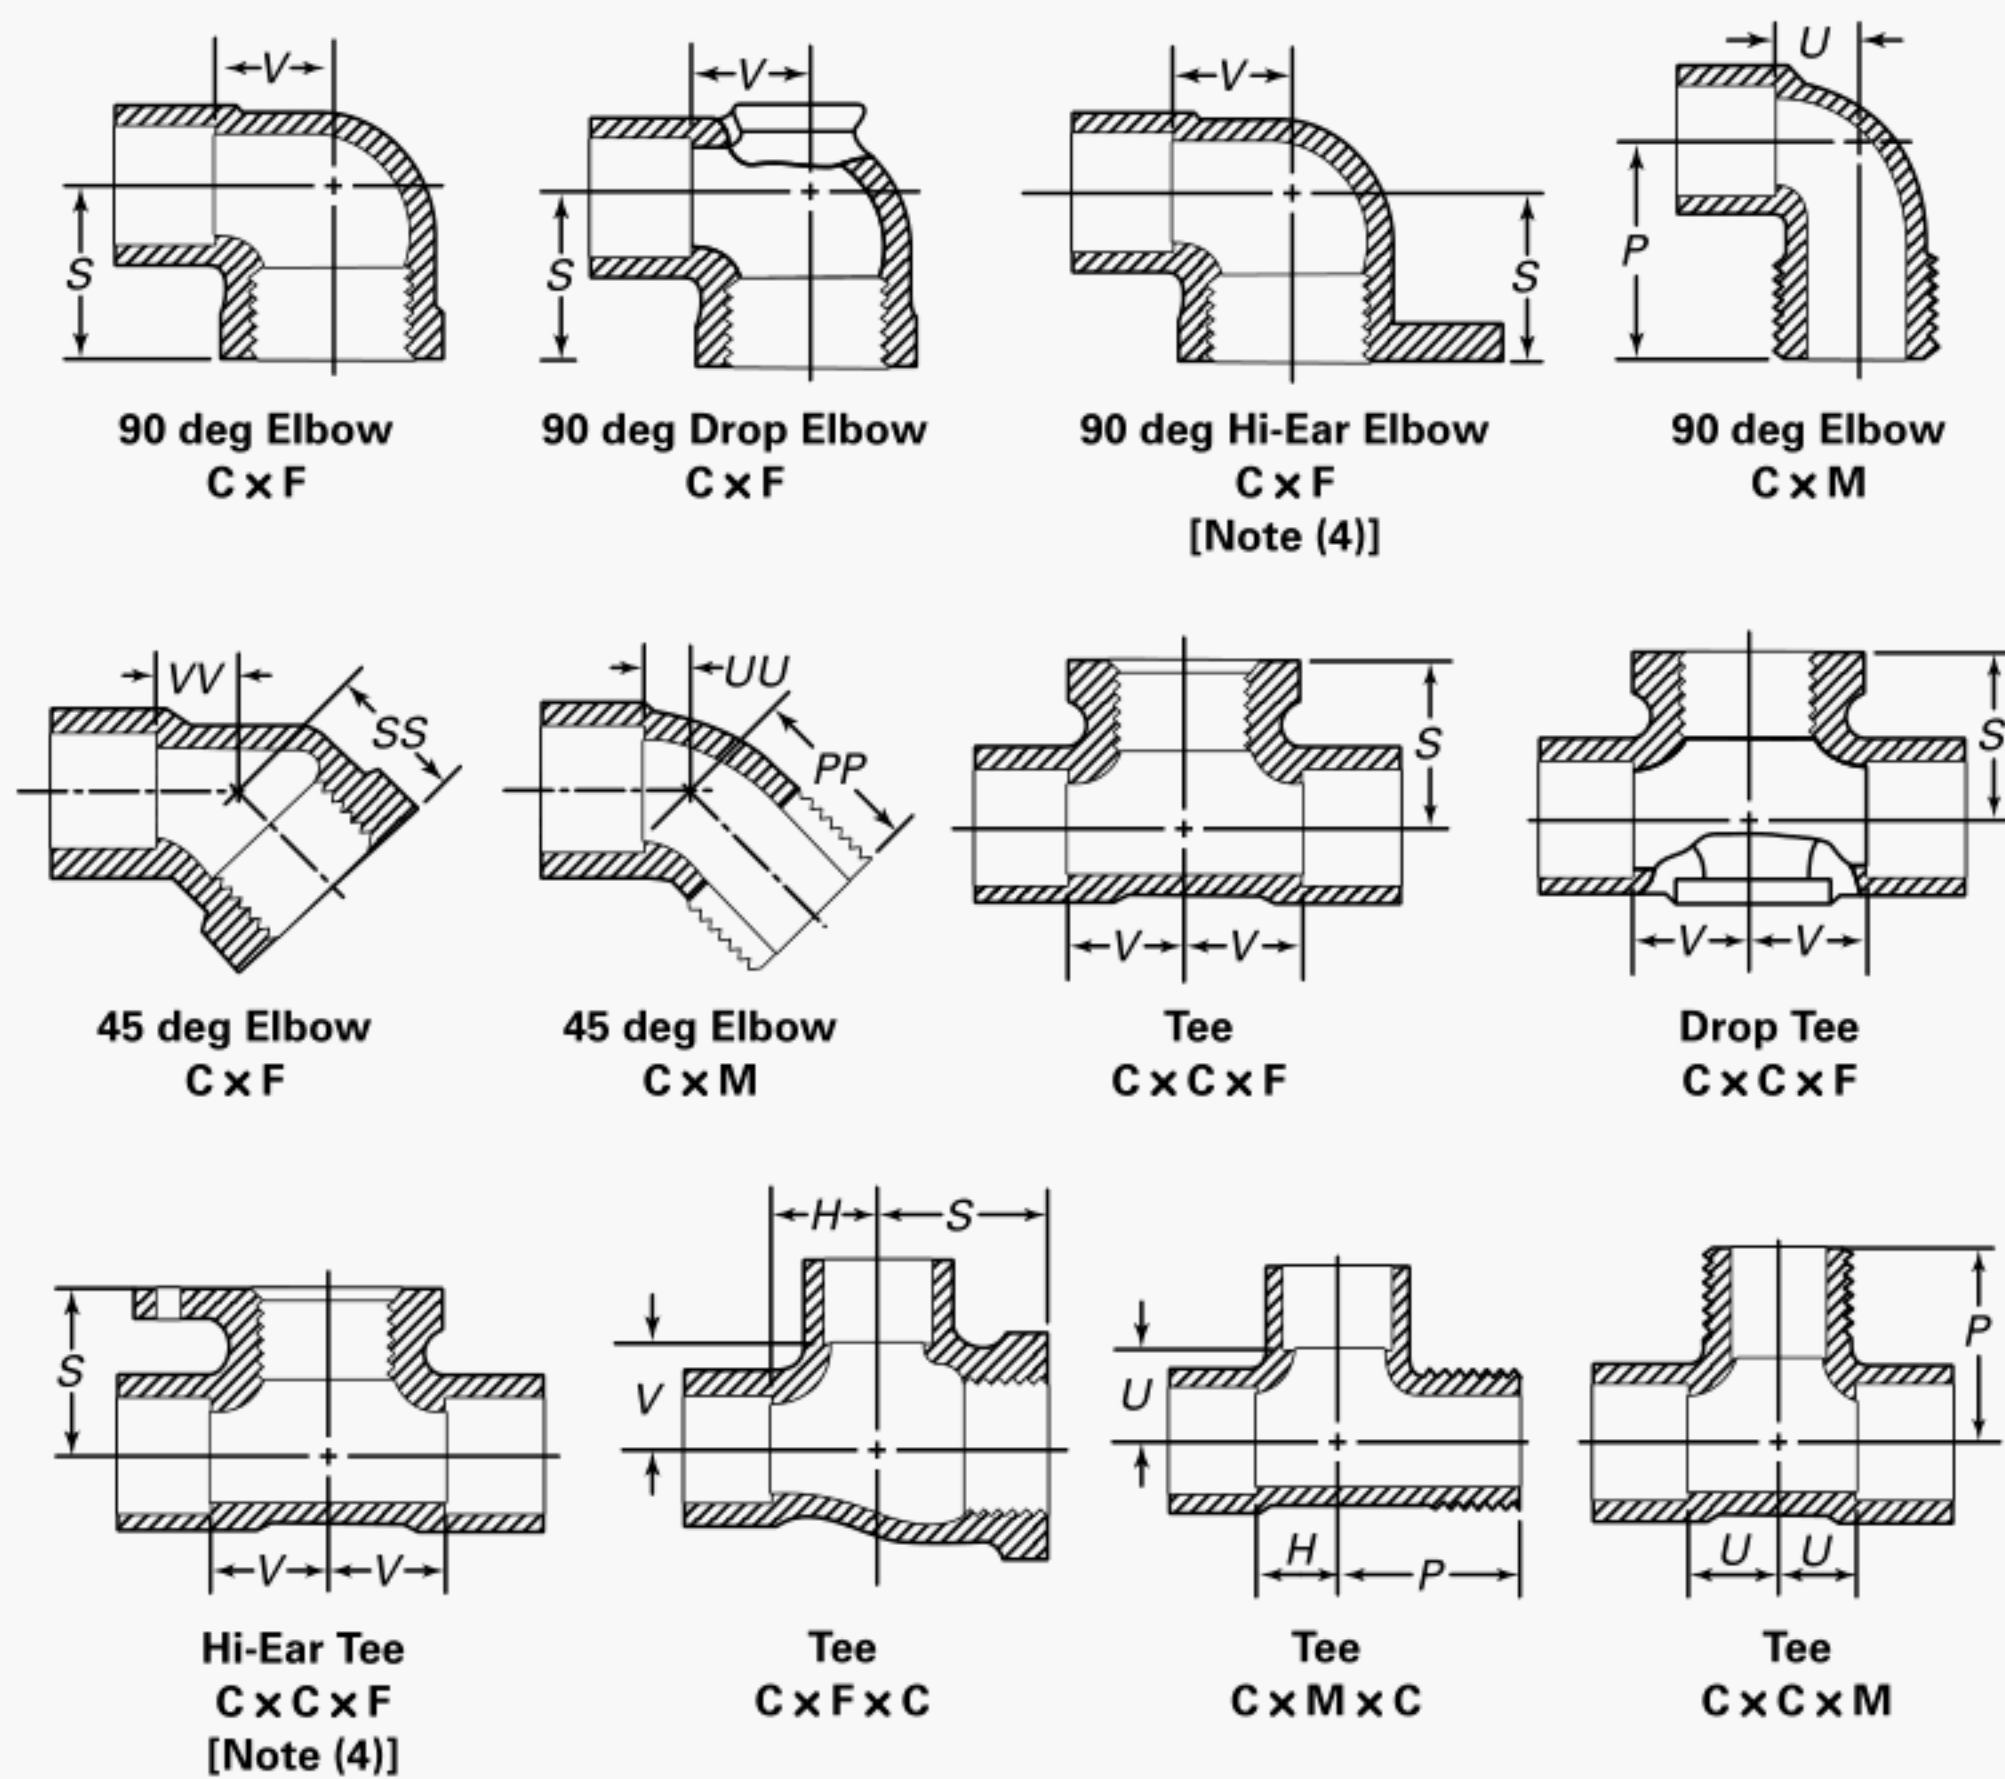


TABLE B10 AND B11 ILLUSTRATION

**TABLE B10 DIMENSIONS OF SOLDER JOINT ELBOWS AND TEES WITH PIPE THREAD ENDS
(STRAIGHT SIZES)**

Standard Water Tube and Pipe Thread Size [Note (1)]	Internal Threads [Note (2)]					External Threads [Note (2)]				
	Center-to-End [Note (3)]		Laying Length [Note (3)]			Center-to-End [Note (3)]		Laying Length [Note (3)]		
	Ell and Tee, <i>S</i>	45 deg Ell, <i>SS</i>	Ell and Tee, <i>V</i>	Tee, <i>H</i>	45 deg Ell, <i>VV</i>	Ell and Tee, <i>P</i>	45 deg Ell, <i>PP</i>	Ell and Tee, <i>U</i>	Tee, <i>H</i>	45 deg Ell, <i>UU</i>
$\frac{1}{4}$	14.5	...	9.5	24.0	...	6.5
$\frac{3}{8}$	17.5	17.5	11.0	8.0	4.5	27.0	20.5	8.0	8.0	4.5
$\frac{1}{2}$	22.0	24.0	14.5	11.0	4.5	33.5	25.5	11.0	11.0	4.5
$\frac{3}{4}$	25.5	25.5	17.5	14.5	6.5	38.0	30.0	14.5	14.5	6.5
1	32.0	30.0	22.0	19.0	8.0	41.5	33.5	19.0	19.0	8.0
$1\frac{1}{4}$	38.0	...	25.5	22.0	...	51.0	...	22.0
$1\frac{1}{2}$	41.5	...	28.5	25.5	...	55.5	...	25.5
2	49.0	...	35.0	32.0	...	66.5	...	32.0
$2\frac{1}{2}$	63.5	...	41.5
3	71.5	...	49.0
4	87.5	...	62.0
6	124.0	...	98.5

GENERAL NOTES:

- (a) For reference, see Table B10 Illustration beginning on page 40.
 (b) Dimensions are in millimeters.
 (c) For dimensions of threaded ends, see ASME B16.15. For configuration of threaded ends, see Section 10. For dimensions of solder joint ends, see Table B3.
 (d) For dimensions of reducing tees and ells, see Table B11.

NOTES:

- (1) For size designation of fitting, see Section 4.
 (2) For threads of threaded ends, see Section 9.
 (3) For inspection tolerances, see Section 8 and Table 2.
 (4) Hi-ear fittings are designed for use with 14 mm maximum width strap.

**TABLE B11 DIMENSIONS OF SOLDER JOINT ELBOWS AND TEES WITH PIPE THREAD ENDS
(REDUCING SIZES)**

Standard Water Tube and Pipe Thread Size [Note (1)]	Internal Threads [Note (2)]							External Threads [Note (2)]	
	Center-to-End			Laying Length [Note (3)]				Center- to- End	Laying Length [Note (3)]
	<i>S</i>			<i>V</i>			<i>H</i>	<i>P</i>	<i>U</i>
	90 deg El C-F	Tee C-C-F	Tee C-F-C	90 deg El C-F	Tee C-C-F	Tee C-F-C	Tee C-F-C	90 deg El C-M	90 deg El C-M
$\frac{3}{8} \times \frac{3}{8} \times \frac{1}{2}$...	20.5	14.5
$\frac{3}{8} \times \frac{1}{2}$	20.5	14.5	32.0	11.0
$\frac{1}{2} \times \frac{1}{2} \times \frac{3}{4}$...	23.5	17.5
$\frac{1}{2} \times \frac{3}{4}$	24.0	17.5	35.0	14.5
$\frac{1}{2} \times \frac{1}{2} \times \frac{3}{8}$...	20.5	12.5
$\frac{1}{2} \times \frac{3}{8}$	20.5	12.5	28.5	8.0
$\frac{3}{4} \times \frac{3}{4} \times 1$...	28.5	22.0
$\frac{3}{4} \times 1$	28.5	22.0	43.0	19.0
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$...	24.0	24.0	...	14.5	17.5	11.0
$\frac{3}{4} \times \frac{1}{2}$	24.0	14.5	36.5	11.0
$\frac{3}{4} \times \frac{3}{4} \times \frac{3}{8}$...	22.0	12.5
$\frac{3}{4} \times \frac{3}{8}$	22.0	12.5
$\frac{3}{4} \times \frac{1}{2} \times \frac{3}{4}$	24.0	14.5	14.5
$\frac{3}{4} \times \frac{1}{2} \times \frac{1}{2}$...	24.0	22.0	...	14.5	14.5	11.0
$1 \times 1\frac{1}{4}$	35.0	25.5
$1 \times 1 \times \frac{3}{4}$...	30.0	17.5
$1 \times \frac{3}{4}$	30.0	17.5	41.5	14.5
$1 \times 1 \times \frac{1}{2}$...	28.5	14.5
$1 \times 1 \times \frac{3}{8}$...	27.0	12.5
$1 \times \frac{3}{4} \times 1$...	32.0	30.0	...	22.0	19.0	19.0
$1 \times \frac{3}{4} \times \frac{3}{4}$...	30.0	17.5
$1 \times \frac{3}{4} \times \frac{1}{2}$...	28.5	14.5
$1 \times \frac{1}{2} \times 1$	28.5	19.0	19.0
$1 \times \frac{1}{2}$	28.5	14.5
$1\frac{1}{4} \times 1\frac{1}{4} \times 1$...	36.5	22.0
$1\frac{1}{4} \times 1$	36.5	22.0
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{3}{4}$...	33.5	17.5
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{1}{2}$...	32.0	14.5
$1\frac{1}{4} \times 1\frac{1}{4} \times \frac{3}{8}$...	30.0	12.5
$1\frac{1}{4} \times \frac{3}{4} \times 1$	30.0	22.0	19.0
$1\frac{1}{2} \times 1\frac{1}{2} \times 1$...	38.0	35.0	...	22.0	28.5	19.0
$1\frac{1}{2} \times 1\frac{1}{2} \times \frac{3}{4}$...	36.5	17.5
$1\frac{1}{2} \times 1\frac{1}{2} \times \frac{1}{2}$...	35.0	14.5
$1\frac{1}{2} \times \frac{3}{4} \times 1$	30.0	25.5	19.0
$2 \times 2 \times 1\frac{1}{2}$...	47.5	28.5
$2 \times 2 \times 1$...	44.5	22.0
$2 \times 2 \times \frac{3}{4}$...	43.0	17.5
$2 \times 2 \times \frac{1}{2}$...	41.5	14.5
$2\frac{1}{2} \times 2\frac{1}{2} \times \frac{3}{4}$...	52.5	17.5

(continued)

TABLE B11 (CONT'D)

GENERAL NOTES:

- (a) For reference, see Table B11 Illustration beginning on page 40.
- (b) Dimensions are in millimeters.
- (c) For dimensions of threaded ends, see ASME B16.15. For configuration of threaded ends, see Section 10. For dimensions of solder joint ends, see Table B3.

NOTES:

- (1) For designation of fitting, see Section 4.
- (2) For threads of threaded ends, see Section 9.
- (3) For inspection tolerance, see Section 8 and Table 2.

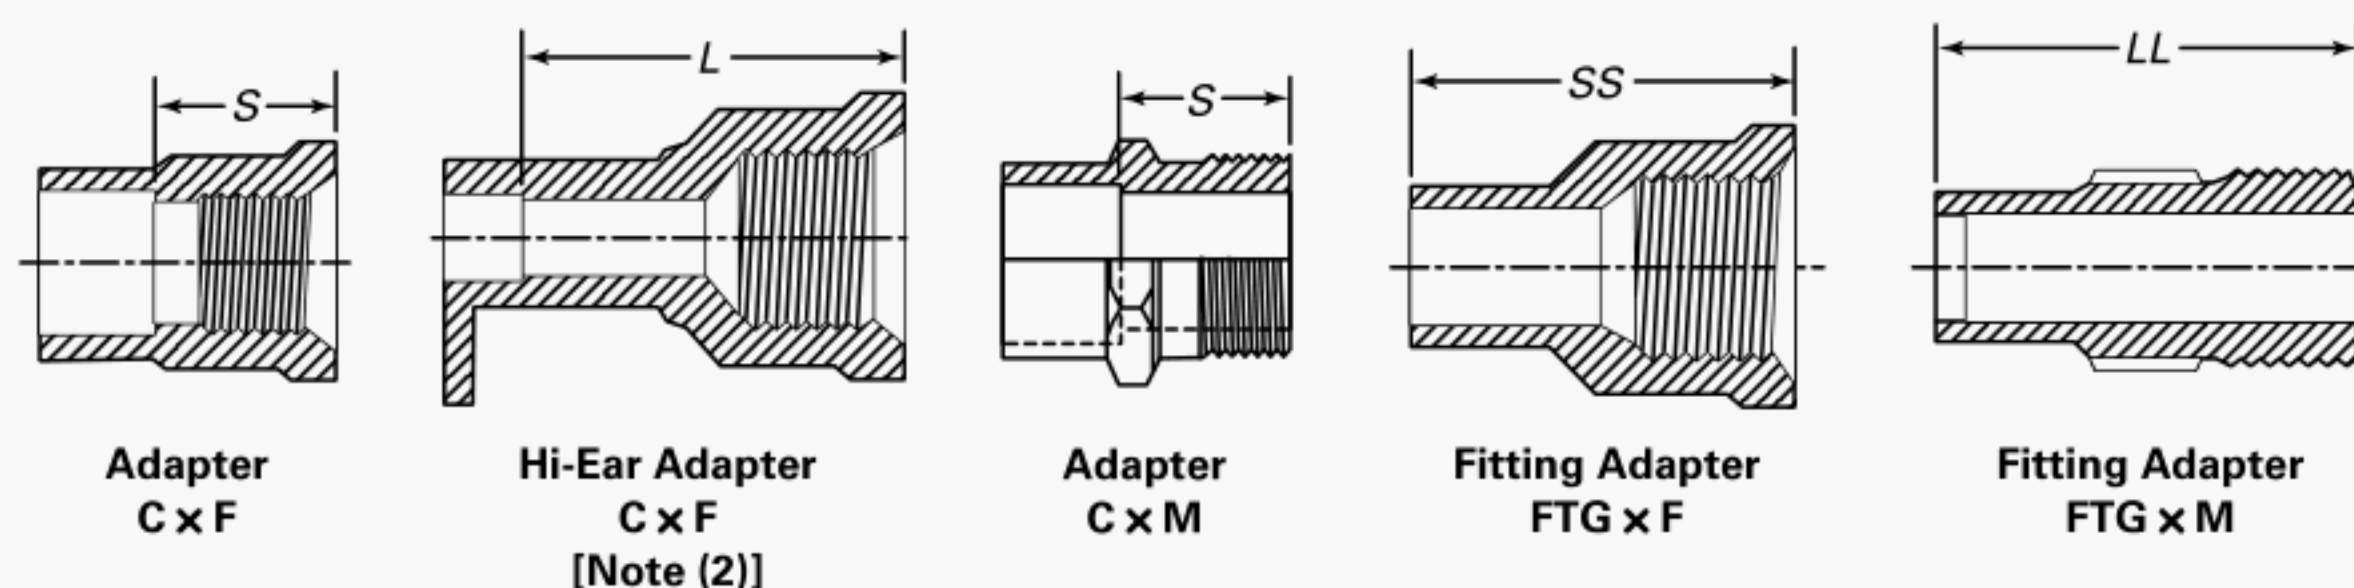


TABLE B12 DIMENSIONS OF SOLDER JOINT ADAPTERS AND FITTING ADAPTERS WITH PIPE THREAD ENDS (STRAIGHT AND REDUCING SIZES)


Standard Water Tube and Pipe Thread Size [Note (1)]		Shoulder- to-End <i>S</i>	End-to-End		End-to- Tube Stop <i>L</i>
Solder Joint	Pipe Thread		<i>SS</i>	<i>LL</i>	
1/4	3/8	16.0
1/4	1/4	16.0	...	25.5	...
3/8	1/2	19.0	...	32.0	...
3/8	3/8	16.0	27.0	28.5	...
1/2	1	25.5
1/2	3/4	22.0	36.5	37.5	...
1/2	1/2	18.0	35.0	35.0	32.0
1/2	3/8	16.0	31.0	32.0	...
3/4	1	25.5	46.0	48.5	...
3/4	3/4	22.0	42.0	43.5	...
3/4	1/2	19.0	41.5	41.5	...
1	1 1/4	27.0	53.0	55.0	...
1	1	25.5	50.0	53.0	...
1	3/4	22.0	46.0	48.5	...
1 1/4	2	28.5	...	60.5	...
1 1/4	1 1/2	27.0	56.5	58.0	...
1 1/4	1 1/4	27.0	51.5	56.5	...
1 1/4	1	27.0	51.5	54.0	...
1 1/2	2	28.5	...	63.5	...
1 1/2	1 1/2	27.0	56.5	61.0	...
1 1/2	1 1/4	27.0	56.5	59.5	...
1 1/2	1	25.5	...	57.0	...
2	2	28.5	64.5	70.0	...
2	1 1/2	28.5	...	67.5	...
2 1/2	2 1/2	35.0	78.5	79.5	...
3	3	38.0	82.0	86.5	...
4	4	43.0	97.0	105.0	...
6	6	50.5	135.5	146.0	...
8	8	57.0

(continued)

TABLE B12 (CONT'D)

GENERAL NOTES:
(a) Dimensions are in millimeters.
(b) For threaded ends, see Section 9.
(c) For dimensions of threaded ends, see ASME B16.15, Class 125. For sizes not listed in ASME B16.15, Class 125, refer to ASME B16.3, Class 150. For configuration of threaded ends, see Section 10. For dimensions of solder joint ends, see Table B3.

NOTES:
(1) For size designation of fitting, see Section 4.
(2) Hi-ear fittings are designed for use with 14 mm maximum width strap.

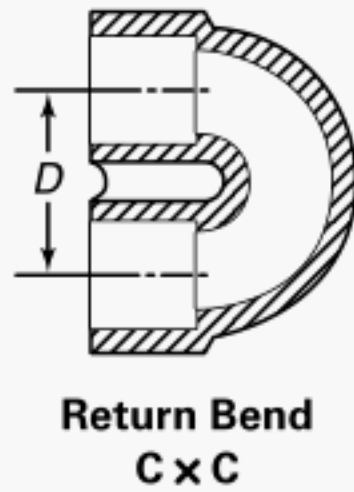**TABLE B13 DIMENSIONS OF RETURN BENDS (STRAIGHT SIZES)**


Standard Water Tube Sizes [Note (1)]	Center-to-Center, <i>D</i>
$\frac{1}{2}$	25.5
$\frac{3}{4}$	33.5
1	47.5
$1\frac{1}{4}$	51.0
$1\frac{1}{2}$	63.5
2	76.0
3	101.5
4	127.0

GENERAL NOTES:

- (a) Dimensions are in millimeters.
 (b) For dimensions not given in this table, see Table B3.

NOTE:

- (1) For size designation of fitting, see Section 4.

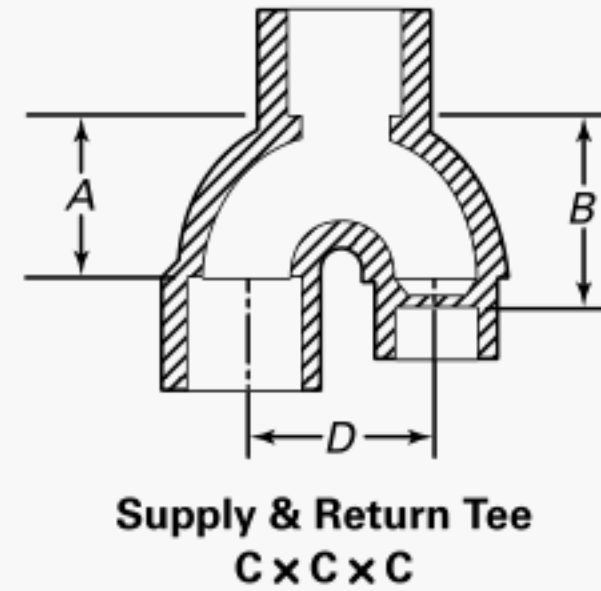**TABLE B14 DIMENSIONS OF SUPPLY AND RETURN TEES**


Standard Water Tube Size [Note(1)]	Laying Lengths		Center-to-Center, <i>D</i>
	<i>A</i>	<i>B</i>	
$\frac{1}{2}$	20.5	20.5	25.5
$\frac{3}{4}$	28.0	28.0	33.5
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$	28.0	28.0	33.5
$\frac{3}{4} \times \frac{1}{2} \times \frac{1}{2}$	28.0	32.5	33.5

GENERAL NOTES:

- (a) Dimensions are in millimeters.
 (b) For dimensions not given in this table, see Table B3.
 (c) For inspection tolerances, see Section 8 and Table 2.

NOTE:

- (1) For size designation of fittings, see Section 4.

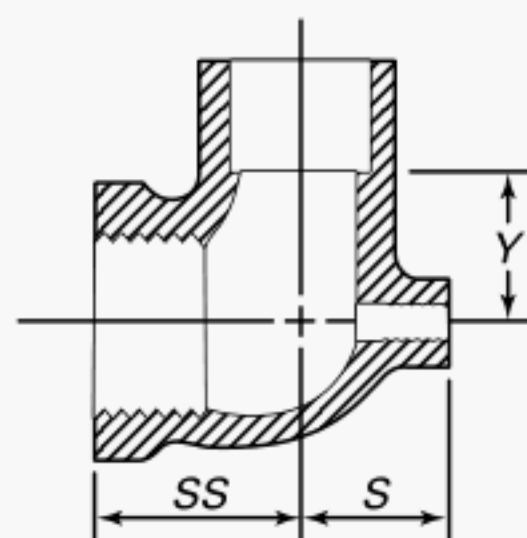

Baseboard Tee
F x F x C

TABLE B15 DIMENSIONS OF BASEBOARD TEES


Standard Water Tube Size [Note (1)]	Laying Lengths		
	SS	S	Y
$\frac{1}{2} \times \frac{1}{8} \times 1$	28.5	20.5	14.5
$\frac{1}{2} \times \frac{1}{8} \times \frac{3}{4}$	24.0	17.5	14.5
$\frac{3}{4} \times \frac{1}{8} \times 1$	30.0	20.5	17.5
$\frac{3}{4} \times \frac{1}{8} \times \frac{3}{4}$	25.5	17.5	17.5
$1\frac{1}{4} \times \frac{1}{8} \times 1\frac{1}{4}$	47.0	24.0	22.0

GENERAL NOTES:

- (a) Dimensions are in millimeters.
 (b) For dimensions not given in this table, see Table B3.
 (c) For inspection tolerances, see Section 8 and Table 2.

NOTE:

- (1) For size designation of fittings, see Section 4.

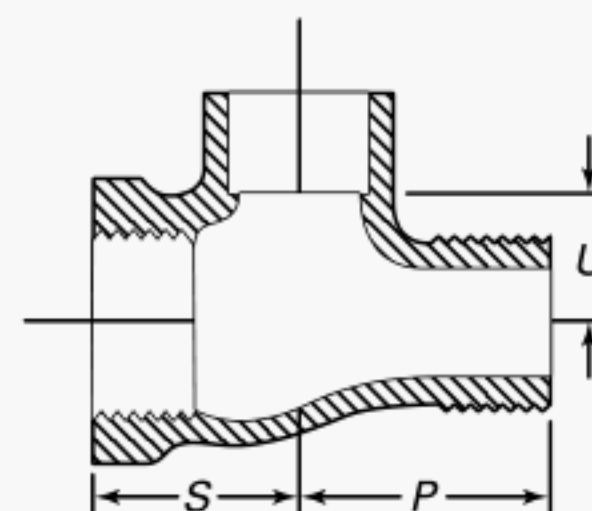

Tee
F x M x C

TABLE B16 DIMENSIONS OF TEES


Standard Water Tube Size [Note (1)]	Laying Lengths		
	U	P	S
$\frac{1}{2} \times \frac{3}{4} \times \frac{1}{2}$	17.5	31.0	24.5
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$	17.5	34.0	25.5
$\frac{3}{4} \times \frac{3}{4} \times \frac{1}{2}$	17.5	31.0	24.5

GENERAL NOTES:

- (a) Dimensions are in millimeters.
 (b) For dimensions not given in this table, see Table B3.
 (c) For inspection tolerances, see Section 8 and Table 2.

NOTE:

- (1) For size designation of fittings, see Section 4.

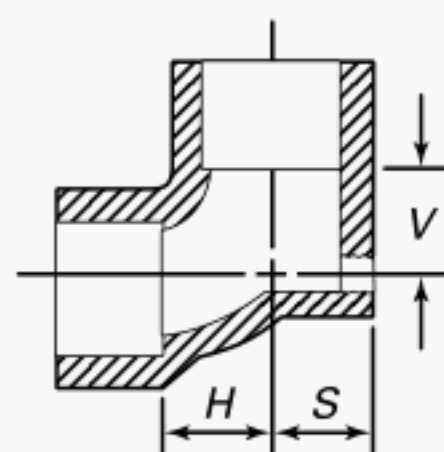

Baseboard Tee
C x F x C

TABLE B17 DIMENSIONS OF BASEBOARD TEES


Standard Water Tube Size [Note (1)]	Laying Lengths		
	H	S	V
$\frac{3}{8} \times \frac{1}{8} \times \frac{3}{8}$	15.0	24.5	15.0
$\frac{1}{2} \times \frac{1}{8} \times 1$	19.0	20.5	11.0
$\frac{1}{2} \times \frac{1}{8} \times \frac{3}{4}$	14.5	17.5	11.0
$\frac{1}{2} \times \frac{1}{8} \times \frac{1}{2}$	11.0	14.5	11.0
$\frac{3}{4} \times \frac{1}{8} \times 1\frac{1}{4}$	20.5	24.0	14.5
$\frac{3}{4} \times \frac{1}{8} \times 1$	19.0	20.5	16.0
$\frac{3}{4} \times \frac{1}{8} \times \frac{3}{4}$	11.0	17.5	11.0
$1 \times \frac{1}{8} \times 1$	18.0	19.0	15.0
$1\frac{1}{4} \times \frac{1}{8} \times 1\frac{1}{4}$	22.0	24.0	22.0

GENERAL NOTES:

- (a) Dimensions are in millimeters.
 (b) For dimensions not given in this table, see Table B3.
 (c) For inspection tolerances, see Section 8 and Table 2.

NOTE:

- (1) For size designation of fittings, see Section 4.

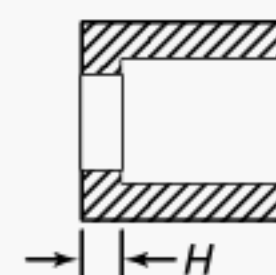

Flush Bushing
FTG x C

TABLE B18 DIMENSIONS OF FLUSH BUSHINGS


Standard Water Tube Size [Note (1)]	Laying Length [Note (1)], H
$\frac{1}{4} \times \frac{1}{8}$	2.0
$\frac{3}{8} \times \frac{1}{4}$	2.0
$\frac{1}{2} \times \frac{3}{8}$	2.5
$\frac{1}{2} \times \frac{1}{4}$	6.5
$\frac{5}{8} \times \frac{1}{2}$	2.0
$\frac{3}{4} \times \frac{5}{8}$	5.0
$\frac{3}{4} \times \frac{1}{2}$	2.5
$\frac{3}{4} \times \frac{3}{8}$	11.0
$1 \times \frac{3}{4}$	3.0
$1 \times \frac{1}{2}$	12.0
$1\frac{1}{4} \times 1$	2.5
$1\frac{1}{2} \times 1\frac{1}{4}$	4.0
$2 \times 1\frac{1}{2}$	3.0

GENERAL NOTES:

- (a) Dimensions are in millimeters.
 (b) For dimensions not given in this table, see Table B3.
 (c) For inspection tolerances, see Section 8 and Table 2.

NOTE:

- (1) For size designation of fittings, see Section 4.

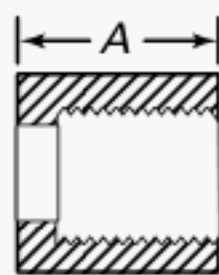

Flush Bushing
FTG x F

TABLE B19 DIMENSIONS OF FLUSH BUSHINGS

Standard Water Tube Size [Note (1)]	Laying Length, A
$\frac{1}{2} \times \frac{1}{8}$	14.0
$\frac{3}{4} \times \frac{3}{8}$	20.5
$1 \times \frac{1}{2}$	24.5
$1\frac{1}{4} \times \frac{3}{4}$	26.0
$1\frac{1}{2} \times 1$	29.5
$2 \times 1\frac{1}{2}$	35.5

GENERAL NOTES:

- (a) Dimensions are in millimeters.
- (b) For dimensions not given in this table, see Table B3.
- (c) For inspection tolerances, see Section 8 and Table 2.

NOTE:

- (1) For size designation of fittings, see Section 4.

NONMANDATORY ANNEX C FITTING RATING

The rated internal working pressures of the fitting are shown in Table 1. These values are the same as those calculated for annealed temper ASTM B88 Type L copper water tube. The rated internal working pressures for annealed temper ASTM B88 Type L copper water tube are calculated as follows:

$$P = \frac{2St}{D - 0.8t}$$

- P = rated working pressure at temperature, psi
- S = allowable stress at temperature, psi from ASME B31.1 or ASME B31.9 for annealed temper ASTM B88 Type L copper water tube
- D = maximum outside diameter, in. from annealed temper ASTM B88 for Type L copper water tube
- t = minimum wall thickness, in. from annealed temper ASTM B88 for Type L copper water tube

NONMANDATORY ANNEX D REFERENCES

The following is a list of standards and specifications referenced in this Standard showing the year of approval.

ASME B1.20.1-1983 (R92), Pipe Threads, General Purpose (Inch)¹

ASME B16.3-1998, Malleable Iron Threaded Fittings¹

ASME B16.15-1985 (R94), Cast Bronze Threaded Fittings, 125 and 250 lb¹

Publisher: The American Society of Mechanical Engineers (ASME International), Three Park Avenue, New York, NY 10016-5990

ASTM B 32-96, Specification for Solder Metal

ASTM B 62-93, Specification for Composition Bronze or Ounce Metal Castings

ASTM B 88-99, Specification for Seamless Copper Water Tube

ASTM B 584-98a, Specification for Copper Alloy Sand Castings for General Applications

ASTM E 29-93a (R1999), Standard Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications

Publisher: American Society for Testing and Materials (ASTM), 100 Barr Harbor Drive, West Conshohocken, PA 19428-2959

ISO 9000-1: 1994, Quality management and quality assurance standards — Part 1: Guidelines for selection and use

ISO 9000-2: 1997, Quality management and quality assurance standard — Part 2: Generic guidelines for the application of ISO 9001, ISO 9002, and ISO 9003

ISO 9000-3:1997, Quality management and quality assurance standards — Part 3: Guidelines for the application of ISO 9001 to the development, supply and maintenance of software

ISO 9001: 1994, Quality systems — Model for quality assurance in design, development, production, installation, and servicing

ISO 9002: 1994, Quality systems — Model for quality assurance in production and servicing

ISO 9003: 1994, Quality systems — Model for quality assurance in final inspection and test

Publisher: International Organization for Standardization (ISO), 1 rue de Varembe, Case Postale 131, CH-1211, Genève 20, Switzerland/Suisse

MSS SP-25-1998, Standard Marking System for Valves, Fittings, Flanges and Unions

Publisher: Manufacturers Standardization Society of the Valve and Fittings Industry (MSS), 127 Park Street, N.E., Vienna, VA 22180

¹ May also be obtained from American National Standards Institute (ANSI), 11 West 42nd Street, New York, NY 10036.

NONMANDATORY ANNEX E QUALITY SYSTEM PROGRAM

The products manufactured in accordance with this Standard shall be produced under a quality system program following the principles of an appropriate standard from the ISO 9000 series.¹ A determination of the need for registration or certification of the product

¹ The series is also available from the American National Standard Institute (ANSI) and the American Society for Quality Control (ASQC). As American National Standards that are identified by the prefix "Q," replacing the prefix "ISO." Each standard of the series is listed under Appendix II, References.

manufacturer's quality system program by an independent organization, or both, shall be the responsibility of the manufacturer. The detailed documentation demonstrating program compliance shall be available to the purchaser at the manufacturer's facility. A written summarized description of the program utilized by the product manufacturer shall be available to the purchaser upon request. The product manufacturer is defined as the entity whose name, or trademark, appears on the product in accordance with the marking or identification requirements of this standard.

AMERICAN NATIONAL STANDARDS FOR PIPING, PIPE FLANGES, FITTINGS, AND VALVES

Scheme for the Identification of Piping Systems.....	A13.1-1996
Pipe Threads, General Purpose (Inch).....	B1.20.1-1983(R1992)
Dryseal Pipe Threads (Inch).....	B1.20.3-1976(R1998)
Cast Iron Pipe Flanges and Flanged Fittings: Classes 25, 125, and 250.....	B16.1-1998
Malleable Iron Threaded Fittings: Classes 150 and 300.....	B16.3-1998
Gray Iron Threaded Fittings: Classes 125 and 250.....	B16.4-1998
Pipe Flanges and Flanged Fittings (NPS ½ Through NPS 24).....	B16.5-1996
Factory-Made Wrought Butt welding Fittings.....	B16.9-2001
Face-to-Face and End-to-End Dimensions of Valves.....	B16.10-2000
Forged Fittings, Socket-Welding and Threaded.....	B16.11-2001
Cast Iron Threaded Drainage Fittings.....	B16.12-1998
Ferrous Pipe Plugs, Bushings, and Locknuts with Pipe Threads.....	B16.14-1991
Cast Bronze Threaded Fittings: Classes 125 and 250.....	B16.15-1985(R1994)
Cast Copper Alloy Solder Joint Pressure Fittings.....	B16.18-2001
Metallic Gaskets for Pipe Flanges: Ring-Joint, Spiral-Wound, and Jacketed.....	B16.20-1998
Nonmetallic Flat Gaskets for Pipe Flanges.....	B16.21-1992
Wrought Copper and Copper Alloy Solder Joint Pressure Fittings.....	B16.22-1995
Cast Copper Alloy Solder Joint Drainage Fittings — DWV.....	B16.23-1992
Cast Copper Alloy Pipe Flanges and Flanged Fittings: Class 150, 300, 400, 600, 900, 1500, and 2500.....	B16.24-2001
Butt welding Ends.....	B16.25-1997
Cast Copper Alloy Fittings for Flared Copper Tubes.....	B16.26-1988
Wrought Steel Butt welding Short Radius Elbows and Returns.....	B16.28-1994
Wrought Copper and Wrought Copper Alloy Solder Joint Drainage Fittings — DWV.....	B16.29-1994
Manually Operated Metallic Gas Valves for Use in Gas Piping Systems up to 125 psig (Sizes ½ Through 2).....	B16.33-1990
Valves — Flanged, Threaded, and Welding End.....	B16.34-1996
Orifice Flanges.....	B16.36-1996
Large Metallic Valves for Gas Distribution (Manually Operated, NPS 2½ to 12, 125 psig Maximum).....	B16.38-1985(R1994)
Malleable Iron Threaded Pipe Unions.....	B16.39-1998
Manually Operated Thermoplastic Gas Shutoffs and Valves in Gas Distribution Systems.....	B16.40-1985(R1994)
Functional Qualification Requirements for Power Operated Active Valve Assemblies for Nuclear Power Plants.....	B16.41-1983(R1989)
Ductile Iron Pipe Flanges and Flanged Fittings, Classes 150 and 300.....	B16.42-1998
Manually Operated Metallic Gas Valves for Use in House Piping Systems.....	B16.44-1995
Cast Iron Fittings for Sovent® Drainage Systems.....	B16.45-1998
Large Diameter Steel Flanges (NPS 26 Through NPS 60).....	B16.47-1996
Steel Line Blanks.....	B16.48-1997
Factory-Made Wrought Steel Butt welding Induction Bends for Transportation and Distribution Systems.....	B16.49-2000
Power Piping.....	B31.1-1998
Fuel Gas Piping (not an ANSI standard).....	B31.2-1968
Process Piping.....	B31.3-1999
Pipeline Transportation Systems for Liquid Hydrocarbons and Other Liquids.....	B31.4-1998
Refrigeration Piping and Heat Exchanger Components.....	B31.5-2000
Gas Transmission and Distribution Piping Systems.....	B31.8-1999
Building Services Piping.....	B31.9-1996
Slurry Transportation Piping Systems.....	B31.11-1989(R1998)
Manual for Determining the Remaining Strength of Corroded Pipelines.....	B31G-1991
Welded and Seamless Wrought Steel Pipe.....	B36.10M-1996
Stainless Steel Pipe.....	B36.19M-1985(R1994)
Self-Operated and Power-Operated Safety-Related Valves Functional Specification Standard.....	N278.1-1975(R1992)

The ASME Publications Catalog shows a complete list of all the Standards published by the Society. For a complimentary catalog, or the latest information about our publications, call 1-800-THE-ASME (1-800-843-2763).

ASME Services

ASME is committed to developing and delivering technical information. At ASME's Information Central, we make every effort to answer your questions and expedite your orders. Our representatives are ready to assist you in the following areas:

ASME Press	Member Services & Benefits	Public Information
<i>Codes & Standards</i>	Other ASME Programs	Self-Study Courses
Credit Card Orders	Payment Inquiries	Shipping Information
IMechE Publications	Professional Development	Subscriptions/Journals/Magazines
Meetings & Conferences	Short Courses	Symposia Volumes
Member Dues Status	Publications	Technical Papers

How can you reach us? It's easier than ever!

There are four options for making inquiries* or placing orders. Simply mail, phone, fax, or E-mail us and an Information Central representative will handle your request.

<i>Mail</i>	<i>Call Toll Free</i>	<i>Fax—24 hours</i>	<i>E-Mail—24 hours</i>
ASME	US & Canada: 800-THE-ASME	973-882-1717	Infocentral@asme.org
22 Law Drive, Box 2900	(800-843-2763)	973-882-5155	
Fairfield, New Jersey	Mexico: 95-800-THE-ASME		
07007-2900	(95-800-843-2763)		
	Universal: 973-882-1167		

* Information Central staff are not permitted to answer inquiries about the technical content of this code or standard. Information as to whether or not technical inquiries are issued to this code or standard is shown on the copyright page. All technical inquiries must be submitted in writing to the staff secretary. Additional procedures for inquiries may be listed within.

ISBN 0-7918-2729-1



9 780791 827291



J07101